

The carbon dioxide removal potential of cement and lime kiln dust via ocean alkalinity enhancement

Gunter Flipkens^{1*}, Greet Lembregts¹ and Filip J.R. Meysman¹

¹Geobiology, Department of Biology, University of Antwerp, Antwerp, Belgium

5 Correspondence to: Gunter Flipkens (Gunter.Flipkens@uantwerpen.be)

Keywords: ocean liming, ocean alkalinity enhancement, CDR, cement kiln dust, lime kiln dust

Abstract. Ocean alkalinity enhancement (OAE) is a proposed method for atmospheric carbon dioxide removal (CDR), and involves the addition of alkaline minerals to surface waters to elevate seawater alkalinity and enhance atmospheric CO₂ storage. Cement kiln dust (CKD) and lime kiln dust (LKD) are alkaline side streams from the cement and lime industry that

10 have OAE potential due to their widespread availability and fine particle size. Here, we evaluated the dissolution kinetics, CO₂ sequestration potential, and ecological risks of CKD and LKD by means of laboratory dissolution experiments. A reactive fraction (~25 % in LKD and ~29 % in CKD) dissolved rapidly within 24 hours, with most dissolution occurring within the first hour. Dissolution provided a concomitant alkalinity release that was higher for LKD (up to 8.0 ± 0.5 mmol alkalinity per g) than CKD (2.4 ± 0.2 mmol g⁻¹), thus providing a sizeable CO₂ sequestration capacity for LKD (297 ± 20 g CO₂ per kg) and
15 CKD (88 ± 6 g CO₂ per kg). Based on current industrial production rates, this translates into global CDR potentials of up to 8.7 ± 0.6 Mt CO₂ yr⁻¹ for LKD and 25 ± 2 Mt CO₂ yr⁻¹ for CKD. These estimates, suggesting that both materials could serve as viable OAE feedstocks, although further testing under conditions that more closely mimic natural coastal conditions is needed. Furthermore, we hypothesize that the substantial residual calcite content of LKD (~54 %) and CKD (~37 %) may provide additional sequestration via metabolic dissolution in marine sediments. However, kiln dust deployment will generate
20 elevated turbidity levels that may exceed environmental thresholds, underscoring the need for carefully designed application strategies to minimize local ecological impacts.

1 Introduction

As global temperatures continue to rise, the urgency for climate mitigation increases (IPCC, 2023). In addition to substantial cuts in greenhouse gas emissions, gigaton-scale atmospheric carbon dioxide removal (CDR) is needed to meet the goals of the
25 Paris Agreement (Rockström et al., 2017; Minx et al., 2018; IPCC, 2023). One proposed CDR method is mineral-based ocean alkalinity enhancement (OAE), which offers considerable removal potential and long-term CO₂ storage (Kheshgi, 1995; Renforth and Henderson, 2017). Mineral-based OAE targets the addition of specific basic minerals to the surface ocean, which

release alkalinity upon dissolution, thereby stimulating oceanic CO₂ uptake (Renforth and Henderson, 2017; Geerts et al., 2025).

30 A variety of minerals have been proposed as feedstock for mineral-based OAE, and approaches largely fall into two categories. So-called “enhanced weathering” techniques target the addition of natural rock material containing silicates (e.g. olivine Mg₂SiO₄) or carbonates (e.g. calcite CaCO₃) to sediments, which then slowly dissolve up or in the seabed over a time scale of years to decades (Montserrat et al., 2017; Flipkens et al., 2023; Dale et al., 2024; Fuhr et al., 2025; Geerts et al., 2025). In contrast, “ocean liming” procedures involve the addition of industrially processed minerals such as slaked lime (Ca(OH)₂) or
35 brucite (Mg(OH)₂), thus targeting a much faster alkalinity release upon dissolution in the water column over a time scale of minutes to hours (Renforth et al., 2013; Renforth and Henderson, 2017; Caserini et al., 2021; Foteinis et al., 2022; Kitidis et al., 2024). Slaked lime is produced by calcining limestone (CaCO₃) to form quicklime (CaO) (Eq. (1)), which is then hydrated (Eq. (2)) (Moras et al., 2022).



Upon dissolution in seawater, slaked lime releases alkalinity and binds CO₂ in the form of bicarbonate (HCO₃⁻).



Ocean liming has the benefit of rapid ~~CO₂ sequestration~~ seawater alkalization upon deployment, and offers the potential to remove gigatons of atmospheric CO₂ annually, with ample global reserves to support deployment (Caserini et al., 2022; Foteinis et al., 2022). However, large-scale deployment would require a substantial increase in limestone mining and lime production, carrying significant economic and environmental costs (Caserini et al., 2021; Foteinis et al., 2022). As a result, industrial by-products and mine tailings are attracting a growing interest for CDR applications, thanks to their lower processing costs, and alignment with circular economy principles (Bullock et al., 2021; Bullock et al., 2022; Moras et al., 2024).

The cement and lime industries are among the largest mineral production sectors globally, producing approximately 4.1 Gt of cement and 0.42 Gt of lime annually (CEMBUREAU, 2024; USGS, 2025). Both rely on the high-temperature calcination of limestone in kilns to produce quicklime and cement clinker. This process generates fine particulate kiln dust, which is captured by air pollution control systems for recycling or disposal (Arulrajah et al., 2017; Barnat-Hunek et al., 2018). Kiln dust accounts

for 2–20 % of the kiln output, depending on process conditions and gas flow rates (Al-Refeai and Al-Karni, 1999; Elbaz et al., 2019; Al-Bakri et al., 2022; Ahmed et al., 2023). Lime kiln dust (LKD) mainly consists of unreacted limestone (CaCO_3) and calcium (hydr)oxides (CaO or $\text{Ca}(\text{OH})_2$), while cement kiln dust (CKD) is a mix of unreacted feedstock, clinker dust, fuel ash, halides, and other volatiles (Sreekrishnavilasam et al., 2006; Ban et al., 2022). Both types of kiln dust contain a substantial fraction of CaO , and $\text{Ca}(\text{OH})_2$, which hence provides alkalization potential upon addition to seawater (Eq. (3)).

Hence, given their large-scale production, LKD and CKD show a potential as feedstocks for OAE, which is investigated and quantified here through laboratory experiments. OAE suitability was assessed by: (1) evaluating dissolution kinetics and alkalinity generation in seawater, and (2) monitoring changes in seawater properties during dissolution, specifically turbidity, trace elements, and pH increases. These effects were compared to existing environmental guidelines to assess potential risks to marine ecosystems.

2 Material and methods

2.1 Solid phase characterization

The CKD and LKD were oven-dried at 40°C for 72 h before experimental use. Grain size distribution was determined with a Malvern Mastersizer 3000 equipped with a Hydro LV dispersion system and operated at a stirring speed of 3000 RPM and no sonication prior to measurement. The dry solid phase density of the kiln dust was determined by measuring water displacement in a graduated cylinder (Dan-Asabe et al., 2013). To characterize the elemental composition, a 125 mg aliquot of dry, ball-milled ($<2 \mu\text{m}$) kiln dust was added to Teflon vessels and digested overnight at 90°C in a heat block with a mixture of 1.5 mL HClO_4 , 1 mL HNO_3 , and 2.5 mL HF. After cooling, the caps were removed, and the vessels were heated to 140°C to evaporate HF, leaving a gel-like residue. Next, 25 mL of 4.5 % HNO_3 was added to each vessel, which was then capped and heated at 90°C for 2 hours. The resulting solutions were diluted and analyzed for elemental composition using ICP-OES (Avio 500, Perkin-Elmer) at the GeoLab (Utrecht University, The Netherlands). Quality control measures included a blank, two certified river clay standards (ISE 921), and a duplicate sample. Recorded elemental concentration were between 98 and 109 % of certified values. The mineralogical composition of the samples was determined in duplicate via quantitative X-ray diffraction (XRD) on a Bruker D8 Advance Eco diffractometer ($\text{Cu K}\alpha$, 40 kV, 25 mA) over 5–70° 2 θ with 0.015° steps and 0.5 s per

step. Samples were rotated at 10 rpm using a 10 mm variable divergence slit, and patterns were recorded with a LynxEye XE-T detector. Phase identification and quantification were performed using EVA and TOPAS (Bruker, V7). The BET specific surface area was determined by N₂ adsorption using a Quantachrome NOVA 2200E at the laboratory for Process Engineering for Sustainable Systems (KU Leuven, Belgium). The geometric specific surface area was calculated from the grain size distribution results (Appendix A Sect. A1). Finally, the grain morphology and presence of secondary minerals on kiln dust grains recovered from the dissolution experiments were analyzed via Scanning Electron Microscopy (SEM) using a Phenom ProX SEM equipped with an energy dispersive spectrometer (EDS), operated at an accelerating voltage of 15 kV. For SEM analysis, the dried kiln dust was mounted on aluminum (Al) pin stubs using double-sided carbon tape.

85 2.2 Dissolution experiments

The dissolution kinetics of LKD and CKD in seawater were assessed in two separate experiments (Table 1), hereafter referred to as experiments I and II. In experiment I, the short-term dissolution behaviour was tracked via continuous pH monitoring. Filtered (<0.2 µm) seawater from the Eastern Scheldt (saline water body in The Netherlands adjacent to the North Sea; salinity 32.3 ± 0.5) was obtained from Stichting Zeeschelp (Kamperland, The Netherlands). The filtered seawater (FSW) was aerated for 24 hours before use, yielding an initial seawater pCO₂ of 458–557 µatm The filtered seawater (FSW) was aerated for 24 hours before use to ensure atmospheric CO₂-equilibration. The initial seawater pH on a total scale (pH₀) and total alkalinity (A_T) were analysed (as described in Sect. 2.3). For A_T analysis, 55 mL seawater was collected in duplicate using a 60 mL plastic syringe, and filtered (0.8/0.2 µm polyethersulfone (PES) membrane). Based on preliminary tests, three different masses concentrations of CKD (30, 130, and 309 mg kg⁻¹) and LKD (11, 48, and 113 mg kg⁻¹) were added selected to targeting 95 a specific aragonite saturation states ($\Omega_{\text{Arg}} = 3.6, 5.7$ and 9.7) at the end (final concentration and estimated Ω_{Arg} are provided in Table 1). Experiment I was carried out in triplicate. Kiln dusts were weighed in small aluminium (Al) foil cups using a micro balance (XP26 Excellence Plus, Mettler Toledo) and then transferred to 200 mL polystyrene vials with polyethylene screw caps containing approximately 200 mL of FSW. These small-scale laboratory experiments provide a high-throughput, cost-effective first assessment of a material's suitability for OAE. Vials were weighed on an analytical balance (Sartorius 100 TE3102S) to precisely determine the mass of added seawater. Plastic vials were rinsed with 0.5 M HCl and ultrapure water (PURELAB® flex 3, Elga Veolia) before usage. The pH electrode was inserted through a hole in the vial cap, which fit tightly

Formatted: Subscript

Formatted: Superscript

Formatted: Superscript

to minimize atmospheric CO₂ exchange. Vials were wrapped in tape to block light and contained minimal headspace.

Subsequently, the pH_T of the suspension was measured every minute over a period 8 hours (see pH_T measurement procedure below). Seawater temperature was kept constant at 20°C during the incubation by means of a water bath (T100, Grant).

Formatted: Subscript

105 Magnetic stirring was applied at a rate of 700 rotation per minute (RPM) to ensure good mixing of the suspension and to create optimal dissolution conditions. At the end of experiment I (after ~8 hours)-, vials were opened and 55 mL of seawater was collected in duplicate for A_T analysis. Salinity was measured, and the samples were subsequently analysed for A_T (see Sect. 2.3).

To assess the alkalinity generation potential and the possibility of secondary mineral formation, we conducted a second, longer-term dissolution experiment with incubation periods of one and 15 days. The one-day (i.e. 24 h) incubation reflects the time needed for ensured complete dissolution of the reactive phases in the kiln dusts, while the 15-day incubation allows for the verification of secondary mineral precipitation, in case this would occur. At the start of experiment II, clean 200 mL plastic vials were again filled with 200 mL of FSW on an analytical balance (TE3102S, Sartorius). Different amounts of LKD (11–

111 111 mg kg⁻¹) and CKD (30–308 mg kg⁻¹) were added to achieve a target Ω_{Arg} ranging from 3.6 to 9.7 (Table 1). A control

115 containing only 200 mL of FSW without kiln dust was also included. Vials were closed tightly and had minimal headspace to minimize gas exchange with the atmosphere. Experiment II was conducted in triplicate at ambient room temperature (17.5–22.7 °C). Vials were subsequently incubated on bottle rollers (ThermoFisher Scientific) for 1 or 15 days at 14 RPM, a speed sufficient to keep particles suspended and ensure optimal dissolution conditions. Vials were subsequently placed on bottle rollers (ThermoFisher Scientific) at 14 RPM and incubated for either one or 15 days. The one-day incubation reflects the time

120 needed for complete dissolution of the reactive phases in the kiln dusts, while the 15-day incubation allows for the verification of secondary mineral precipitation, in case this would occur. Duplicate samples for seawater A_T, dissolved inorganic carbon (DIC), dissolved metals, turbidity, and A_T and dissolved metal analysis were collected on both sampling days by drawing water with a syringe right after opening the vials in duplicate on both sampling days. analytical procedures are described in Sect. 2.3. DIC samples were collected first to minimize the exposure time to the atmosphere. Nevertheless, some CO₂ exchange

Formatted: Font color: Auto

125 inevitably occurred during the incubations because the vials contained a small headspace, meaning the solutions could partially re-equilibrate with the air. However, this also reflects natural deployment conditions, where atmospheric CO₂ exchange occurs

Formatted: Subscript

alongside alkalinization, although at a slower rate. Samples for Ar, DIC, and dissolved metals were filtered using 0.8/0.2 μm PES membrane filters. DIC samples (12 mL) were fixed with 10 μL of saturated HgCl_2 solution and stored at 4°C in 12 mL exetainers until analysis. Dissolved metal samples were acidified with TraceMetal™ Grade 67–69 % nitric acid to a final acid concentration of 1.4 % (v/v) and stored at -20°C prior until analysis. The remaining suspension in the incubation vials was filtered through a 0.2 μm polycarbonate membrane filter to collect solids, which were rinsed with deionized water and then oven dried at 40°C in preparation for SEM-EDX analysis (see Sect. 2.1).

Table 1. Experimental specifications of the two dissolution experiments (I and II). Target aragonite saturation state (Ω_{Arg}), concentrations of lime kiln dust (LKD), cement kiln dust (CKD), incubation time and temperature, and seawater stirring method are provided.

Exp.	Target	LKD	CKD	Incubation	Temperature	Stirring
	Ω_{Arg} concentration	concentration	time (days)	(°C)	method	
	(mg kg^{-1})	(mg kg^{-1})				
I	3.6	10.9	29.9	0.33	20	Magnetic
					(700 RPM)	
	5.7	47.7	130.3			
	9.7	113.07	309.2			
II	3.0	0	0	1 or 15	17.5–22.7	Rotation
					(14 RPM)	
H	3.6	10.75	30.12	1 or 15	17.5–22.7	Rotation
					(14 RPM)	
	4.2	20.96	47.93			
	5.2	37.15	88.85			
	5.7	46.49	129.12			
	7	69.12	191.81			



2.3 Seawater physicochemical analyses

Seawater salinity and pH_{L} were measured with an OrionTM DuraProbeTM 4-Cell conductivity probe (Thermo Scientific) and Unitrode pH electrode (Metrohm) connected to an Orion Star A215 pH/conductivity meter. The pH electrode was calibrated 140 using 35 salinity TRIS (2-amino-2-hydroxy-1,3-propanediol) and AMP (2-aminopyridine) buffers, and the pH_{L} was calculated
 on the total hydrogen ion scale following Dickson et al. (2007).

For A_T analysis, samples were titrated with 0.1 M HCl using an automated titrator setup (888 Titrando with 814 USB Sample Processor, Metrohm). The titrant was calibrated with certified reference material (batch 209; OCADS). A_T was derived from the titrant volume and electromotive force measurements recorded by the Unitrode pH electrode, using a non-linear least-squares method as described by Dickson et al. (2007). Blank FSW samples were analyzed at the start of the run, after every 145 tenth sample, and at the end for quality control, yielding relative standard deviations (RSD) smaller than 1.1 %. The specific A_T release $\Delta N_{\text{AT}}(t)$ at a given incubation time t , and expressed in mmol A_T per g of kiln dust, was derived via

$$\Delta N_{\text{AT}}(t) = (\text{A}_\text{T}(t) - \text{A}_\text{T}(t_0)) \frac{m_{\text{FSW}}}{m_{\text{KD}}} \quad (4)$$

Here, $\text{A}_\text{T}(t)$ represents the seawater alkalinity (mmol kg⁻¹) at a given incubation time, $\text{A}_\text{T}(t_0)$ is the alkalinity (mmol kg⁻¹) of 150 the blank FSW at the start of the experiment, m_{FSW} is the mass of FSW added to the incubation vials (kg), and m_{KD} is the mass of added kiln dust (g).

In experiment I, the A_T was only measured at the begin and end of the experiment, and so only one $\Delta N_{\text{AT}}(t)$ value can be calculated. To verify the observed alkalinity release, we calculated a theoretical value based on measured pH_{L} . To this end, the initial DIC of the seawater was first calculated from measured values of pH_{L} , A_T , temperature, and salinity using the AquaEnv 155 package in R with default settings (Hofmann et al., 2010). Under the assumption that DIC remained constant throughout the experiment, the corresponding A_T was then calculated from the measured pH_{L} and fixed DIC. The difference between this

Formatted: Font: 10 pt

Formatted: Subscript

calculated A_T and the starting A_T was used to compute $\Delta N_{AT}(t)$, and the value at the end (8 hours) was compared to the measured $\Delta N_{AT}(t)$.

For experiment I, the fraction of reactive phases in the kiln dust that dissolved over time, $\chi_{diss}(t)$ (%), was determined by

160 normalizing $\Delta N_{AT}(t)$ to the maximum experimentally observed specific A_T increase ($\Delta N_{AT,max}$):

$$\chi_{diss}(t) = \frac{\Delta N_{AT}(t)}{\Delta N_{AT,max}} \cdot 100 \quad (5)$$

Seawater DIC concentrations were measured using a DIC analyzer (AS-C6L, Apollo SciTech) coupled to a trace gas analyzer (LI-7815, LI-COR). Measurements were repeated until the relative standard deviation (RSD) for at least three repeats was ≤ 0.1 %. DIC concentrations were determined using a calibration curve based on an internal standard solution (0.002 M NaHCO_3)

165 adjusted to a salinity of 30 ppt with NaCl and spiked with 0.05 % (v/v) saturated HgCl_2 . This internal standard was calibrated against certified reference material (CRM; batch 209, OCADS). For quality control, CRM (batch 209, OCADS) was analyzed at the start and end of the sequence, and the internal standard was run at the start and after every eight samples. Quality control checks consistently yielded an RSD ≤ 0.25 %.

The remaining seawater carbonate chemistry parameters, including the aragonite and calcite saturation state and seawater $\text{pH}_{T,}$

Formatted: Subscript

170 ~~on a total scale~~, were calculated using the AquaEnv package in R (Hofmann et al., 2010). Measured A_T , DIC, salinity, and temperature were given as input values, with all other parameters set to their default values.

Seawater samples for dissolved trace metal analysis were thawed and diluted 20-fold with 2 % (v/v) TraceSELECT™ HNO_3 (Honeywell Fluka) to a final volume of 10 mL. Before analysis, samples were spiked with 100 μL of an internal standard solution (10 ppm Y; Alfa Aesar) and analyzed using high-resolution inductively coupled plasma mass spectrometry (HR-ICP-175 MS; Agilent 7850) at the ELCAT group, University of Antwerp, Belgium.

Seawater turbidity was measured with a HI98713 ISO portable turbidity meter (Hanna Instruments) which was calibrated with four turbidity standards (<0.1, 15, 100, and 750 FNU, Hanna Instruments) before each use.

2.4 Saturation state calculations

Saturation ~~state (Ω) index (SI)~~ values for kiln dust mineral phases were calculated using PHREEQC Interactive (version 3.7.3-

180 15968) with the LLNL thermodynamic database (Parkhurst and Appelo, 2013). Saturation indices were converted to saturation

states (Ω) according to $\Omega = 10^{SI}$. Input parameters included measured seawater temperature, salinity, A_T , and pH_T . Major constituent concentrations (Cl, Na, Mg, K, Ca, SO_4) were derived based on the average composition of natural seawater, scaled to measured salinity (Hem, 1985). Aragonite and calcite saturation states were not computed in PHREEQC but were instead calculated using the AquaEnv package in R, as described previously (Hofmann et al., 2010). [AquaEnv uses carbonic acid dissociation constants from](#) Lueker et al. (2000) [and solubility product constants for \$CaCO_3\$ from](#) Mucci (1983), [which differ from the thermodynamic data used in the LLNL PHREEQC database to describe the carbonate system. We used the AquaEnv approach to remain consistent with the methodology commonly applied in most OAE studies.](#)

185 Formatted: Subscript

2.5 Statistical analyses

Differences in seawater physico-chemistry across kiln dust concentrations and incubation times were assessed using two-way
190 analysis of variance (ANOVA). The best fitting models were determined by the ANOVA and the lowest Akaike Information Criterion (AIC). Normality and homoscedasticity of residuals were evaluated both visually (via QQ and residual plots) and statistically (via Shapiro-Wilk and Levene's tests). Post-hoc pairwise comparisons were performed using estimated marginal means (EMMs) with Holm-adjusted p-values. Comparisons were conducted within each concentration, adjusting for incubation time, and vice versa. Data are presented as mean \pm standard deviation (S.D.), unless otherwise specified. All
195 statistical analyses were performed in RStudio (version 2024.12.0+467) using R version 4.3.3 (R Core Team, 2022).

3 Results

3.1 Kiln dust physicochemical properties

XRD analysis revealed that the kiln dusts contained substantial amounts of calcite ($CaCO_3$; CKD $\sim 37\%$ and LKD $\sim 54\%$; Table 2) and amorphous phases ($\sim 34\%$ in CKD and $\sim 14\%$ in LKD). Furthermore, lime (CaO), portlandite ($Ca(OH)_2$), quartz
200 (SiO_2) and anhydrite ($CaSO_4$) were additionally present in both kiln dusts at concentrations of 0.1–20 %. Finally, CKD also contained 0.9 % sylvite (KCl), 9.5 % syngenite ($K_2Ca(SO_4)_2 \cdot H_2O$), and 3.9 % Aphthitalite ($(K,Na)_3Na(SO_4)_2$) (Table 2).
[Furthermore, minor phases including 2.1% larnite/β-C₂S \(\$Ca_2SiO_4\$ \), 0.68% hematite \(\$Fe_2O_3\$ \), and 0.56% maghemite \(\$\gamma-Fe_2O_3\$ \)](#)

205 Formatted: Font: (Default) +Body (Times New Roman), 10 pt, Not Highlight

Formatted: Font: (Default) +Body (Times New Roman), 10 pt, Not Highlight

were identified with low confidence in one of the duplicate CKD samples analyzed by XRD. Both materials exhibited a relatively wide grain size distribution (Table 2 and Appendix A Fig. A1), but CKD ($D_{50} = 8.4 \pm 0.1 \mu\text{m}$) was significantly 205 finer than LKD ($D_{50} = 72 \pm 4 \mu\text{m}$). The observed elemental composition was generally in lineecongruent with the XRD results, showing high calcium contents in both CKD (27.8 wt%) and LKD (44.9 wt%), which fall within the range previously reported for CKD (14–46 %) and LKD (20–49 wt%) (Collins and Emery, 1983; Pavía and Regan, 2010; Latif et al., 2015; Drapanauskaite et al., 2021; Dvorkin and Zhitkovsky, 2023). While LKD exhibited relatively low levels of trace elements, CKD showed elevated concentrations, particularly of Zn (0.65 wt%) and Pb (0.15 wt%) (Table 2). Further details on the 210 elemental composition are provided in Appendix A Table A1.

Based on the mineralogical composition, the theoretical alkalinity release upon dissolution in seawater was calculated from the reaction stoichiometry. Saturation state analysis (Appendix B Fig. B2) show that seawater is undersaturated ($\Omega < 1$) with respect to most mineral phases present in the kiln dusts, with the exception of calcite and quartz. This indicates that dissolution is thermodynamically favourable, although it may be limited by kinetic constraints. Among the undersaturated minerals, 215 anhydrite, sylvite, aphthalite, and syngenite do not contribute to alkalinity upon dissolution in seawater. Furthermore, the hematite and maghemite present in the CKD are essentially insoluble under oxic conditions in natural seawater, and filtration would remove Fe-reducing bacteria capable of enhancing their dissolution (Canfield, 1989). In contrast, the dissolution of portlandite and lime each produces two moles of A_g per mole (Eq. 3), while larnite (potentially present in the CKD) would 220 yield four moles of A_g per mole upon dissolution (Brand et al., 2019). Overall, complete dissolution of these phases corresponds to maximum alkalinity contributions of 8.8 mmol g^{-1} for the LKD and 1.7 mmol g^{-1} for the CKD, respectively.

Table 2. Physicochemical properties of the experimental cement kiln dust (CKD) and lime kiln dust (LKD). ND indicates that the phases were not detectable. The minor phases larnite/beta-calcium disilicate ($\beta\text{-Ca}_2\text{Si}_2\text{O}_7$; 2.1%), hematite (Fe_2O_3 ; 0.68%), and maghemite ($\gamma\text{-Fe}_2\text{O}_3$; 0.56%) were detected with low confidence in one of the duplicate samples and are therefore mentioned here but not included in the table. The complete measured elemental composition is provided in Appendix A Table A1.

Mineral composition (% w/w)	CKD	LKD
Calcite (CaCO_3)	37.0	53.8
Lime (CaO)	1.5	9.4
Portlandite ($\text{Ca}(\text{OH})_2$)	2.8	20.1
Quartz (SiO_2)	3.4	0.13
Anhydrite (CaSO_4)	4.7	2.2

Formatted: Font: (Default) +Body (Times New Roman), 10 pt

Formatted: Font: (Default) +Body (Times New Roman)

Formatted: Subscript

Formatted: Font: 10 pt

Sylvite (KCl)	0.9	ND
Syngenite ($K_2Ca(SO_4)_2 \cdot H_2O$)	9.5	ND
Aphthitalite ($(K,Na)_3Na(SO_4)_2$)	3.9	ND
Amorphous phases	34.3	14.4
Theoretical alkalinization potential (mmol g⁻¹)	1.75	8.8
Textural composition		
D10 (μm)	2.2 ± 0.02	6.4 ± 0.2
D25 (μm)	3.9 ± 0.02	22 ± 1
D50 (μm)	8.4 ± 0.05	72 ± 4
D75 (μm)	24 ± 0.3	172 ± 12
D90 (μm)	49 ± 0.9	327 ± 35
Geometric specific surface area ($m^2 g^{-1}$)	0.455 ± 0.007	0.121 ± 0.004
BET specific surface area ($m^2 g^{-1}$)	4.2	3.2
Particle density ($g cm^{-3}$)	2.71 ± 0.18	2.87 ± 0.14
Elemental composition (% w/w)		
Ca	27.8	44.9
Mg	0.56	0.22
Zn	0.65	0.0029
Pb	0.15	<0.000014


225

3.2 Kiln dust dissolution speed

The dissolution kinetics of CKD and LKD in seawater (salinity 32 ± 0.1 , temperature $20^\circ C$, initial $pH_{T,pH}$ of 8.05 ± 0.03) were investigated in experiment I over a period of 8 hours at three different kiln dust concentrations under continuous stirring. A rapid increase in seawater $pH_{T,pH}$ was observed for both kiln dusts: about 69 ± 8 % of the total $pH_{T,pH}$ rise occurred within 230 the first ~10 minutes, after which the $pH_{T,pH}$ continued to slowly increase for the rest of the 8-hour incubation (Fig. 1A). The final $pH_{T,pH}$ increase $\Delta pH_{T,pH} = pH_{T,pH}(t_{end}) - pH_{T,pH}(t_0)$ was greater for LKD than for CKD and increased with higher kiln dust concentrations (Fig. 1C).

Upon dissolution, the percentage of reactive phases that had effectively dissolved $\chi_{\text{diss}}(t)$ rapidly increased with time, with 50 % of the reactive phases dissolved within 9.5 ± 3 minutes for LKD and within 9.9 ± 2.4 minutes for CKD (Fig. 1B). At the 235 lowest kiln dust concentration, approximately 83 ± 9 % of the reactive phases in LKD and 72 ± 12 % in CKD had dissolved after one hour, which increased to 88 ± 7 % and 82 ± 17 % respectively after 8 hours. At higher kiln dust concentrations, the percentage of dissolved reactive phases was generally lower (Fig. 1B). This effect is likely caused by secondary mineral precipitation, and not so much by reduced dissolution, as further discussed in Sect. 3.3.

Kiln dust dissolution in seawater resulted in a concomitant increase in alkalinity, $\Delta A_T = A_T(t) - A_T(t_0)$, which increased with 240 higher kiln dust concentrations (Fig. 1D), and attained values ranging from 60 to $447 \mu\text{mol kg}^{-1}$ for CKD and 110 to $416 \mu\text{mol kg}^{-1}$ for LKD, depending on the applied kiln dust concentration. Notably, the relationship between ΔA_T and kiln dust addition was non-linear and showed a saturating effect (Fig. 1D), suggesting a decreased specific alkalinity release at higher kiln dust concentrations.

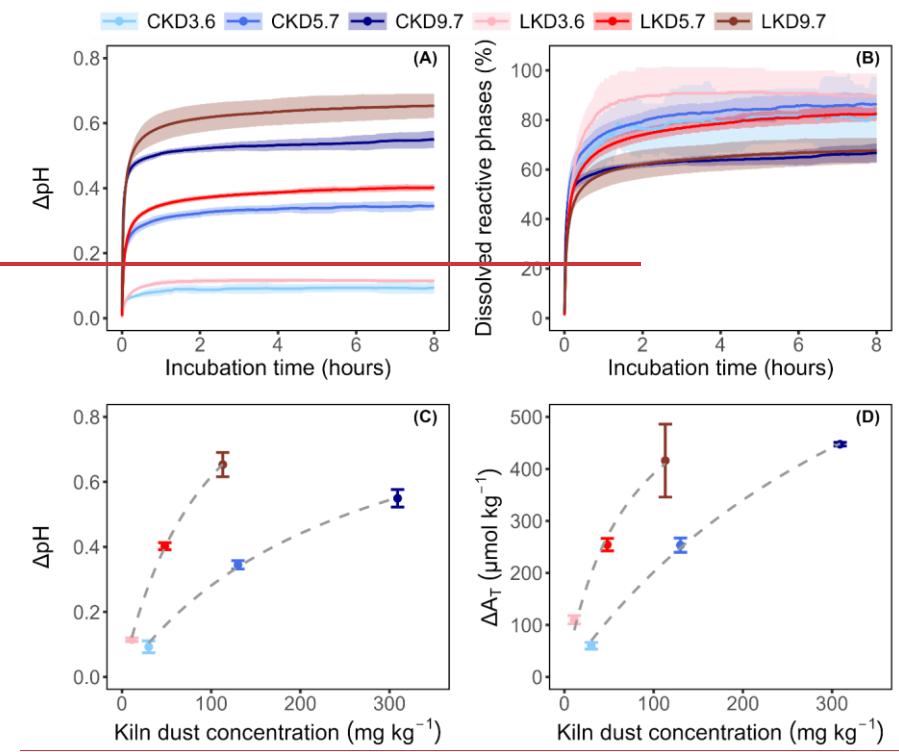

245

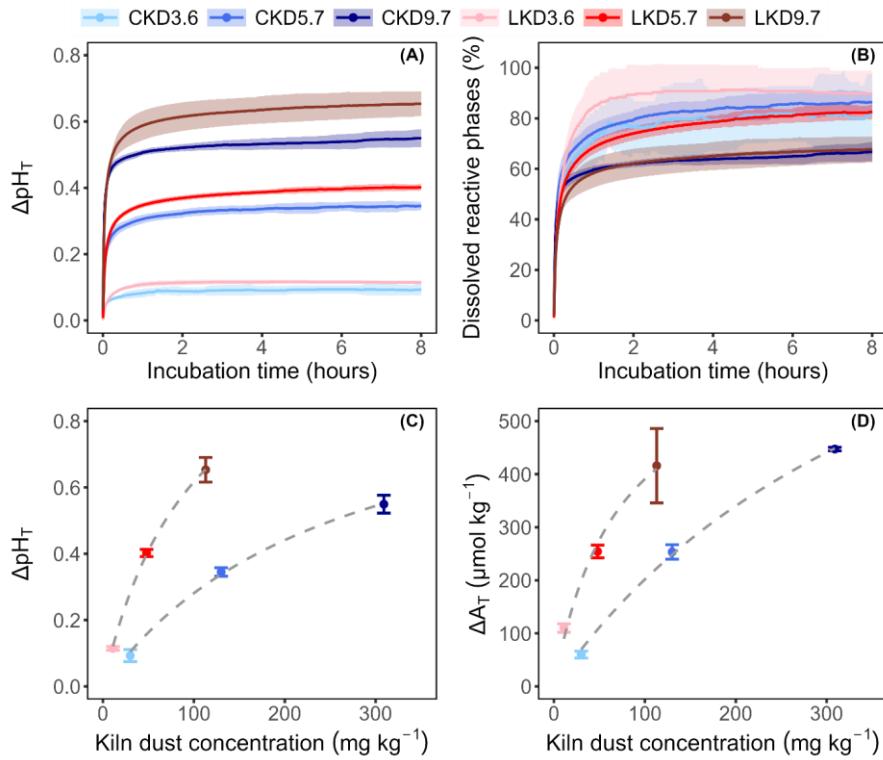


Figure 1. Results (Mean \pm S.D., $N = 3$) obtained in experiment I for three concentrations of cement kiln dust (CKD, in blue) and lime kiln dust (LKD, in red). (A) Change in seawater pH_{TpH} (ΔpHT) as a function of incubation time. pH on total scale. (B) Estimated percentage of reactive kiln dust phases (χ_{diss}) dissolved as a function of incubation time. Change in (C) seawater pH_{TpH} and (D) total alkalinity (ΔAT) after 8 hours as a function of kiln dust concentration. Fitted non-linear least squares curves are shown as a grey dashed line in (C) and (D).

3.3 Alkalinity generation

In experiment II, we investigated the alkalinity release from LKD and CKD after 1 and 15 days of incubation across a range of kiln dust concentrations. Dissolution resulted in a change in seawater pH_{TpH} and A_T that markedly varied with kiln dust concentration (Fig. 2A and 2B). After one day, the pH_{TpH} increased showed a non-linear (saturating) increase with the kiln

dust concentrations for both LKD and CKD (Fig. 2A), consistent with the results of experiment I after 8 hours (Fig. 1C). Yet after 15 days of incubation, the $\Delta\text{pH}_{\text{TpH}}$ curve showed a marked difference between LKD and CKD. For CKD, the $\Delta\text{pH}_{\text{TpH}}$ curve at 15 days showed a similar saturating shape as after 1 day, though with slightly decreased $\Delta\text{pH}_{\text{TpH}}$ values at higher kiln dust concentrations (suggesting a process at play that reduced pH_{TpH}). For LKD, the $\Delta\text{pH}_{\text{TpH}}$ curve at 15 days was entirely

260 different compared to day 1, with a marked decrease in $\Delta\text{pH}_{\text{TpH}}$ at higher concentrations. For the highest LKD concentration examined (111 mg kg⁻¹), the pH_{TpH} after 15 days was almost the same as at the start ($\Delta\text{pH}_{\text{TpH}} = 0.17 \pm 0.14$) (Fig. 2A).

The observed changes in alkalinity (Fig. 2B) were congruent with those seen for $\Delta\text{pH}_{\text{TpH}}$. After one day, ΔA_T showed a monotonous increase with the CKD concentration, while for LKD, the ΔA_T curve showed-reached a maximum at higher concentrations 69 mg kg⁻¹ and decreased at higher application concentrations (Fig. 2B). The ΔA_T curves for LKD and CKD

265 obtained at 15 days of incubation were markedly different from those at day 1, showing reduced ΔA_T values at higher kiln dust concentrations, indicative of a process that consumes alkalinity. Notable, for LKD, ΔA_T became negative at higher concentrations (Fig. 2B), indicating a removal of alkalinity compared to the initial situation.

The specific alkalinity release quantifies the alkalinity release per mass of kiln dust added, and generally decreased for higher concentrations (Fig. 2C). The highest values for the specific alkalinity release were obtained at the lowest kiln dust

270 concentrations applied (21 mg kg⁻¹ and lower for LKD, 89 mg kg⁻¹ or lower for CKD). The maximum specific alkalinity release for LKD (8.02 ± 0.53 mmol g⁻¹) was more than three times higher than that of CKD (2.38 ± 0.16 mmol g⁻¹). Moreover, the LKD value was in good agreement with the theoretical prediction (8.8 mmol g⁻¹; see section 3.1), while the CKD value deviated more substantially from the theoretical estimate (1.7 mmol g⁻¹), and generally agreed with the theoretically calculated value (8.8 mmol g⁻¹ for LKD and 1.3 mmol g⁻¹; see Sect. 3.1). The specific alkalinity release after 15 days showed a clear

275 difference with day 1, which was more pronounced for LKD compared to CKD. At the low application concentrations, the specific A_T release after 15 days of incubation was not statistically significantly different from the release after 1 day (Fig. 2C), thus indicating that all A_T -generating reactive phases had dissolved within the first day and no alkalinity removal took place. Yet, the specific A_T release decreased substantially at higher kiln dust concentrations, with a more pronounced decline for LKD compared to CKD. In the case of LKD, the specific A_T release became even negative after 15 days of incubation,

280 thus indicating overall alkalinity consumption rather than production (Fig. 2C).


Formatted: Superscript

Formatted: Superscript

Formatted: Superscript

To verify whether secondary carbonate precipitation could be responsible for the observed alkalinity consumption, we calculated the seawater aragonite saturation state (Ω_{Arg}). The increase in seawater total alkalinity (A_T) from kiln dust dissolution led to a corresponding rise in aragonite saturation state (Ω_{Arg}) from an initial value of 3.0 ± 0.1 at the start of the experiment II to 9.3 ± 0.3 and 10.3 ± 0.1 after 1 day of incubation at the highest concentrations of LKD and CKD, respectively (Fig. 2D).

285 Moreover, a significant decrease in Ω_{Arg} was observed at day 15 compared to day 1 for LKD concentrations above 21 mg kg^{-1} and for CKD concentrations above 89 mg kg^{-1} , suggesting alkalinity scavenging by secondary mineral precipitation. This decrease became more pronounced at higher application concentrations and was notably greater for LKD compared to CKD. For the highest LKD concentration investigated (111 mg kg^{-1}), Ω_{Arg} after 15 days (2.5 ± 0.6) was not significantly different from the initial Ω_{Arg} value (Fig. 2D).

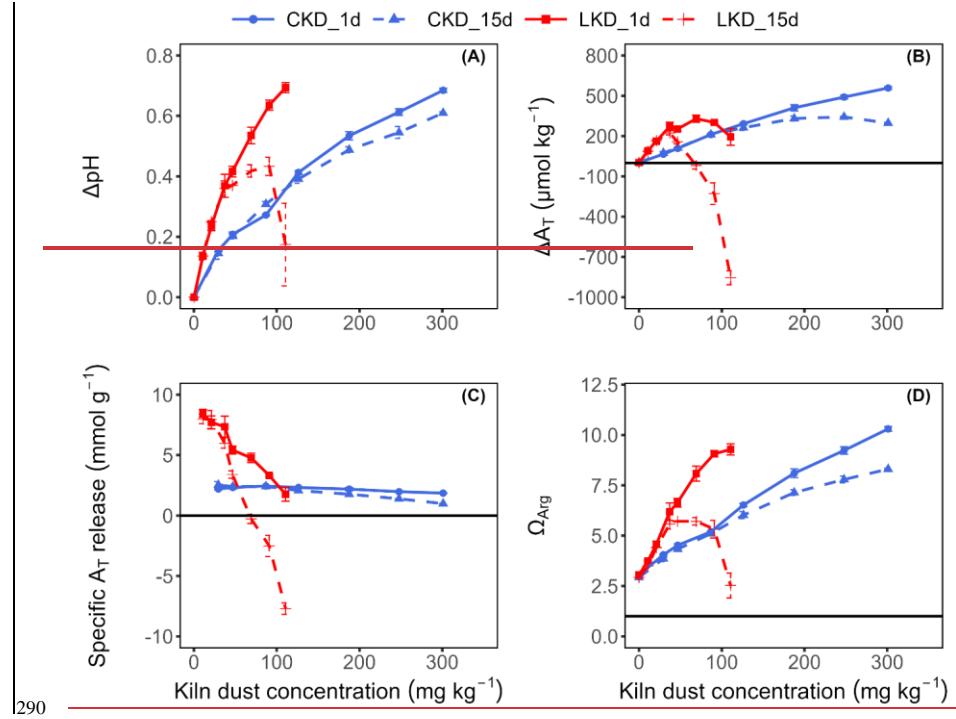

Formatted: Normal (Web), Line spacing: single

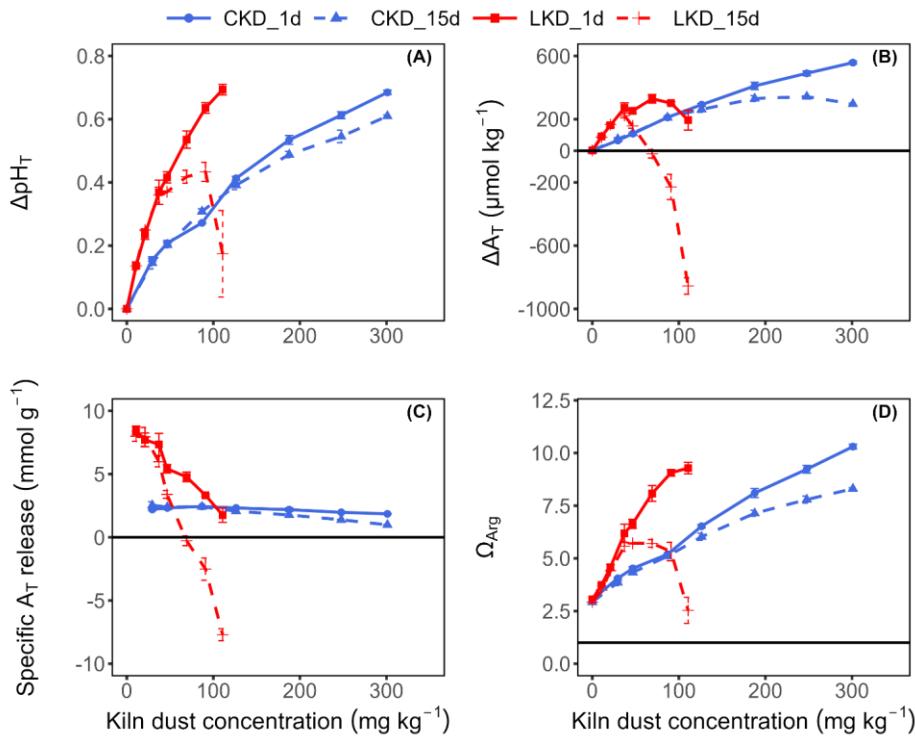


Figure 2. Results obtained in experiment II for different concentrations of cement kiln dust (CKD, blue) and lime kiln dust (LKD, red). (A) Change in seawater pH_{TPH} ($\Delta\text{pH}_{\text{TPH}}$), (B) total alkalinity (ΔA_T , expressed in $\mu\text{mol kg}^{-1}$), (C) Specific A_T release (mmol mg^{-1}) and (D) aragonite saturation state (Ω_{ArG}) as a function of the kiln dust application concentration (mg kg^{-1}). Results (as mean \pm S.D., $N=3$) after 1 day (solid lines) and 15 days of incubation (dashed lines) are shown.

295


3.4 Mineral morphology and secondary mineral precipitation

The morphology of kiln dust particles was compared before and after chemical weathering (i.e., fresh material versus samples retrieved after 15 days in experiment II). Fresh lime kiln dust (LKD) consisted of a heterogeneous mixture of particles of varying size and shape, dominated by small ($<10 \mu\text{m}$), irregular, calcium-rich particles (~10–20 at%) (Fig. 3A). In weathered 300 LKD, the abundance of these fine particles decreased (Fig. 3C, E), while larger particles developed rough surface texture

Formatted: Do not check spelling or grammar, Not Highlight

(representative particle indicated by red arrow in Fig. 3C), suggesting dissolution of surface phases. After 15 days of incubation at the highest LKD concentration, most particles were extensively coated with bundles of needle-like, calcium-rich precipitates (Fig. 3E).

Fresh cement kiln dust (CKD) also contained irregularly shaped particles of various sizes (Fig. 3B). In addition, spherical fly
305 ash particles of varying diameters were prominent in both fresh and weathered CKD samples and showed no signs of weathering during experiment II (red arrows in Fig. 3B, D, F). In contrast to LKD, weathered CKD particles showed neither roughened surfaces nor secondary calcium carbonate precipitation, regardless of concentration or incubation duration (Fig. 3D, F).

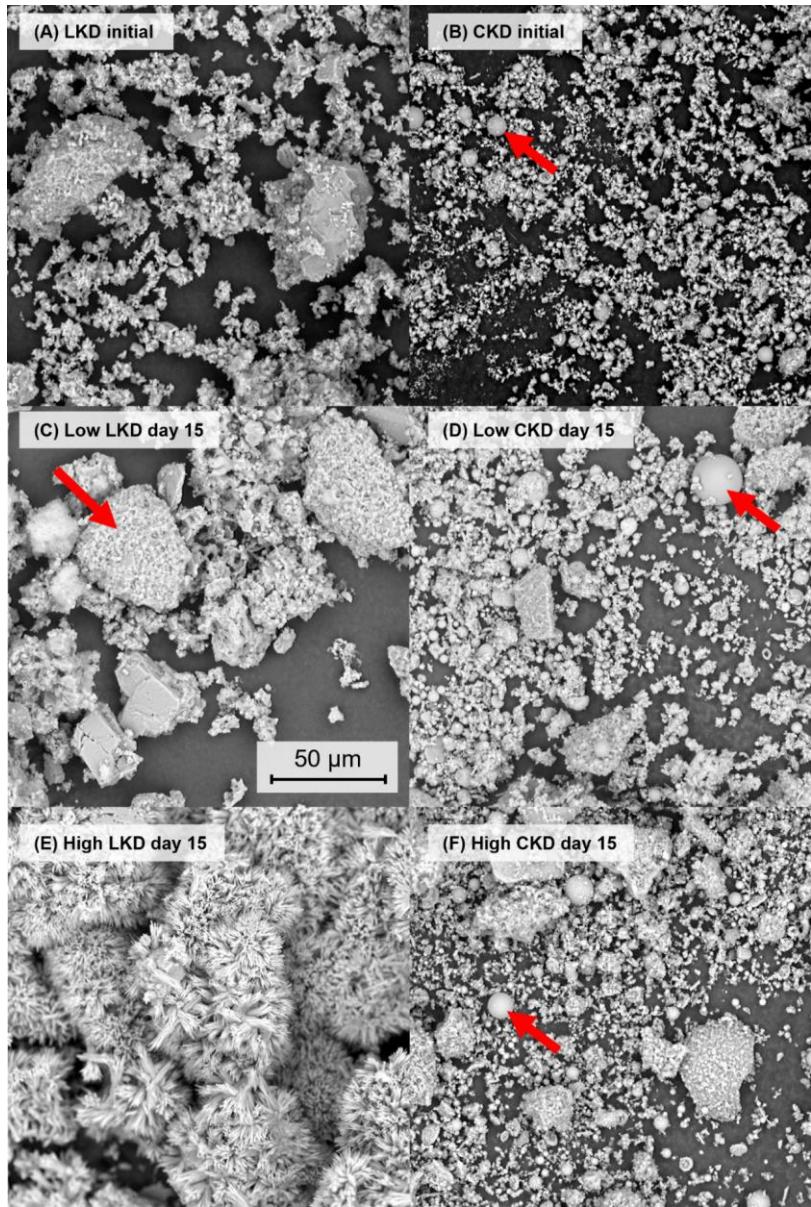

315 **Figure 3:** Representative **Scanning scanning** electron microscopy (SEM) images of kiln dust particles at different time points in experiment II. (A) Fresh lime kiln dust (LKD) and (B) fresh cement kiln dust (CKD). Images (C) and (D) show CKD and LKD particles after 15 days of incubation at low application concentrations (88.85 mg kg^{-1} and 20.96 mg kg^{-1} , respectively). Images (E) and (F) show CKD and LKD particles incubated for 15 days at the highest application concentrations ($307.84 \text{ mg kg}^{-1}$ and 110.7 mg kg^{-1} , respectively). Red arrows in panels (B), (D), and (F) mark fly ash particles, while the red arrow in panel (C) highlights the rough surface texture of a weathered large LKD particle.

3.5 Turbidity and trace metals

The turbidity in solution after 1 and 15 days increased linearly with the applied kiln dust concentration, as expected. At equivalent application concentrations, turbidity was ~ 2.4 times higher for CKD than for LKD, consistent with the finer grain size of the CKD (Fig. 4A). After 15 days of incubation, seawater turbidity rose from $0.33 \pm 0.10 \text{ FNU}$ in the initial filtered seawater to $281 \pm 3 \text{ FNU}$ at the highest CKD concentration and $52 \pm 3 \text{ FNU}$ at the highest LKD concentration. Turbidity was slightly but statistically significantly greater on day 15 compared to day 1 at higher kiln dust concentrations ($>253 \text{ mg kg}^{-1}$ for CKD; $>69 \text{ mg kg}^{-1}$ LKD), possibly due to fragmentation of unreacted kiln dust particles and/or the formation of secondary calcium carbonate providing fine particles in solution (Fig. 4A).

325 The accumulation of dissolved Fe, Ni, Cu, Zn, As, and Pb was low in both the LKD and CKD incubations and showed no clear dependence on kiln dust concentration (Appendix B Fig. B3). So trace metal release was limited, apart from vanadium (V) in the CKD incubation, which linearly scaled with the kiln dust concentration (Fig. 4B). After 15 days, V accumulation reached $0.51 \pm 0.09 \text{ } \mu\text{mol kg}^{-1}$ at the highest CKD concentration and $0.008 \pm 0.001 \text{ } \mu\text{mol kg}^{-1}$ at the highest LKD concentration, respectively. These values agreed relatively well with the expected accumulations of $0.63 \text{ } \mu\text{mol kg}^{-1}$ and $0.0033 \text{ } \mu\text{mol kg}^{-1}$, based on the elemental composition and assuming that V belongs to the dissolvable fraction of the kiln dusts (Appendix B Fig. B4). The dissolved V accumulation after 15 days did not differ significantly from that on day 1, suggesting that V is not involved in secondary reactions. For CKD, concentration-dependent accumulation of Al, Cr, and Mn was also observed, though the accumulation represented only a small fraction of what was expected based on complete dissolution of reactive phases: 2–11 % for Al, 24–35 % for Cr, and 0.6–2 % for Mn (Appendix B Fig. B3–4).

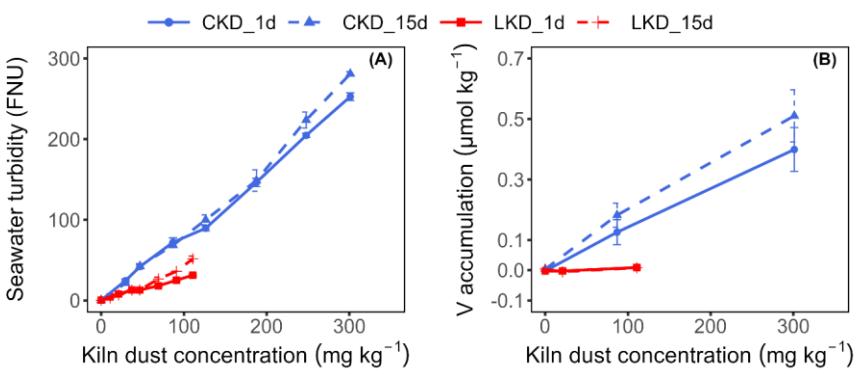
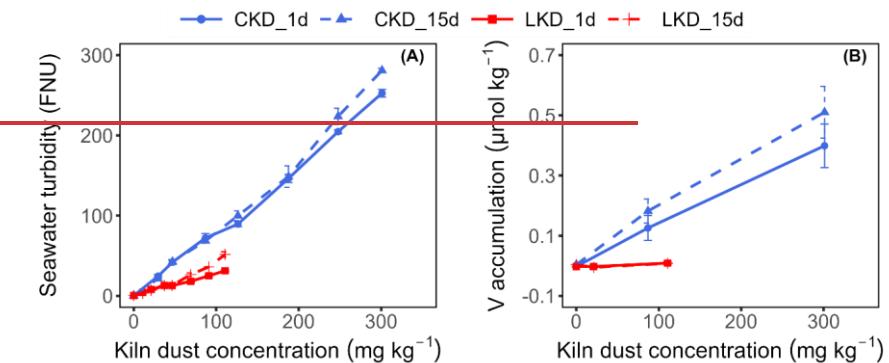


Figure 4. Impact of dissolution on turbidity and trace metals in experiment II. Results (as mean \pm S.D., N=3) are shown for lime kiln dust (LKD, red) and cement kiln dust (CKD, blue) after 1 day (solid lines) or 15 days (dashed lines) of incubation. (A) Seawater turbidity (FNU) and (B) accumulation of dissolved vanadium (V, $\mu\text{mol kg}^{-1}$) as a function of the kiln dust concentration.

4.1 Dissolution kinetics and alkalinity generation potential

The dissolution kinetics of LKD and CKD were studied in natural seawater (salinity: 32.3 ± 0.5 ; temperature: $17.5\text{--}22.7^\circ\text{C}$) under continuous stirring. LKD mainly consists of calcite (CaCO_3), with smaller amounts of quartz, portlandite, lime,

Formatted: Normal (Web), Line spacing: single

anhydrite, mullite, and dolomite (Strydom et al., 1996; Ban et al., 2022). CKD is more compositionally complex, typically
345 containing calcite along with various sulfates, chlorides, silicates, and aluminates, including belite, aphthitalite, spurite,
ettringite, arcanite, and ferrite (Ayman et al., 2004; Siddique and Rajor, 2012; Beltagui et al., 2017; Adekunle, 2024; Lee and
Choi, 2024; Nikolov et al., 2025). The compositional complexity of kiln dusts underscores the need for detailed mineralogical
and chemical characterization to properly assess the CDR potential and environmental risks in OAE applications.

Both materials generated significant alkalinity upon dissolution in seawater, with maximum values of $8.02 \pm 0.53 \mu\text{mol mg}^{-1}$
350 for LKD and $2.38 \pm 0.16 \mu\text{mol mg}^{-1}$ for CKD after 24 hours. This alkalinity originated from a fraction of reactive phases
contained within the kiln dust (25 % by mass in LKD; 29 % in CKD), which we estimated based on the mineral components
that are unstable in seawater. Consequently, both LKD and CKD contained a substantial amount of unreactive phases that
remained inert over the 15-day duration of our short-term experiments. In preliminary tests, replacement of the overlying
seawater after 15 days did not result in further dissolution or alkalinization. The residual fraction in LKD and CKD consisted
355 primarily of calcite, which is supersaturated in surface seawater (Appendix B Fig. B2G), preventing its dissolution (Sulpis et
al., 2021).

The experimentally observed alkalinity release from LKD ($8.02 \pm 0.53 \text{ mmol g}^{-1}$) was slightly lower than the theoretical value
(8.8 mmol g^{-1}), whereas CKD released substantially more alkalinity ($2.38 \pm 0.16 \text{ mmol g}^{-1}$) than predicted from its
360 mineralogical composition (1.73 mmol g^{-1}). In LKD, alkalinity release was fully ~~be~~ attributed to the dissolution of portlandite
($\text{Ca}(\text{OH})_2$) and lime (CaO), whereas in CKD these phases explained only about half ($54 \pm 3 \%$) of the observed alkalinity

365 release. Calcium silicates (e.g. larnite Ca_2SiO_4) are also alkalinity-generating phases that occur in minor amounts in CKD.

They originate from the raw materials used in cement production (e.g. iron ore, clay, or shale) and exhibit a relatively high
reactivity in water (Brand et al., 2019; Adekunle, 2024). Dissolution of the larnite present in our CKD sample (~ 2.1 %) could
account for $17 \pm 1\%$ of the observed Al release, which hence provides a substantial additional contribution. The remaining

Formatted: Subscript

Formatted: Subscript

370 ~29% of the alkalinity released from alkalinity release from CKD likely originated from dissolution of amorphous phases,
including (partially dehydrated) clay minerals, reactive amorphous silica, and kiln-derived materials such as fly ash or slag
(Khanna, 2010; Pavía and Regan, 2010). ICP-OES analysis revealed 8.0 % Ca, 2.7 % K, 0.7 % Na, 0.9 % S, 1.6 % Fe and 3 %
Al that were not accounted for by the crystalline phases detected via XRD (Table 2 and Table A1). This suggests the possible

Formatted: Subscript

presence of amorphous calcium aluminosilicates, alkali sulfates, and poorly crystalline CaO or Ca(OH)₂, which may have

370 contributed to the remaining alkalinity upon dissolution in seawater (Hu et al., 2024; Nikolov et al., 2025). There is a possibility that some reactive phases remained sequestered in larger particles and did not react with seawater on the time scale of the experiment. However, this fraction is likely minor, since the experimentally observed alkalinity release was close to, or even exceeded, the maximum theoretically predicted values from the mineralogical composition.

The dissolution of kiln dusts was rapid, with 65–92 % of the reactive phases dissolving within the first hour of incubation

375 under continuous stirring (Fig. 1B). This estimate assumes a constant DIC concentration over time, although values could have increased due to CO₂ uptake from the (limited) vial headspace or decreased through secondary aragonite precipitation at higher application concentrations. Therefore, the χ_{diss} values reported (Fig. 1B) should be considered best estimates based on available data. Nonetheless, the rapid alkalinity release highlights the potential of kiln dusts for OAE. Using our measured particle size distribution and assuming particle sinking follows Stokes' law, all CKD particles and the majority of LKD particles (85 ± 2 % V/V) will remain in the surface ocean mixed layer (assumed to be 200 m) for about-at least one hour, thus allowing sufficient time for most reactive phases to dissolve and generate alkalinity (Appendix A Sect. A2). However, ocean turbulence and particle aggregation induced by biological exudates can significantly accelerate particle sinking (Yang and Timmermans, 2024) and affect kiln dust dissolution kinetics. Consequently, further research is needed to quantify kiln dust dissolution rates and settling velocities under a range of scenarios that more closely mimic *in situ* hydrodynamic conditions.

385 **Formatted: Font: Italic**

This information is essential for the careful selection of application areas, ensuring that dissolution of the reactive phases occurs within the ocean mixed layer. Hence, application areas need to be carefully chosen to ensure that dissolution of the reactive phase takes place in the ocean mixed layer.

4.2 Emergence and prohibition of secondary precipitation

Alkalinity addition to seawater should avoid triggering secondary precipitation reactions that consume alkalinity, as these

390 reduce the overall efficiency of OAE. Specific A_T release significantly decreased at concentrations above 21 mg kg⁻¹ for LKD and 89 mg kg⁻¹ for CKD, with greater reductions at higher kiln dust concentrations and longer incubation times (Fig. 2C). Furthermore, the decrease was stronger for LKD relative to CKD at equivalent aragonite saturation states (Fig. 2C and 2D).

The observed reduction in specific A_T release can be attributed to secondary mineral precipitation, as indicated by the reduction in seawater DIC concentrations (Appendix B Fig. B1) and the formation of Ca-rich needle-like structures on weathered LKD

395 grains (Fig. 3E). These needles resemble the early developmental stage of aragonite precipitates, as described by Suitner et al.

(2024). No significant A_T loss occurred at Ω_{Arg} values of 5.1 ± 0.07 for CKD and 4.5 ± 0.1 for LKD, but significant loss was observed at higher kiln dust concentrations. This aligns with the previously documented $\Omega_{\text{Arg}} = 5$ threshold for secondary aragonite precipitation, when fine-grained ($<63 \mu\text{m}$) quick lime (CaO) or slaked lime ($\text{Ca}(\text{OH})_2$) powder from a chemical and industrial supplier are added to natural seawater at 35 salinity (Moras et al., 2022). While the Ω_{Arg} precipitation threshold was

400 similar for LKD and CKD, the CKD treatment showed a lower precipitation rate, possibly because CKD has a lower content of Ca-rich phases (e.g., calcite, lime and portlandite), which can serve as nucleation sites for aragonite precipitation (Pan et al., 2021; Moras et al., 2022; Suitner et al., 2024). Prolonged exceedance of critical saturation thresholds can trigger "runaway

CaCO_3 precipitation", leading to a net A_T loss, as seen at the highest LKD concentration after 15 days (Fig. 2B) (Moras et al., 2022). Under natural conditions, freshly precipitated aragonite may redissolve after dilution in the ship's wake, especially

405 when not yet fully crystallized, recovering some of the lost alkalinity due to secondary precipitation (Hartmann et al., 2023).

Aragonite precipitates that settle onto the sediment at the deployment site may undergo further metabolic dissolution provided that geochemical conditions are favourable, offsetting the earlier alkalinity loss (see Section 4.4). However, these fine-grained precipitates could also disperse far from the deployment site, thus complicating monitoring, reporting, and verification (MRV) of CDR via kiln-dust-based OAE. So, despite that some secondary aragonite may redissolve, its formation is best minimized

410 to maximize the alkalization potential. Based on our temporal dissolution data (Fig. 1A-B), it is recommended to adjust the OAE dispensing and deployment procedure in such a way, that dilution to $\Omega_{\text{Arg}} < 5$ occurs within minutes as to minimize secondary mineral precipitation.

4.3 Potential ecological impacts of kiln dust dissolution

Mineral-based OAE shows promise as a CDR technique, but its effects on seawater carbonate chemistry, turbidity, and trace

415 element concentrations could lead to adverse ecological impacts that need to be mitigated (Bach et al., 2019; Flipkens et al., 2021). For ocean liming, rapid mineral dissolution can cause acute spikes in pH_{TpH} and alkalinity right after discharge, raising

potential environmental concerns (Caserini et al., 2021; Varliero et al., 2024). In our study, CKD and LKD caused fast, concentration-dependent seawater pH_{ipH} increases (Fig. 1A). Model predictions indicate that pH could rise by 1 to 1.5 units for several minutes during ship-based ocean liming (Caserini et al., 2021), which may have an impact on marine life if pH 420 exceeds 9 (ANZECC and ARMCANZ, 2000; Pedersen and Hansen, 2003; Camatti et al., 2024). To avoid temporary exceedances of pH 9, CKD concentrations should stay below 343–502 mg kg⁻¹, and LKD below 102–149 mg kg⁻¹ under average, depending on local surface seawater conditions ($\text{A}_\text{T} = 2350 \mu\text{mol kg}^{-1}$, $\text{DIC} = 2100 \mu\text{mol kg}^{-1}$, salinity = 35, temperature = 10–25 °C). Application concentrations must be tailored to local seawater geochemistry at the deployment site to prevent exceeding the pH 9 threshold.

425 Seawater turbidity rose linearly with kiln dust concentration and was greater for CKD than LKD at equivalent doses, consistent with the finer grain size of CKD (Fig. 4A). Increased turbidity could reduce primary production by obstructing light (Cloern, 1987; Köhler et al., 2013), and impair feeding efficiency in marine suspension feeders (e.g. bivalves, sponges, and tunicates) (Cheung and Shin, 2005; Bell et al., 2015) and visual foragers (e.g. most marine fish and mammals) (Lowe et al., 2015; Lunt and Smee, 2020). Additionally, the sinking rate of organic carbon to the deep sea could be enhanced by the adsorption of 430 organic molecules onto suspended particles (Santinelli et al., 2024), which may affect ecosystem carbon cycling, but also would provide additional CDR. Turbidity guidelines are designed to protect marine life from harmful increases: for example, in Canada, seawater turbidity should not increase by more than 8 NTU over 24 hours in clear water, or 5 NTU at any time in already turbid water (8–50 NTU background) (Singleton, 2021). To stay within these limits, ambient CKD concentrations must remain below 9.7 mg kg⁻¹ in clear water and 6.1 mg kg⁻¹ in turbid water, while LKD concentrations should stay below 435 23.7 and 14.8 mg kg⁻¹, respectively (Fig. 4B). In real applications, kiln dust will be rapidly mixed into much larger volumes of surface water, meaning that the allowable concentration in the input stream will depend on the discharge rate, and the the intensity of local turbulence, and kiln dust settling time (which is primarily determined by initial particle size). Accurate numerical modelling to determine suitable discharge rates therefore requires detailed knowledge of both the environmental conditions at the deployment site and the behaviour of kiln dust particles under varying hydrodynamic conditions (Fennel et 440 al., 2023; Yang and Timmermans, 2024). This information is essential to extrapolate small-scale laboratory results to realistic field scenarios and ensure that concentrations remain below guideline levels.

At the turbidity thresholds, the maximum seawater alkalinity enhancement would range from 119 to 190 $\mu\text{mol A}_T \text{ kg}^{-1}$ for LKD, and only 15 to 23 $\mu\text{mol A}_T \text{ kg}^{-1}$ for CKD. The corresponding increases in pH_T (assuming $\text{A}_T = 2350 \mu\text{mol kg}^{-1}$, $p\text{CO}_2 = 420 \mu\text{atm}$, salinity = 35, and temperature = 10–25 °C) are $\Delta\text{pH}_T = 0.18\text{--}0.30$ for LKD and $\Delta\text{pH}_T = 0.002\text{--}0.004$ for CKD, both 445 remaining well below the threshold of $\Delta\text{pH}_T = \sim 0.9$ (rise up to $\text{pH}_T 9$). Moreover, the carrying capacity of natural coastal and shelf ecosystems appears to be large enough to execute LKD- and CKD-based OAE within the existing turbidity constraints. For example, the North Sea has a total volume 54.000 km³ and an average residence time of ~1 year (Lee, 1980; Liu et al., 450 2019). A hypothetical one-time application of LKD-based OAE across the entire North Sea at the maximum level of 119 $\mu\text{mol A}_T \text{ kg}^{-1}$ for LKD, would require 823 Mton of LKD, which is ~28 times larger than the global annual LKD production rate (~29 Mton yr⁻¹).

The dissolution of alkaline minerals can release trace metals into the environment, which may be beneficial or toxic to marine life (Bach et al., 2019; Flipkens et al., 2021). CKD contained notable amounts of Zn and Pb, while LKD had generally low trace element levels (Appendix A Table A1). Trace metal content in kiln dusts varies with raw materials, fuels, and kiln operations, and is typically higher and more variable in CKD (Siddique and Rajor, 2012; Nyström et al., 2019). In experiment 455 II, metal release from LKD was limited, whereas CKD showed concentration-dependent release of V, Cr, Mn, and Fe (Fig. 4B; Appendix B Fig. B3). Regulatory guidelines exist to protect aquatic life from trace metal toxicity. For example, Tulcan et al. (2021), proposed a seawater V guideline of 0.022 $\mu\text{mol L}^{-1}$, which would require CKD concentrations to remain below 14.1 mg kg^{-1} to avoid exceedance. Higher application rates may be permissible under other guidelines for V, Cr, or Mn. Residual kiln dust mixing with surface sediments may elevate metal levels, particularly Zn and Pb from CKD. Sediment 460 Quality Guidelines (SQGs) aim to protect benthic ecosystems (Hübner et al., 2009; Simpson and Batley, 2016). Assuming full mixing in the top 10 cm of the sediment, up to 1.4 kg CKD or 74.8 kg LKD per m² could be applied to pristine sediments without exceeding the strictest marine SQG of 30.2 mg kg^{-1} for Pb (Appendix C). [Using a kiln dust bulk density of 0.62 g cm⁻³](#) (Nikolov et al., 2025), [this corresponds to an applied layer of approximately 0.2 cm for CKD and 12 cm for LKD. The exact layer thickness would of course be dependent on the specific kiln dust properties and local grain packing. These estimates indicate that burial risk for benthic organisms is small for CKD, but could be considerable for LKD, since the deposition of a cm-thick layer could substantially impact the resident benthic infauna and epifauna. Moreover, applying LKD at this scale is](#) 465

Formatted: Not Highlight
Formatted: Not Highlight

also not advisable because it may lead to changes in habitat suitability (e.g., grain size, permeability, organic carbon content) (Speybroeck et al., 2006; Flipkens et al., 2024) and alter geochemical sediment processes (see Sect. 4.4). Overall, these findings underscore the need for ecotoxicological testing and cautious application of CKD-kiln dust to avoid ecological harm.

470 4.4 Longer term fate of unreacted phases

Both LKD and CKD contained a significant amount of unreactive phases (75 and 71 wt%, respectively) that remained inert over the 15-day experimental time scale. In coastal and shelf environments, this residual material would rapidly settle to the seafloor. The residual fraction consists primarily of CaCO_3 phases (52 % in CKD and 72 % in LKD). When residual CaCO_3 or freshly precipitated secondary CaCO_3 become mixed into the seabed through local hydrodynamics and bioturbation, porewater acidification resulting from microbial degradation of organic matter can trigger metabolic CaCO_3 dissolution (Rao et al., 2012; Kessler et al., 2020). This process takes place under oxic conditions and produces 2 moles of alkalinity per mole of dissolved CaCO_3 .



In anoxic environments, organic matter mineralization generates more A_T than DIC, quickly increasing Ω_{cal} and thereby inhibiting dissolution (Morse and Mackenzie, 1990; Burdige, 2006). If kiln dusts OAE is applied would be applied to continental shelf waters overlying sediments with potential for enhanced carbonate dissolution, including lying above permeable organic-rich, carbonate-poor marine sediments (Lunstrum and Berelson, 2022; Dale et al., 2024; Biçe et al., 2025; Fuhr et al., 2025) or coastal upwelling zones (Harris et al., 2013; Fuhr et al., 2025), weathering of all calcite in the residual kiln dust could additionally produce a maximum of 10.8 mmol A_T g^{-1} LKD and 7.4 mmol A_T g^{-1} CKD. However, large-scale fining of sediment with kiln dust could reduce sediment properties, such as the permeability, solute exchange rates, and the oxygen penetration depth (Speybroeck et al., 2006; Ahmerkamp et al., 2017). The latter, would limit limiting the zone in which for metabolic CaCO_3 dissolution can occur. Relatively high CaCO_3 concentrations may further reduce the dissolution efficiency- (i.e. dissolution rate per amount of CaCO_3 added) (Dale et al., 2024). Additionally, ecological impacts may arise through changes of the solid sediment matrix and modifications of porewater conditions (see Sect. 4.3). The potential for enhanced sedimentary alkalinity generation via residual kiln dust addition to permeable organic-rich, carbonate-poor marine

Formatted: Not Highlight

Formatted: Subscript

Formatted: Subscript

Formatted: English (United Kingdom)

Formatted: Subscript

Formatted: Subscript

495 sediments therefore warrants further experimental investigation. If fully realized, the total alkalinity release potential (immediate dissolution and metabolic CaCO_3 dissolution-) could reach up to 18.8 mmol g^{-1} for LKD and 9.8 mmol g^{-1} for CKD. By contrast, in open-ocean applications, the residual material would settle to the deep seafloor, where metabolic dissolution would occur in waters isolated from the atmosphere and thus would not contribute to CDR on relevant (year–decade) timescales.

4.5 Carbon dioxide removal potential

Achieving the Paris Agreement targets will require rapid and deep CO_2 emission reductions, complemented by 12–15 Gt CO_2 year $^{-1}$ of carbon removal by 2100 (Rockström et al., 2017; Minx et al., 2018). Kiln dusts ~~dissolution in seawater~~ could potentially be one contributing approach within a broader CDR portfolio contribute to this CDR portfolio. Currently, most kiln dust is landfilled (El-Attar et al., 2017), while the remainder is recycled for applications such as soil stabilization, concrete mix, chemical treatment, ceramics, and brick manufacturing (Al-Bakri et al., 2022). CKD can replace 5–10% of cement, or up to 20% when combined with pozzolanic materials (fly ash, slag), reducing waste, lowering raw material and energy consumption, and cutting CO_2 emissions by a similar percentage (Huntzinger and Eatmon, 2009; Al-Bakri et al., 2022). While this represents the ideal use of CKD in terms of CO_2 mitigation, high levels of alkalis, sulfate, and chloride limit the extent to which CKD can be recycled in cement manufacturing (Al-Bakri et al., 2022). Carbonation of kiln dusts, involving the reaction of metal oxides with CO_2 to form solid carbonates, has been proposed as an alternative CO_2 sequestration method (Huntzinger et al., 2009; Adekunle, 2024):



This process captures 1 mol CO_2 per mol metal oxide, which is less than what can be achieved via CaO hydration and 510 subsequent $\text{Ca}(\text{OH})_2$ dissociation in seawater (~ 1.68 mol CO_2 mol $^{-1}$ metal oxide). In landfills, both processes naturally occur when kiln dust is exposed to rainwater (Sreekrishnavilasam et al., 2006). However, limited water availability in large kiln dust piles promotes secondary precipitation of carbonates or clay minerals, reducing the effective CO_2 sequestration. As such, the ad hoc CDR effect that occurs during landfill disposal of LKD and CKD remain uncertain. Similarly, application of kiln dust to agricultural soils for enhanced weathering purposes (as an alternative to primary mined rocks such as basalt or dunite) could

Formatted: Subscript

Formatted: Superscript

Formatted: Font: Not Bold

Formatted: Subscript

Formatted: Font: Not Bold

515 contribute to CO₂ removal, though restricted water availability may again increase the risk of secondary mineral formation
(Buckingham and Henderson, 2024; Xu and Reinhard, 2025). The focus of this study is the usage of kiln dusts via OAE in
natural marine environments. Alternatively, kiln dusts could also be used in reactor-based OAE approaches, such as accelerated
weathering of limestone (Rau and Caldeira, 1999; review in Huysmans et al., 2025). These methods allow fast, controlled, and
easily monitored alkalinity addition, but require higher energy inputs and dedicated infrastructure compared to ship-based
520 distribution in natural environments (Rau and Caldeira, 1999; Rau et al., 2007; Huysmans et al., 2025).

Formatted: Font: Not Bold

Formatted: Font: Not Bold

Formatted: Font: Not Bold

525 In this study, short-term weathering of LKD and CKD in seawater produced up to 8.02 ± 0.53 and 2.38 ± 0.16 mol of alkalinity
per kg of source material, respectively (Fig. 2C). On average, 1 mol of added alkalinity sequesters 0.84 mol CO₂ in surface
ocean waters (Schulz et al., 2023), thus resulting in 297 ± 20 g CO₂ kg⁻¹ LKD and 88 ± 6 g CO₂ kg⁻¹ CKD. With current global
annual production of approximately 29 Mt for LKD and 287 Mt for CKD (CEMBUREAU, 2024; USGS, 2025), their maximum
530 carbon dioxide removal potential via dissolution in seawater, assuming an average of 0.07 t of kiln dust produced per tonne of
lime or cement (Al-Refeai and Al-Karni, 1999), is approximately 8.7 ± 0.6 Mt CO₂ yr⁻¹ for LKD and 25 ± 2 Mt CO₂ yr⁻¹ for
CKD. Additional CO₂ uptake through metabolic calcite dissolution in coastal and shelf sediments could potentially further
increase this to 13.4 Mt yr⁻¹ for LKD and 57 Mt yr⁻¹ for CKD, although the effectiveness and time scaling of this process are
uncertain. Cumulatively, this would amount to 1 Gt and 4.3 Gt CO₂ by 2100, assuming constant kiln dust production rates and
535 complete utilization for OAE from 2025 onwards. While significant, this represents only 1.9–2.8 % of the 2.5–3.7 Gt CO₂
emitted annually by the cement and lime industries (Simoni et al., 2022; Cheng et al., 2023). Therefore, decarbonizing these
sectors remains the top priority for effective climate change mitigation (Simoni et al., 2022; Barbhuiya et al., 2024).

The CDR estimates presented here are upper-bound values, assuming that all globally produced LKD and CKD will be used
540 for OAE, and that production rates remain constant throughout the 21st century. In practice, some kiln dust will be used for
other economically viable applications (Al-Bakri et al., 2022), while on the other hand, cement demand is projected to increase
by 12–23 % by 2050, which will increase kiln dust production (IEA, 2018). CO₂ emissions from transporting kiln dust to the
ocean were not considered, but their impact on net CDR is likely minor if deployment occurs near production sites with
minimal road transport (Foteinis et al., 2022). These CDR estimates also assume full atmospheric CO₂ equilibration of A_T–

540 enriched surface waters ($\gamma_{CO_2} \approx 0.84$), while actual values in coastal regions are possibly lower ($\gamma_{CO_2} \approx 0.65 - 0.8$), due to
alkalinity transport to the deep ocean without prior atmospheric exchange (He and Tyka, 2023). Therefore, application should
focus on continental shelf seas, especially those with [organic-rich](#), carbonate-poor sediments (Lunstrum and Berelson, 2022;
Dale et al., 2024), to promote metabolic $CaCO_3$ dissolution and maximize the CDR potential. Importantly, only one specific
type of CKD and LKD were tested in this study, and mineralogical and chemical composition can vary significantly with the
545 production process, thus affecting the CDR potential (Pavía and Regan, 2010; Siddique, 2014; Drapanauskaite et al., 2021).
Tailoring application concentrations to site-specific conditions and material properties is therefore essential for safe and
effective deployment.


5 Conclusions

Cement kiln dust (CKD) and lime kiln dust (LKD) are abundant, fine-grained, and alkaline industrial byproducts available at
550 low cost. We conducted laboratory experiments to evaluate their suitability as mineral-based OAE feedstocks. Reactive phases
in CKD and LKD dissolved rapidly in [continuously stirred](#) seawater, with 65–92 % dissolving within 1 hour and complete
reactive phase dissolution within 24 hours. LKD generated up to 8.02 ± 0.53 mmol of alkalinity per g, compared to $2.38 \pm$
 0.16 mmol g⁻¹ for CKD. Alkalinity consuming secondary aragonite precipitation was observed at saturation states ≥ 6.2 , with
a saturation state of ~ 5 identified as a safe threshold. Based on current global production (~ 29 Mt year⁻¹ for LKD and ~ 287 Mt
555 year⁻¹ for CKD), the theoretical maximum CDR potential via dissolution in seawater is 8.7 ± 0.6 Mt CO₂ year⁻¹ for LKD and
 25 ± 2 Mt CO₂ year⁻¹ for CKD. Turbidity increases from both LKD and CKD, and trace metal release from CKD, present
potential environmental risks. To minimize secondary mineral formation and ecological impacts, site-specific application
concentrations should be determined through particle dispersal modelling that accounts for local hydrodynamic conditions. A
large portion of both materials, 75 % of LKD and 71 % of CKD, remained undissolved, with calcite making up 72 % and 52
560 % of this residual fraction, respectively. If this residual calcite undergoes metabolic dissolution in marine sediments, it could
further contribute to CDR, potentially adding up to 4.7 Mt CO₂ year⁻¹ for LKD and 32 Mt CO₂ year⁻¹ for CKD, although this
requires further experimental validation. Overall, LKD and, to a lesser extent, CKD show promise for OAE, with a CDR
potential of up to 13.4 Mt year⁻¹ for LKD and 57 Mt year⁻¹ for CKD at current production levels, [based on our small-scale](#)

laboratory experiments. However, additional experiments that more closely mimic natural conditions are warranted to further
565 constrain particle behaviour in the water column, interactions with sediments, and potential biological impacts of kiln-dust-based OAE.

Appendix A: Kiln dust properties

A1 Grain size, specific surface area, and elemental composition

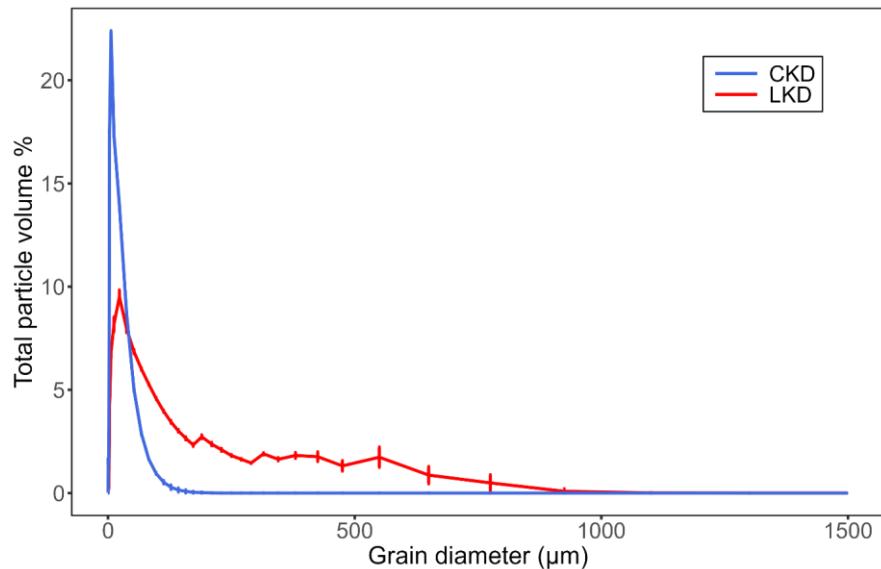

570 | Figure A1: Volumetric grain size distribution of the fresh lime kiln dust (LKD, in red) and cement kiln dust (CKD, in ~~redblue~~). Mean and standard deviation are shown (N = 3).

The geometric surface area A_{GEO} ($\text{m}^2 \text{ g}^{-1}$) of the experimental kiln dusts is shown in Table 2 of the main text. It was calculated
575 from the different grain diameter classes i ($n = 37$, between 0.35 and 1300 μm grain diameter) of the volumetric particle size distribution (Fig. A1) as

$$A_{GEO} = \sum_{i=1}^n \left(\frac{\frac{V_{KD_i}}{V_{grain_i}} * A_{grain_i}}{\rho_{KD}} \right) \quad (1)$$

Where V_{KD_i} represents the relative volume ($\text{cm}^3 \text{ cm}^{-3}$) for a certain grain diameter class i (e.g. 180 – 200 μm). V_{grain_i} and A_{grain_i} are the volume (cm^3) and surface area (m^2) of a single KD grain calculated from the average grain diameter of a certain grain diameter class (e.g. 190 μm for 180 – 200 μm), assuming perfect spherical particles. ρ_{KD} is the specific gravity of the kiln dust (g cm^{-3}).

Table A1: Elemental composition (wt%) of the cement kiln dust (CKD) and lime kiln dust (LKD). Concentrations were analysed via ICP-OES after heated digestion in a mixture of HClO_4 , HNO_3 , and HF as described in section 23.1 of the main text.


Element composition (wt%)	CKD	LKD
Al	3.02	0.038
As	<0.000016	<0.000016
Ba	0.044	0.00082
Be	0.000095	0.000012
Ca	27.8	44.9
Cd	0.0030	<0.00000085
Ce	0.0025	<0.0000028
Co	0.0015	<0.0000021
Cr	0.017	0.0011
Cu	0.028	0.0015
Fe	2.44	0.11
K	6.05	0.17
Li	0.0079	0.00025
Mg	0.57	0.22
Mn	0.11	0.0049
Mo	<0.0000082	<0.0000082
Na	1.22	0.080
Ni	0.011	<0.0000043
P	0.12	<0.000011
Pb	0.15	<0.000014
S	4.64	0.63
Sc	0.00046	<0.00000008
Sr	0.072	0.028
Ti	0.19	0.0013
V	0.036	0.00063
Y	0.0013	0.00016
Zn	0.65	0.0029

585 **A2 Kiln dust settling time**

To provide an initial simplified assessment of whether kiln dust particles could settle out of the ocean's mixed layer (assumed to be 200 m deep) before the complete dissolution of their reactive phases, Stokes' law (Eq. (2)) was applied to estimate their gravimetric settling velocity, assuming spherical particle geometry:

$$v = \frac{gd^2(\rho_p - \rho_s)}{18\eta} \quad (2)$$

590 where g is the acceleration of gravity ($9.81 \text{ m}^2 \text{ s}^{-1}$), d is the particle diameter (m), ρ_p is the density of the particle (2872 kg m^{-3} for LKD and 2712 kg m^{-3} for CKD), ρ_s is the density of the solution (1022 kg m^{-3} for 32 % seawater at 20°C), and η is the dynamic viscosity of the solution ($0.00108 \text{ kg m}^{-1} \text{ s}^{-1}$). Seawater density and dynamic viscosity were derived using the "swRho" and "swViscosity" function of the "oce" package in R. The settling time (h) required for particles to exit the mixed layer was calculated by dividing the mixed layer depth (200 m) by the settling velocity and converting the result from seconds to hours
595 by multiplying by 3600.

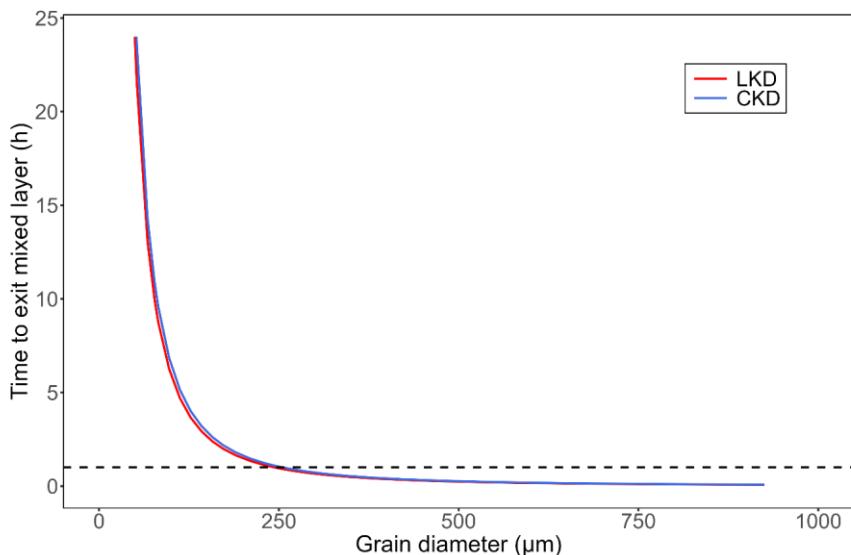

600 **Figure A2: Expected time for perfectly spherical lime kiln dust (LKD, in red) and cement kiln dust (CKD, in blue) particles to sink below the mixed layer depth (assumed to be 200 m) according to Stokes' law. Horizontal black dashed line at represents the time (1 h) at which most (72 – 85%) reactive phases in LKD and CKD have dissolved.**

After one hour of incubation at low application concentrations, most of the reactive phases in CKD ($72 \pm 12\%$) and LKD ($85 \pm 11\%$) had dissolved (Fig. 1B). Particles of LKD smaller than $244 \mu\text{m}$ and CKD smaller than $255 \mu\text{m}$ will remain suspended in the mixed layer for at least one hour (Fig. A2). Given the measured grain size distributions (Fig. A1), this means that 100% of CKD particles and $85 \pm 2\%$ of LKD particles would stay suspended in a 200 m in the mixed layer for this duration.

605

A3 Residual kiln dust fraction experiment

Due to the limited remaining material ($<70 \text{ mg}$) after the dissolution experiments presented in the main text, it was not possible to accurately quantify the residual mass of kiln dusts following dissolution in seawater. To address this, a separate small-scale test was conducted to determine the residual mass fraction. Two 2-liter plastic bottles were filled with 2 L of filtered seawater
610 and continuously aerated using air stones to speed up equilibration with atmospheric CO_2 . Kiln dust was added to each bottle at concentrations of 87 mg kg^{-1} for CKD and 21 mg kg^{-1} for LKD, three times per day over the course of three consecutive days. Additions were spaced a minimum of 2.5 hours apart to avoid high pH_{t} increases that might induce secondary aragonite formation. After the final addition, the bottles were left to incubate at room temperature ($16.1\text{--}17.5^\circ\text{C}$) for 24 hours to ensure complete dissolution of the reactive phases. The suspensions were then filtered through pre-weighed dried (at 60°C for 24 h)
615 0.3 μm pore size membrane filters (Seitz type M) using a Sartorius Microsart E-jet filtration unit. The filters were placed in pre-weighed Al foil cups, then dried at 60°C for 72 hours, and subsequently reweighed using the same Mettler Toledo XP26 Excellence Plus microbalance to determine the residual solid mass. For LKD, the residual fraction was 75.42% of the added mass (379.28 mg), while for CKD, it was 70.58% of the added mass (1567.65 mg).

Formatted: Subscript

Appendix B: Seawater parameters experiment II

620 B1 Observed seawater chemistry changes

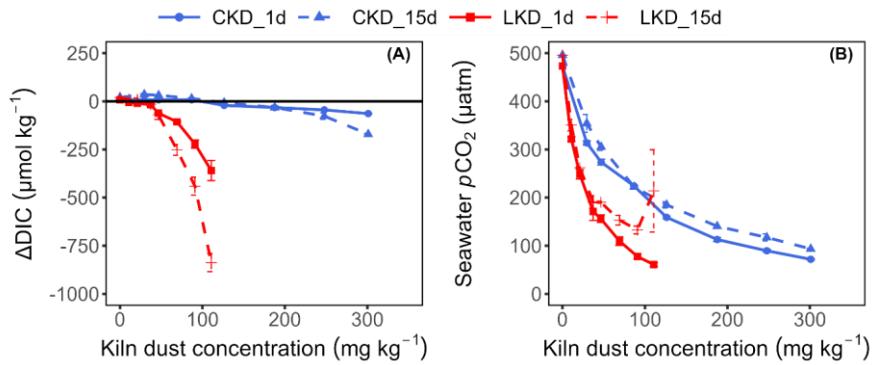
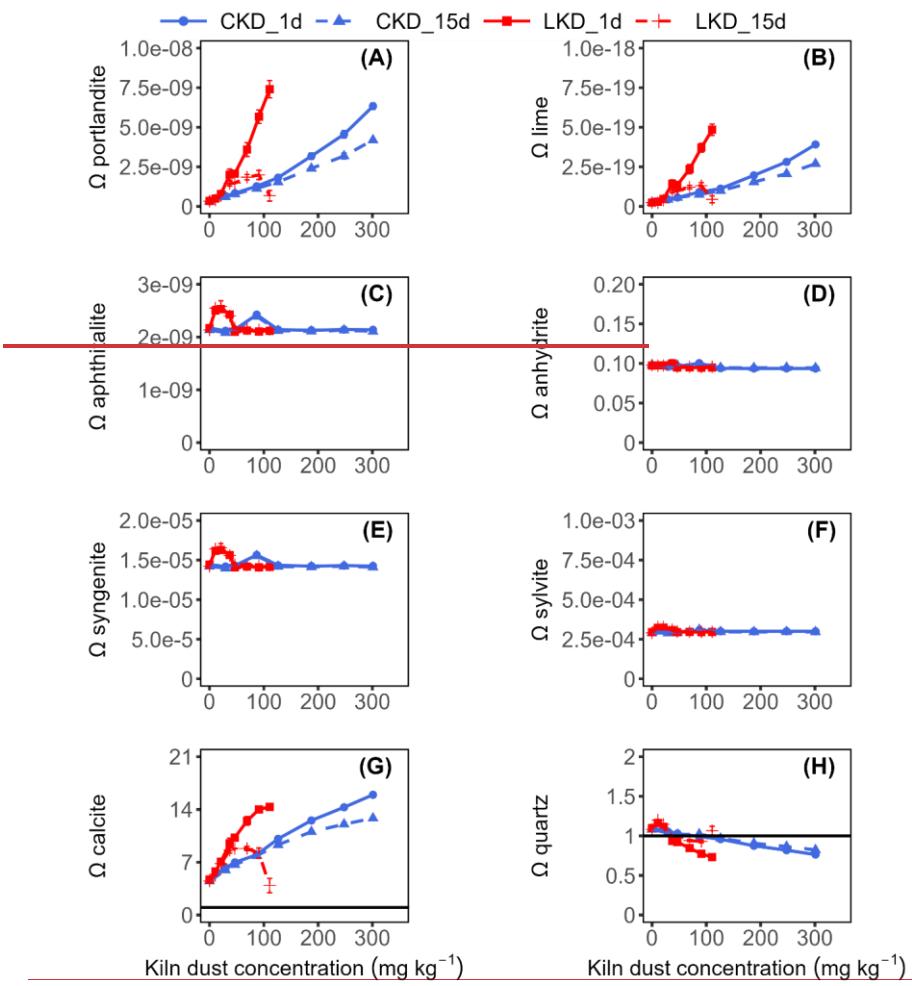


Figure B1. (A) Change in DIC concentration ($\mu\text{mol kg}^{-1}$) and (B) partial CO_2 pressure ($p\text{CO}_2$, expressed in μatm) as a function of the kiln dust application concentration (mg kg^{-1}) during dissolution experiment II. Results (as mean \pm S.D., $N=3$) are shown for lime kiln dust (LKD, in red) and cement kiln dust (CKD, in blue) after 1 day (solid lines) or 15 days of incubation (dashed lines) in FSW.

625




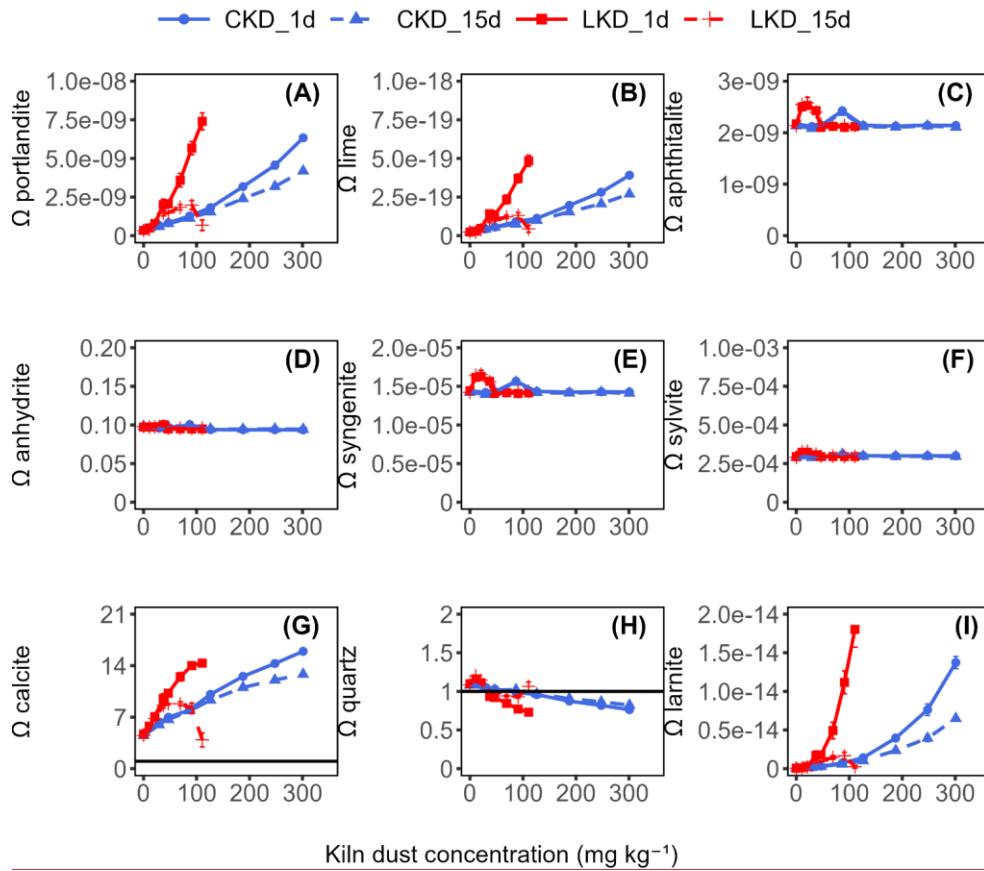


Figure B2. Saturation state (Ω) of (A) portlandite, (B) lime, (C) aphthalite, (D) anhydrite, (E) syngenite, (F) sylvite, (G) calcite, and (H) quartz, and (I) larnite as a function of the kiln dust application concentration (mg kg^{-1}) during experiment II. Results (as mean \pm S.D., $N=3$) are shown for lime kiln dust (LKD, in red) and cement kiln dust (CKD, in blue) after 1 day (solid lines) or 15 days of incubation (dashed lines) in FSW. The horizontal solid black line at $\Omega = 1$ represents the critical saturation threshold.

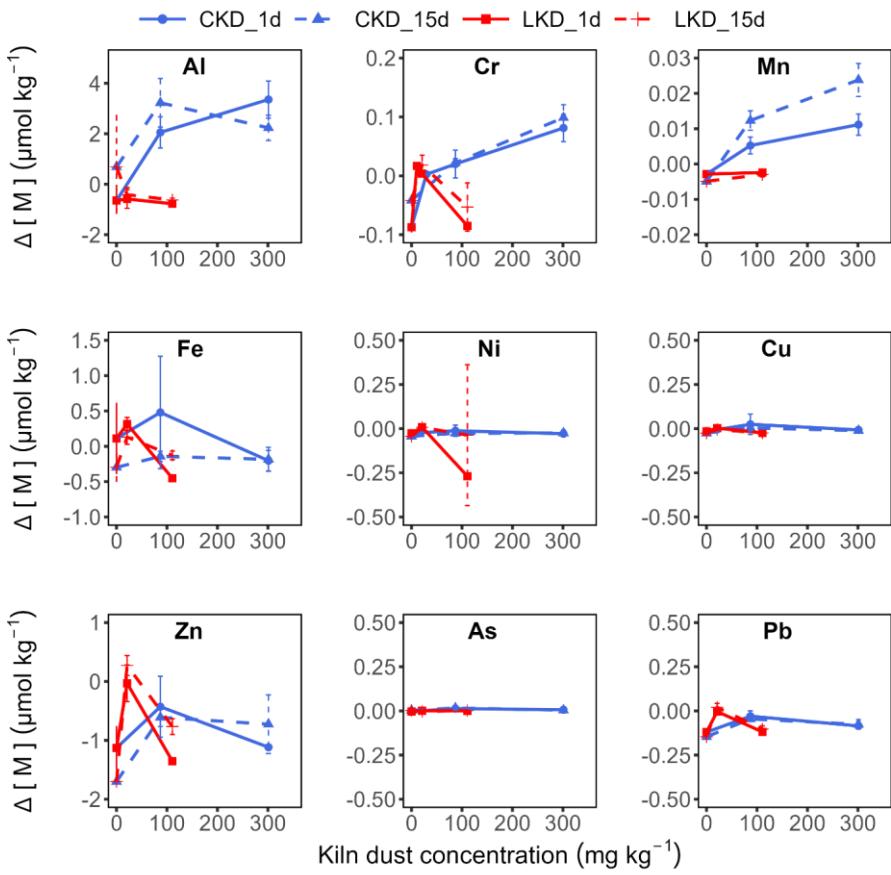

635 **Figure B3:** Metal(loid) accumulation in filtered seawater ($\mu\text{mol kg}^{-1}$) as a function of the kiln dust application concentration (mg kg^{-1}) during dissolution experiment II. The accumulation was calculated as the increase in metal(loid) concentrations above the initial seawater levels. Results (as mean \pm S.D., $N=3$) are shown for lime kiln dust (LKD, in red) and cement kiln dust (CKD, in blue) after 1 day (solid lines) or 15 days of incubation (dashed lines) in FSW.

B2 Expected seawater trace metal accumulation

640 The expected accumulation ΔC_i (expressed in $\mu\text{mol kg}^{-1}$) of a given metal(lloid) i in filtered seawater (FSW) under the assumption of stoichiometric KD weathering was calculated from the measured total metal(lloid) concentration χ (expressed in mg kg^{-1}) in the KD and the dissolved KD fraction φ_{diss} (dimensionless) as follows:

$$\Delta C_i = \frac{m_{KD} \varphi_{diss} \chi}{m_{FSW} M_i} \quad (3)$$

Where m_{KD} and m_{FSW} reflect the masses (g) of kiln dust and filtered seawater, respectively, used in the plastic incubation vials. M_i denotes the molar mass of a given metal(lloid) i .

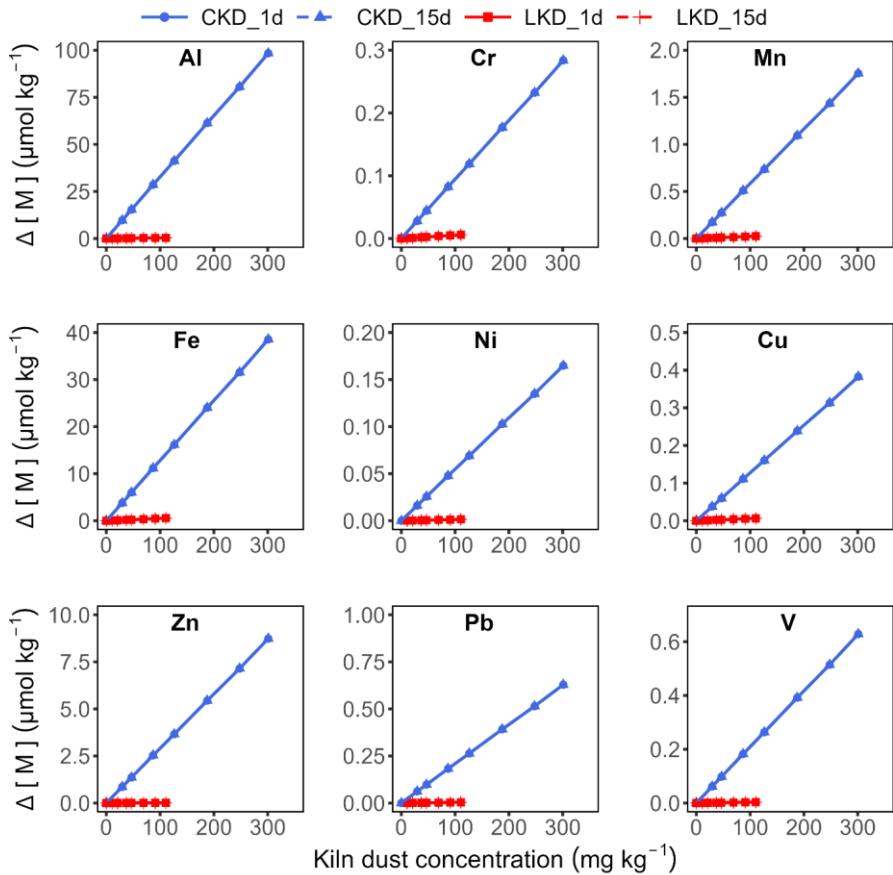


Figure B4. Expected metal(loid) accumulation in filtered seawater ($\mu\text{mol kg}^{-1}$) as a function of the kiln dust application concentration (mg kg^{-1}) during dissolution experiment II. Results are shown for lime kiln dust (LKD, in red) and cement kiln dust (CKD, in blue). Accumulation values after 1 day (solid lines) and 15 days (dashed lines) were assumed to be equal given that all total alkalinity 650 producing reactive phase dissolution occurred within the first day.

Appendix C: Maximum sedimentary kiln dust application concentration

In real-world ship-based deployments, residual kiln dust (KD) would settle on the seafloor, where it would be mixed into the surface sediment through local hydrodynamics and bioturbation. This accumulation and possible subsequent dissolution of residual KD, could lead to the build-up of metals in the surface sediment, potentially posing a toxicological risk to benthic 655 organisms. Sediment Quality Guidelines (SQGs) are employed to assess the risk of metal toxicity to marine biota in a tiered approach, with the first step involving the comparison of total sediment metal concentrations to these guidelines (Hübner et al., 2009; Simpson and Batley, 2016). The kiln dust contain a range of metals (Appendix A Table A1) of which Pb could mostly easily exceed existing SGQs based on preliminary screening. Following Flipkens et al. (2021) we derived the maximum allowable KD application m_{app} (expressed in kg m^{-2} seafloor) that would not exceed marine Pb SQGs via:

$$660 \quad m_{app} = \frac{(C_{SQG} - C_{bg})V_s\rho_s(1-\phi)}{\chi} \quad (4)$$

where C_{SQG} is the sediment quality guideline for Pb (mg kg^{-1} dry wt), C_{bg} is the background sedimentary Pb concentration (mg kg^{-1} dry wt), V_s is the volume of the sediment in which the kiln dust is mixed per m^2 of seabed ($\text{m}^3 \text{ m}^{-2}$ seabed), ρ_s is the specific density of marine sediment (2650 kg m^{-3}), ϕ is the porosity of the sediment, and χ is the concentration of Pb (mg kg^{-1} dry wt) in CKD or LKD (Table A1). The porosity of marine surface sediment was assumed to be 0.60 based on the predicted 665 global coastal sediment porosity ranging from approximately 0.50 to 0.85 (Martin et al., 2015). A sediment mixing depth of 10 cm was assumed, reflecting the typical depth where most benthic biota are found (Simpson and Batley, 2016; Solan et al., 2019). Given the global variation in Pb SQGs, maximum allowable KD application (m_{app}) calculations were made using different sediment quality guidelines, including the Chinese Interim Sediment Quality Guideline–Low (ISQV-low), the Australian Interim Sediment Quality Guideline–Low (ISQG-low), the Norwegian Predicted No Effect Concentration (PNEC), 670 and the American Threshold Effect Level (TEL) (Hübner et al., 2009).

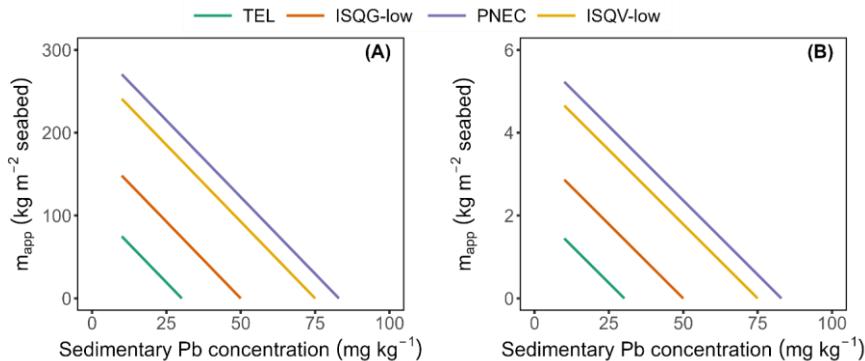


Figure C1: Maximum allowable application (m_{app} , expressed in kg m^{-2}) of (A) lime kiln dust or (B) cement kiln, without exceedance of lead (Pb) sediment quality guidelines (SQGs), plotted as a function of the background sedimentary Pb concentration (mg kg^{-1}). The considered SQGs include the Threshold Effect Level (TEL, green), the Interim Sediment Quality Guideline-low (ISQG-low, orange), the Predicted No Effect Concentration (PNEC, blue), and the Interim Sediment Quality Value-low (ISQV-low, yellow). A sediment mixing depth of 10 cm was assumed, and kiln dust Pb concentrations were based on measured values reported in Table A1. Results represent a conservative, worst-case scenario in which all Pb released during KD dissolution is retained within the sediment.

675

680 Code availability

The code used for analysis in this study is available upon request. Interested parties may contact the corresponding author.

Data availability

The data supporting the findings of this study have been deposited in Zenodo, DOI: <https://doi.org/10.5281/zenodo.1793838> <https://doi.org/10.5281/zenodo.1717449>. They are under embargo until the 1 June 685 2026, after which they will be publicly available. Reviewers have access via the following link: https://zenodo.org/records/17174450?token=eyJhbGciOiJIUzUxMiJ9eyJpZCI6IjBmYWQxODBkLWRiZTItNDNkYyIiYmZmLTJODjkZjZjNWFkZjIiImRhdGEiOnt9LCIyYW5k20iI2MDUwYTgzYjE4ZTF1NDRiN2E4NDVjNGE2Y2UwNGNiNyJ9.LbKTFMoy80SNuFdLtX2e8797eHhtKkoh-HH9XLRBSe6FvMkveXWMVXIN5BEwDVRT43Ke_JeJF99FKThMv7PwA.

690 **Author contribution**

GF was responsible for conceptualization, data curation, formal analysis, investigation, methodology, visualization, writing original draft preparation, and writing review and editing. GF and GL carried out the investigation. FJRM was responsible for conceptualization, methodology, funding acquisition, resources, supervision, and writing review and editing.

Competing interests

695 The authors declare that they have no conflict of interest.

Acknowledgements

The authors thank Afshin Neshad Ashkzari and Helen de Waard (Utrecht University) for conducting the ICP-OES analyses, Max Van Brussele (UAntwerpen) for the ICP-MS analysis, and Tom Van Gerven and Michèle Vanroelen (KU Leuven) for the BET analysis. Moreover, we appreciated the help of Romello Cavalier (UAntwerpen) with the sample collection and we 700 thank Tom Huysmans (UAntwerpen) for diluting the seawater samples for ICP-MS analysis. Finally, during the preparation of this work, the authors used ChatGPT to assist in improving the flow of the text. All content was subsequently reviewed and edited by the authors, who take full responsibility for the final content of the publication.

Financial support

This research was supported by the VLAIO De Blauwe Cluster project “Blue Alkalinity” (HBC.2023.0496).

705 **References**

Adekunle, S. K.: Carbon sequestration potential of cement kiln dust: mechanisms, methodologies, and applications, *J. Clean. Prod.*, 446, 141283, <https://doi.org/10.1016/j.jclepro.2024.141283>, 2024.

Ahmed, H. M., Hefni, M. A., Ahmed, H. A., Saleem, H. A.: Cement kiln dust (CKD) as a partial substitute for cement in pozzolanic concrete blocks, *Buildings*, 13, 568, <https://doi.org/10.3390/buildings13020568>, 2023.

710 Ahmerkamp, S., Winter, C., Krämer, K., Beer, D. d., Janssen, F., Friedrich, J., Kuypers, M. M., Holtappels, M.: Regulation of benthic oxygen fluxes in permeable sediments of the coastal ocean, *Limnol. Oceanogr.*, 62, 1935-1954, <https://doi.org/10.1002/limo.10544>, 2017.

Al-Bakri, A. Y., Ahmed, H. M., Hefni, M. A.: Cement kiln dust (CKD): potential beneficial applications and eco-sustainable solutions, *Sustainability*, 14, 7022, <https://doi.org/10.3390/su14127022>, 2022.

715 Al-Refaei, T. O., Al-Karni, A. A.: Experimental study on the utilization of cement kiln dust for ground modification, *J. King Saud Univ. Eng. Sci.*, 11, 217-231, [https://doi.org/10.1016/S1018-3639\(18\)30999-1](https://doi.org/10.1016/S1018-3639(18)30999-1), 1999.

ANZECC, ARMCANZ: Australian and New Zealand Guidelines for Fresh and Marine Water Quality. Retrieved from <https://www.waterquality.gov.au/sites/default/files/documents/anzecc-armcanz-2000-guidelines-vol1.pdf2000>.

720 Arulrajah, A., Mohammadinia, A., D'Amico, A., Horpibulsuk, S.: Effect of lime kiln dust as an alternative binder in the stabilization of construction and demolition materials, *Constr. Build. Mater.*, 152, 999-1007, <https://doi.org/10.1016/j.conbuildmat.2017.07.070>, 2017.

Ayman, G., Shoib, M., Balaha, M.: Thermo-chemical stability and mechanical properties of mortar made with cement kiln dust-blended cement, *Eng. Res. J.*, 27, 49-58, https://erjm.journals.ekb.eg/article_82610_bc01c253b2da0256a63c6232f9fad8e0.pdf, 2004.

725 Bach, L. T., Gill, S. J., Rickaby, R. E., Gore, S., Renforth, P.: CO₂ removal with enhanced weathering and ocean alkalinity enhancement: Potential risks and co-benefits for marine pelagic ecosystems, *Front. clim.*, 1, 7, <https://doi.org/10.3389/fclim.2019.00007>, 2019.

Ban, C. C., Ee, T. L., Ramlı, M., Akil, H. B. M., Mo, K. H.: Properties and microstructure of lime kiln dust activated slag-fly ash mortar, *Constr. Build. Mater.*, 347, 128518, <https://doi.org/10.1016/j.conbuildmat.2022.128518>, 2022.

730 Barbhuiya, S., Kanavaris, F., Das, B. B., Idrees, M.: Decarbonising cement and concrete production: Strategies, challenges and pathways for sustainable development, *J. Build. Eng.*, 108861, <https://doi.org/10.1016/j.jobe.2024.108861>, 2024.

Barnat-Hunek, D., Góra, J., Suchorab, Z., Łagód, G.: Cement kiln dust, Waste and Supplementary Cementitious Materials in Concrete, Elsevier, 149-180, <https://doi.org/10.1016/B978-0-08-102156-9.00005-5>, 2018.

735 Bell, J. J., McGrath, E., Biggerstaff, A., Bates, T., Bennett, H., Marlow, J., Shaffer, M.: Sediment impacts on marine sponges, *Mar. Pollut. Bull.*, 94, 5-13, <https://doi.org/10.1016/j.marpolbul.2015.03.030>, 2015.

Beltagui, H., Sonebi, M., Maguire, K., Taylor, S.: Utilisation of cement kiln dust for the activation of fly ash in low strength applications, *Acad. j. civil eng.*, 35, 549-553, 2017.

740 Biçer, K., Myers Stewart, T., Waldbusser, G. G., Meile, C.: The effect of carbonate mineral additions on biogeochemical conditions in surface sediments and benthic-pelagic exchange fluxes, *Biogeosciences*, 22, 641-657, <https://doi.org/10.5194/bg-22-641-2025>, 2025.

Brand, A. S., Gorham, J. M., Bullard, J. W.: Dissolution rate spectra of β -dicalcium silicate in water of varying activity, *Cem. Concr. Res.*, 118, 69-83, <https://doi.org/10.1016/j.cemconres.2019.02.014>, 2019.

Buckingham, F., Henderson, G.: The enhanced weathering potential of a range of silicate and carbonate additions in a UK agricultural soil, *Sci. Total Environ.*, 907, 167701, <https://doi.org/10.1016/j.scitotenv.2023.167701>, 2024.

745 Bullock, L. A., James, R. H., Matter, J., Renforth, P., Teagle, D. A.: Global carbon dioxide removal potential of waste materials from metal and diamond mining, *Front. clim.*, 3, 694175, <https://doi.org/10.3389/fclim.2021.694175>, 2021.

Bullock, L. A., Yang, A., Darton, R. C.: Kinetics-informed global assessment of mine tailings for CO₂ removal, *Sci. Total Environ.*, 808, 152111, <https://doi.org/10.1016/j.scitotenv.2021.152111>, 2022.

Burdige, D.: *Geochemistry of Marine Sediments*, Princeton New Jersey, Princeton University Press, <https://doi.org/10.1515/9780691216096>, 2006.

750 Camatti, E., Valsecchi, S., Caserini, S., Barbaccia, E., Santinelli, C., Basso, D., Azzellino, A.: Short-term impact assessment of ocean liming: A copepod exposure test, *Mar. Pollut. Bull.*, 198, 115833, <https://doi.org/10.1016/j.marpolbul.2023.115833>, 2024.

Canfield, D. E.: Reactive iron in marine sediments, *Geochim. Cosmochim. Acta*, 53, 619-632, 1989.

755 Caserini, S., Paganò, D., Campo, F., Abbà, A., De Marco, S., Righi, D., Renforth, P., Grosso, M.: Potential of maritime transport for ocean liming and atmospheric CO₂ removal, *Front. clim.*, 3, 575900, <https://doi.org/10.3389/fclim.2021.575900>, 2021.

Caserini, S., Storni, N., Grosso, M.: The availability of limestone and other raw materials for ocean alkalinity enhancement, *Glob. Biogeochem. Cycles*, 36, e2021GB007246, <https://doi.org/10.1029/2021GB007246>, 2022.

760 CEMBUREAU: The European cement association (Cembureau) 2023 activity report, <https://cembureau.eu/media/dnb4xzc/activity-report-2023-for-web.pdf>, 2024.

Cheng, D., Reiner, D. M., Yang, F., Cui, C., Meng, J., Shan, Y., Liu, Y., Tao, S., Guan, D.: Projecting future carbon emissions from cement production in developing countries, *Nat. Commun.*, 14, 8213, <https://doi.org/10.1038/s41467-023-43660-x>, 2023.

765 Cheung, S., Shin, P.: Size effects of suspended particles on gill damage in green-lipped mussel *Perna viridis*, *Mar. Pollut. Bull.*, 51, 801-810, <https://doi.org/10.1016/j.marpolbul.2005.02.019>, 2005.

Cloern, J. E.: Turbidity as a control on phytoplankton biomass and productivity in estuaries, *Cont. Shelf Res.*, 7, 1367-1381, [https://doi.org/10.1016/0278-4343\(87\)90042-2](https://doi.org/10.1016/0278-4343(87)90042-2), 1987.

770 Collins, R. J., Emery, J.: Kiln dust-fly ash systems for highway bases and subbases, United States Department of Transportation - Federal Highway Administration.<https://rosap.ntl.bts.gov/view/dot/41861>, 1983.

Dale, A. W., Geilert, S., Diercks, I., Fuhr, M., Perner, M., Scholz, F., Wallmann, K.: Seafloor alkalinity enhancement as a carbon dioxide removal strategy in the Baltic Sea, *Commun. Earth Environ.*, 5, 452, <https://doi.org/10.1038/s43247-024-01569-3>, 2024.

775 Dan-Asabe, B., Yaro, S., Yawas, D., Aku, S.: Water displacement and bulk density-relation methods of finding density of powdered materials, *Int J of Innov Res in Sc, Eng and Tech*, 2, 2013.

Dickson, A. G., Sabine, C. L., Christian, J. R.: Guide to best practices for ocean CO₂ measurements, North Pacific Marine Science Organization, <https://doi.org/10.25607/OPB-1342>, 2007.

780 Drapanauskaite, D., Buneviciene, K., Repsiene, R., Mazeika, R., Navea, J., Baltrusaitis, J.: Physicochemical characterization of pelletized lime kiln dust as potential liming material for acidic soils, *Waste Biomass Valorization*, 12, 1267-1280, <https://doi.org/10.1007/s12649-020-01107-0>, 2021.

Dvorkin, L., Zhirkovsky, V.: Cement-ash concrete with the addition of lime kiln dust, *Front. Mater.*, 10, 1196407, <https://doi.org/10.3389/fmats.2023.1196407>, 2023.

El-Attar, M. M., Sadek, D. M., Salah, A. M.: Recycling of high volumes of cement kiln dust in bricks industry, *J. Clean. Prod.*, 143, 506-515, <https://doi.org/10.1016/j.jclepro.2016.12.082>, 2017.

785 Elbaz, A., Aboulfotoh, A., Dohdoh, A., Wahba, A.: Review of beneficial uses of cement kiln dust (CKD), fly ash (FA) and their mixture, *J. Mater. Environ. Sci.*, 10, 1062-1073, 2019.

Fennel, K., Long, M. C., Algar, C., Carter, B., Keller, D., Laurent, A., Mattern, J. P., Musgrave, R., Oschlies, A., Ostiguy, J.: Modeling considerations for research on Ocean Alkalinity Enhancement (OAE), *State of the Planet Discussions*, 2023, 1-47, <https://doi.org/10.5194/sp-2-oea2023-9-2023>.

790 Flipkens, G., Blust, R., Town, R. M.: Deriving nickel (Ni (II)) and chromium (Cr (III)) based environmentally safe olivine guidelines for coastal enhanced silicate weathering, *Environ. Sci. Technol.*, 55, 12362-12371, <https://doi.org/10.1021/acs.est.1c02974>, 2021.

Flipkens, G., Dujardin, V., Salden, J., T'Jollyn, K., Town, R. M., Blust, R.: Olivine avoidance behaviour by marine gastropods (*Littorina littorea* L.) and amphipods (*Gammarus locusta* L.) within the context of ocean alkalinity enhancement, *Ecotoxicol. Environ. Saf.*, 270, 115840, <https://doi.org/10.1016/j.ecoenv.2023.115840>, 2024.

795 Flipkens, G., Fuhr, M., Fiers, G., Meysman, F. J., Town, R. M., Blust, R.: Enhanced olivine dissolution in seawater through continuous grain collisions, *Geochim. Cosmochim. Acta*, 359, 84-99, <https://doi.org/10.1016/j.gca.2023.09.002>, 2023.

Foteinidis, S., Andrensen, J., Campo, F., Caserini, S., Renforth, P.: Life cycle assessment of ocean liming for carbon dioxide removal from the atmosphere, *J. Clean. Prod.*, 370, 133309, <https://doi.org/10.1016/j.jclepro.2022.133309>, 2022.

800 Fuhr, M., Dale, A. W., Wallmann, K., Bährle, R., Kalapurakkal, H. T., Sommer, S., Spiegel, T., Dobashi, R., Buchholz, B., Schmidt, M.: Calcite is an efficient and low-cost material to enhance benthic weathering in shelf sediments of the Baltic Sea, *Commun. Earth Environ.*, 6, 106, <https://doi.org/10.1038/s43247-025-02079-6>, 2025.

Geerts, L. J., Hylén, A., Meysman, F. J.: Review and syntheses: Ocean alkalinity enhancement and carbon dioxide removal through marine enhanced rock weathering using olivine, *Biogeosciences*, 22, 355-384, <https://doi.org/10.5194/bg-22-355-2025>, 2025.

Harris, K. E., DeGrandpre, M. D., Hales, B.: Aragonite saturation state dynamics in a coastal upwelling zone, *Geophys. Res. Lett.*, 40, 2720-2725, <https://doi.org/10.1002/grl.50460>, 2013.

Hartmann, J., Suttnar, N., Lim, C., Schneider, J., Marín-Samper, L., Arístegui, J., Renforth, P., Taucher, J., Riebesell, U.: 805 Stability of alkalinity in ocean alkalinity enhancement (OAE) approaches—consequences for durability of CO₂ storage, *Biogeosci. Disc.*, 20, 781-802, <https://doi.org/10.5194/bg-20-781-2023>, 2023.

He, J., Tyka, M. D.: Limits and CO₂ equilibration of near-coast alkalinity enhancement, *Biogeosciences*, 20, 27-43, <https://doi.org/10.5194/bg-20-27-2023>, 2023.

815 Hem, J. D.: Study and interpretation of the chemical characteristics of natural water, Department of the Interior, US Geological Survey, <https://doi.org/10.3133/wsp2254>, 1985.

Hofmann, A. F., Soetaert, K., Middelburg, J. J., Meysman, F. J.: AquaEnv: An Aquatic Acid–Base Modelling Environment in R, *Aquat. Geochem.*, 16, 507-546, <https://doi.org/10.1007/s10498-009-9084-1>, 2010.

Hu, M., Dong, T., Cui, Z., Li, Z.: Mechanical behavior and microstructure evaluation of quicklime-activated cement kiln dust-slag binder pastes, *Materials*, 17, 1253, <https://doi.org/10.3390/ma17061253>, 2024.

820 Hübner, R., Astin, K. B., Herbert, R. J.: Comparison of sediment quality guidelines (SQGs) for the assessment of metal contamination in marine and estuarine environments, *J. Environ. Monit.*, 11, 713-722, <https://doi.org/10.1039/B818593J>, 2009.

Huntzinger, D. N., Eatmon, T. D.: A life-cycle assessment of Portland cement manufacturing: comparing the traditional process with alternative technologies, *J. Clean. Prod.*, 17, 668-675, <https://doi.org/10.1016/j.jclepro.2008.04.007>, 2009.

825 Huntzinger, D. N., Gierke, J. S., Sutter, L. L., Kawatra, S. K., Eisele, T. C.: Mineral carbonation for carbon sequestration in cement kiln dust from waste piles, *J. Hazard. Mater.*, 168, 31-37, <https://doi.org/10.1016/j.jhazmat.2009.01.122>, 2009.

Huysmans, T., Meysman, F. J., van de Velde, S. J.: Reviews and syntheses: Potential and limitations of oceanic carbon dioxide storage via reactor-based accelerated weathering of limestone, *Biogeosciences*, 22, 5557-5572, <https://doi.org/10.5194/bg-22-5557-2025>, 2025.

IEA: Cement technology roadmap plots path to cutting CO₂ emissions 24% by 2050. <https://www.iea.org/news/cement-technology-roadmap-plots-path-to-cutting-co2-emissions-24-by-2050>, Last access 18 September 2025, 2018.

830 IPCC: Climate Change 2023: Synthesis Report. Contribution of Working Groups I, II and III to the Sixth Assessment Report of the Intergovernmental Panel on Climate Change, IPCC. <https://doi.org/10.59327/IPCC/AR6-9789291691647>, 2023.

Kessler, A. J., Rogers, A., Cyronak, T., Bourke, M. F., Hasler-Sheetal, H., Glud, R. N., Greening, C., Meysman, F. J., Eyre, B. D., Cook, P. L.: Pore water conditions driving calcium carbonate dissolution in reef sands, *Geochim. Cosmochim. Acta*, 279, 16-28, <https://doi.org/10.1016/j.gca.2020.04.001>, 2020.

840 Khanna, O. S.: Characterization and utilization of cement kiln dusts (CKDs) as partial replacements of Portland cement, Ph.D. thesis, University of Toronto, <https://utoronto.scholaris.ca/server/api/core/bitstreams/58639a68-539a-4339-ae8d-f9b5181aaa64/content>, 2010.

Khesghi, H. S.: Sequestering atmospheric carbon dioxide by increasing ocean alkalinity, *Energy*, 20, 915-922, [https://doi.org/10.1016/0360-5442\(95\)00035-F](https://doi.org/10.1016/0360-5442(95)00035-F), 1995.

845 Kitidis, V., Rackley, S. A., Burt, W. J., Rau, G. H., Fawcett, S., Taylor, M., Tarhan, G., Woodward, E. M. S., Harris, C., Fileman, T.: Magnesium hydroxide addition reduces aqueous carbon dioxide in wastewater discharged to the ocean, *Commun. Earth Environ.*, 5, 354, <https://doi.org/10.1038/s43247-024-01506-4>, 2024.

Köhler, P., Abrams, J. F., Völker, C., Hauck, J., Wolf-Gladrow, D. A.: Geoengineering impact of open ocean dissolution of olivine on atmospheric CO₂, surface ocean pH and marine biology, *Environ. Res. Lett.*, 8, 014009, <https://doi.org/10.1088/1748-9326/8/1/014009>, 2013.

850 Latif, M. A., Naganathan, S., Razak, H. A., Mustapha, K. N.: Performance of lime kiln dust as cementitious material, *Procedia Engineering*, 125, 780-787, <https://doi.org/10.1016/j.proeng.2015.11.135>, 2015.

Lee, A.: North Sea physical oceanography, *Elsevier Oceanogr Ser*, Elsevier, 467-493, [https://doi.org/10.1016/S0422-9894\(08\)71359-X](https://doi.org/10.1016/S0422-9894(08)71359-X), 1980.

855 Lee, W.-S., Choi, Y.-C.: Hydration and Mechanical Properties of Cement Kiln Dust-Blended Cement Composite, *Materials*, 17, 4841, <https://doi.org/10.3390/ma17194841>, 2024.

Liu, X., Dunne, J. P., Stock, C. A., Harrison, M. J., Adcroft, A., Resplandy, L.: Simulating Water Residence Time in the Coastal Ocean: A Global Perspective, *Geophys. Res. Lett.*, 46, 13910-13919, <https://doi.org/10.1029/2019GL085097>, 2019.

860 Lowe, M., Morrison, M., Taylor, R.: Harmful effects of sediment-induced turbidity on juvenile fish in estuaries, *Mar. Ecol. Prog. Ser.*, 539, 241-254, <https://doi.org/10.3354/meps11496>, 2015.

Lueker, T. J., Dickson, A. G., Keeling, C. D.: Ocean pCO₂ calculated from dissolved inorganic carbon, alkalinity, and equations for K1 and K2: validation based on laboratory measurements of CO₂ in gas and seawater at equilibrium, *Mar. Chem.*, 70, 105-119, [https://doi.org/10.1016/S0304-4203\(00\)00022-0](https://doi.org/10.1016/S0304-4203(00)00022-0), 2000.

865 Lunstrum, A., Berelson, W.: CaCO₃ dissolution in carbonate-poor shelf sands increases with ocean acidification and porewater residence time, *Geochim. Cosmochim. Acta*, 329, 168-184, <https://doi.org/10.1016/j.gca.2022.04.031>, 2022.

Lunt, J., Smee, D. L.: Turbidity alters estuarine biodiversity and species composition, *ICES J. Mar. Sci.*, 77, 379-387, <https://doi.org/10.1093/icesjms/fsz214>, 2020.

Martin, K. M., Wood, W. T., Becker, J. J.: A global prediction of seafloor sediment porosity using machine learning, *Geophys. Res. Lett.*, 42, 10,640-610,646, <https://doi.org/10.1002/2015GL065279>, 2015.

870 Minx, J. C., Lamb, W. F., Callaghan, M. W., Fuss, S., Hilaire, J., Creutzig, F., Amann, T., Beringer, T., de Oliveira Garcia, W., Hartmann, J.: Negative emissions—Part 1: Research landscape and synthesis, *Environ. Res. Lett.*, 13, 063001, <https://doi.org/10.1088/1748-9326/aabf9b>, 2018.

875 Montserrat, F., Renforth, P., Hartmann, J., Leermakers, M., Knops, P., Meysman, F. J.: Olivine dissolution in seawater: implications for CO₂ sequestration through enhanced weathering in coastal environments, *Environ. Sci. Technol.*, 51, 3960-3972, <https://doi.org/10.1021/acs.est.6b05942>, 2017.

Moras, C. A., Bach, L. T., Cyronak, T., Joannes-Boyau, R., Schulz, K. G.: Ocean alkalinity enhancement—avoiding runaway CaCO₃ precipitation during quick and hydrated lime dissolution, *Biogeosciences*, 19, 3537-3557, <https://doi.org/10.5194/bg-19-3537-2022>, 2022.

880 Moras, C. A., Joannes-Boyau, R., Bach, L. T., Cyronak, T., Schulz, K. G.: Carbon dioxide removal efficiency of iron and steel slag in seawater via ocean alkalinity enhancement, *Front. clim.*, 6, 1396487, <https://doi.org/10.3389/fclim.2024.1396487>, 2024.

Morse, J. W., Mackenzie, F. T.: *Geochemistry of sedimentary carbonates*, Elsevier, <https://www.sciencedirect.com/bookseries/developments-in-sedimentology/vol/48/suppl/C>, 1990.

885 Mucci, A.: The solubility of calcite and aragonite in seawater at various salinities, temperatures, and one atmosphere total pressure, *Am. J. Sci.*, 283, 780-799, <https://doi.org/10.2475/ajs.283.7.780>, 1983.

Nikolov, A., Kostov-Kytin, V., Tarassov, M., Tsvetanova, L., Jordanov, N. B., Karamanova, E., Rostovsky, I.: Characterization of cement kiln dust from Bulgarian cement plants, *J. Chem. Technol. Metall.*, 60, 455-463, <https://doi.org/10.5957/jctm.v60.i3.2025.11>, 2025.

890 Nyström, E., Kaasalainen, H., Alakangas, L.: Prevention of sulfide oxidation in waste rock by the addition of lime kiln dust, *Environ. Sci. Pollut. Res.*, 26, 25945-25957, <https://doi.org/10.1007/s11356-019-05846-z>, 2019.

Pan, Y., Li, Y., Ma, Q., He, H., Wang, S., Sun, Z., Cai, W.-J., Dong, B., Di, Y., Fu, W.: The role of Mg²⁺ in inhibiting CaCO₃ precipitation from seawater, *Mar. Chem.*, 237, 104036, <https://doi.org/10.1016/j.marchem.2021.104036>, 2021.

895 Parkhurst, D. L., Appelo, C.: Description of input and examples for PHREEQC version 3—a computer program for speciation, batch-reaction, one-dimensional transport, and inverse geochemical calculations, US geological survey techniques and methods, 6, 497, <https://doi.org/10.3133/tm6A43>, 2013.

Pavía, S., Regan, D.: Influence of cement kiln dust on the physical properties of calcium lime mortars, *Mater. Struct.*, 43, 381-391, <https://doi.org/10.1617/s11527-009-9496-9>, 2010.

Pedersen, M. F., Hansen, P. J.: Effects of high pH on a natural marine planktonic community, *Mar. Ecol. Prog. Ser.*, 260, 19-31, <https://doi.org/10.3354/meps260019>, 2003.

900 R Core Team: R: A language and environment for statistical computing., R foundation for statistical computing <http://www.R-project.org/>, 2022.

Rao, A. M., Polerecky, L., Ionescu, D., Meysman, F. J., De Beer, D.: The influence of pore-water advection, benthic photosynthesis, and respiration on calcium carbonate dynamics in reef sands, *Limnol. Oceanogr.*, 57, 809-825, <https://doi.org/10.4319/lo.2012.57.3.0809>, 2012.

905 Rau, G. H., Caldeira, K.: Enhanced carbonate dissolution: a means of sequestering waste CO₂ as ocean bicarbonate, *Energy Convers. Manage.*, 40, 1803-1813, 1999.

Rau, G. H., Knauss, K. G., Langer, W. H., Caldeira, K.: Reducing energy-related CO₂ emissions using accelerated weathering of limestone, *Energy*, 32, 1471-1477, <https://doi.org/10.1016/j.energy.2006.10.011>, 2007.

910 Renforth, P., Henderson, G.: Assessing ocean alkalinity for carbon sequestration, *Rev. Geophys.*, 55, 636-674, <https://doi.org/10.1002/2016RG000533>, 2017.

Renforth, P., Jenkins, B., Kruger, T.: Engineering challenges of ocean liming, *Energy*, 60, 442-452, <https://doi.org/10.1016/j.energy.2013.08.006>, 2013.

915 Rockström, J., Gaffney, O., Rogelj, J., Meinshausen, M., Nakicenovic, N., Schellnhuber, H. J.: A roadmap for rapid decarbonization, *Science*, 355, 1269-1271, <https://doi.org/10.1126/science.aaah3443>, 2017.

Santinelli, C., Valsecchi, S., Retelletti Brogi, S., Bachì, G., Checucci, G., Guerrazzi, M., Camatti, E., Caserini, S., Azzellino, A., Bassò, D.: Ocean liming effects on dissolved organic matter dynamics, *Biogeosciences*, 21, 5131-5141, <https://doi.org/10.5194/bg-21-5131-2024>, 2024.

920 Schulz, K. G., Bach, L. T., Dickson, A. G.: Seawater carbonate chemistry considerations for ocean alkalinity enhancement research: theory, measurements, and calculations, *State Planet Discuss.*, 2023, 1-24, <https://doi.org/10.5194/sp-2-oea2023-2-2023>, 2023.

Siddique, R.: Utilization of industrial by-products in concrete, *Procedia Engineering*, 95, 335-347, <https://doi.org/10.1016/j.proeng.2014.12.192>, 2014.

925 Siddique, R., Rajor, A.: Use of cement kiln dust in cement concrete and its leachate characteristics, *Resources, Conservation and Recycling*, 61, 59-68, <https://doi.org/10.1016/j.resconrec.2012.01.006>, 2012.

Simoni, M., Wilkes, M. D., Brown, S., Provis, J. L., Kinoshita, H., Hanein, T.: Decarbonising the lime industry: State-of-the-art, *Renewable and Sustainable Energy Reviews*, 168, 112765, <https://doi.org/10.1016/j.rser.2022.112765>, 2022.

930 Simpson, S. L., Batley, G. E.: Sediment quality assessment: a practical guide, CSIRO Publishing, ISBN 978-1-486-30384-7, 2016.

Singleton, H.: Ambient Water Quality Guidelines (Criteria) for Turbidity, Suspended and Benthic Sediments: Overview Report, British Columbia Ministry of Water, Land, and Air Protection. https://www2.gov.bc.ca/assets/gov/environment/air-land-water/water/waterquality/water-quality-guidelines/approved-wqgs/bc_env_turbidity_waterqualityguideline_overview.pdf, 2021.

935 Solan, M., Ward, E. R., White, E. L., Hibberd, E. E., Cassidy, C., Schuster, J. M., Hale, R., Godbold, J. A.: Worldwide measurements of bioturbation intensity, ventilation rate, and the mixing depth of marine sediments, *Sci. Data*, 6, 1-6, <https://doi.org/10.1038/s41597-019-0069-7>, 2019.

Speybroeck, J., Bonte, D., Courtens, W., Gheskiere, T., Grootaert, P., Maelfait, J. P., Mathys, M., Provoost, S., Sabbe, K., Stienen, E. W.: Beach nourishment: an ecologically sound coastal defence alternative? A review, *Aquat. Conserv.: Mar. Freshw. Ecosyst.*, 16, 419-435, <https://doi.org/10.1002/aqc.733>, 2006.

940 Sreekrishnavilasam, A., King, S., Santagata, M.: Characterization of fresh and landfilled cement kiln dust for reuse in construction applications, *Engineering Geology*, 85, 165-173, <https://doi.org/10.1016/j.enggeo.2005.09.036>, 2006.

Strydom, C., Roode, Q., Potgieter, J.: Thermogravimetric and X-ray powder diffraction analysis of precipitator dust from a rotating lime kiln, *Cem. Concr. Res.*, 26, 1269-1276, [https://doi.org/10.1016/0008-8846\(96\)00096-8](https://doi.org/10.1016/0008-8846(96)00096-8), 1996.

945 Suitner, N., Faucher, G., Lim, C., Schneider, J., Moras, C. A., Riebesell, U., Hartmann, J.: Ocean alkalinity enhancement approaches and the predictability of runaway precipitation processes: results of an experimental study to determine critical alkalinity ranges for safe and sustainable application scenarios, *Biogeosciences*, 21, 4587-4604, <https://doi.org/10.5194/bg-21-4587-2024>, 2024.

Sulpis, O., Jeansson, E., Dinauer, A., Lauvset, S. K., Middelburg, J. J.: Calcium carbonate dissolution patterns in the ocean, *Nat. Geosci.*, 14, 423-428, <https://doi.org/10.1038/s41561-021-00743-y>, 2021.

950 Tulcan, R. X. S., Ouyang, W., Lin, C., He, M., Wang, B.: Vanadium pollution and health risks in marine ecosystems: Anthropogenic sources over natural contributions, *Water Research*, 207, 117838, <https://doi.org/10.1016/j.watres.2021.117838>, 2021.

USGS: Lime Statistics and Information. <https://pubs.usgs.gov/periodicals/mcs2025/mcs2025-lime.pdf>, Last access 11 April 2025, 2025.

955 Varliero, S., Buono, A., Caserini, S., Raos, G., Macchi, P.: Chemical Aspect of Ocean Liming for CO₂ Removal: Dissolution Kinetics of Calcium Hydroxide in Seawater, *ACS Engineering Au*, 4, 422-431, <https://doi.org/10.1021/acsengineeringau.4c00008>, 2024.

Xu, P., Reinhard, C. T.: Evaluating the carbon capture potential of industrial waste as a feedstock for enhanced weathering, *Environ. Res. Lett.*, 20, 044013, <https://doi.org/10.1088/1748-9326/adc020>, 2025.

960 Yang, A. J., Timmermans, M.-L.: Assessing the effective settling of mineral particles in the ocean with application to ocean-based carbon-dioxide removal, *Environ. Res. Lett.*, 19, 024035, <https://doi.org/10.1088/1748-9326/ad2236>, 2024.

