

# Temperature sensitivity of snow viscoplasticity: evidence from controlled creep experiments

Louis Védérine<sup>1,2,3</sup>, Marius Brun<sup>1,2,3,4</sup>, Mathis Bozon<sup>1,2,3</sup>, Benoit Laurent<sup>1,2,3</sup>, and Pascal Hagenmuller<sup>1,2,3</sup>

<sup>1</sup>Météo-France, CNRS, Centre d'Études de la Neige, 38000 Grenoble, France.

<sup>2</sup>Université Grenoble Alpes, 38000 Grenoble, France

<sup>3</sup>Université de Toulouse, Toulouse 31000, France

<sup>4</sup>Department of Physics, École Normale Supérieure de Lyon, 69364, Lyon, France

**Correspondence:** Louis Védérine (louis.vedrine@meteo.fr)

**Abstract.** Snow is a warm, porous material whose densification under its own weight is highly temperature-dependent. Despite decades of research, reported activation energies for snow viscoplasticity remain highly scattered, ranging from 40 to 600 kJ mol<sup>-1</sup>. We quantified the temperature dependence of snow viscoplasticity using in-tomograph creep experiments with a newly developed thermo-mechanical cell. This design allows accurate load and temperature control, micrometric displacement measurement, and microstructural evolution monitoring via X-ray tomography. To disentangle microstructural evolution and temperature effects on the compression rate, we used a state-of-the-art viscoplastic model. We conducted five experiments on centimetre-scale samples of decomposing and fragmented precipitation particles with initial densities ranging from 278 to 320 kg m<sup>-3</sup> under an applied stress of 1.25 kPa. Each experiment comprised five temperature steps from -6 to -18°C, each lasting one day, and resulted in a mean final vertical strain of 4%. We show that the viscoplastic response follows is consistent with a two-regime Arrhenius law, with apparent activation energies  $Q_h = 126 \pm 6$  kJ mol<sup>-1</sup> for temperatures above -13±1°C and  $Q_l = 51 \pm 18$  kJ mol<sup>-1</sup> below. This temperature sensitivity matches that reported for polycrystalline ice but is greater than that used in detailed snowpack models.

**KEYWORDS:** Snow mechanics; viscoplasticity; temperature; microstructure; settlement

## 1 Introduction

Snow is a porous material with a wide range of densities, from approximately 50 kg m<sup>-3</sup> for new snow to about 500 kg m<sup>-3</sup> at the end of the winter season in mid-latitude regions. On Earth, it exists close to its melting point, making it highly sensitive to temperature. Snow continuously undergoes metamorphism, including substantial compaction over time through viscoplastic deformation. This viscoplastic creep is strongly temperature dependent, varying by approximately two orders of magnitude between -45°C and 0°C (Yosida, 1955). Therefore, quantifying the temperature dependence of snow viscoplasticity is essential for accurately predicting snowpack evolution (Lehning et al., 2002; Vionnet et al., 2012; Simson et al., 2021), with direct implications for avalanche forecasting (Morin et al., 2020), hydrology (Barnett et al., 2008; DeBeer and Pomeroy, 2017), and palaeoclimatology (Barnola et al., 1987). Knowledge of this temperature sensitivity is also critical for extrapolating laboratory-derived densification laws (Brun et al., 1992; Védérine and Hagenmuller, 2025) to the wide range of

25 natural conditions encountered on Earth, from warm seasonal snow (Lejeune et al., 2019) to cold perennial snow with seasonal temperature variations of up to 40°C (Morris and Wingham, 2014).

Dry snow can be regarded as a two-phase material composed of sintered ice crystals and air (Bader, 1939). Its compaction results from the slow viscoplastic deformation of the ice skeleton and the associated reduction in pore volume (e.g., Yosida, 1955). Consequently, snow densification depends strongly on the spatial arrangement of ice crystals and on the mechanisms by which they deform. The temperature dependence of snow compaction thus stems from these underlying mechanisms. Védrine et al. (2024) showed that ice in snow does not deform in the same way as polycrystalline ice because of pore accommodation, and that snow creep is mainly driven by basal glide. It therefore remains unclear whether the temperature sensitivity of snow viscoplasticity is the same as that of polycrystalline ice, which has been studied far more extensively than snow.

The viscoplasticity of isotropic ice (secondary creep) or snow is commonly described by a power law of the form:

$$\dot{\epsilon} = \dot{\epsilon}_0(T) \left( \frac{\sigma}{\sigma_0} \right)^n, \quad (1)$$

35 where  $\sigma_0$  is the reference stress,  $n$  is the stress exponent and  $\dot{\epsilon}_0(T)$  is the temperature-dependent prefactor. For isotropic polycrystalline ice, this relation corresponds to Glen's law (Glen, 1955). The temperature dependence of  $\dot{\epsilon}_0(T)$  is generally assumed to follow an Arrhenius relationship (e.g., Yosida, 1955; Glen, 1955):


$$\dot{\epsilon}_0(T) \propto \exp \left( -\frac{Q}{RT} \right), \quad (2)$$

40 where  $Q$  is the activation energy,  $R = 8.3 \text{ J mol}^{-1} \text{ K}^{-1}$  is the universal gas constant, and  $T$  is the absolute temperature in kelvin. Quantifying the temperature sensitivity of creep, therefore, primarily amounts to determining the activation energy  $Q$ .

Numerous studies have investigated the activation energy  $Q$  associated with the creep of polycrystalline ice, reporting values ranging from 45 to 167 kJ mol<sup>-1</sup> (e.g., Glen, 1955; Mellor and Smith, 1966; Mellor and Testa, 1969a; Ramseier, 1975) (Fig. 1). An increase in activation energy at warmer temperatures, typically above -10°C, is commonly reported (e.g., Budd and Jacka, 1989; Morgan, 1991). For example, Mellor and Testa (1969a) identified an activation energy of 68.8 kJ mol<sup>-1</sup> between -60°C and -10°C, but did not identify a consistent Arrhenius law above -10°C, noting a stronger temperature dependence in this warmer range. Similarly, Kirchner et al. (2001) reported  $Q = 120 \text{ kJ mol}^{-1}$  above -8°C and  $Q = 78 \text{ kJ mol}^{-1}$  below this threshold. Other studies have reported similar trends, with activation energies of approximately 60 kJ mol<sup>-1</sup> below -10°C and 130 kJ mol<sup>-1</sup> above (Steinemann, 1954; Glen, 1955; Barnes et al., 1971).

Several experimental studies have also investigated the influence of temperature on snow creep (Bucher, 1948; Yosida, 1955; Kirchner et al., 2001; Scapozza and Bartelt, 2003; Delmas, 2013; Schleef et al., 2014b; Li et al., 2024; Horlings et al., 2025) (Fig. 1). Yosida (1955) reported activation energies of 87 and 99 kJ mol<sup>-1</sup> for densities of 156 kg m<sup>-3</sup> and 230 kg m<sup>-3</sup>, respectively, independent of temperature over the range from -20°C to 0°C. Kirchner et al. (2001) derived a transition in the activation energy near -6°C, with  $Q = 56 \pm 2.6 \text{ kJ mol}^{-1}$  below this threshold and  $Q = 260.6 \pm 38.6 \text{ kJ mol}^{-1}$  above. They associated this transition with that observed for polycrystalline ice (see above). Scapozza and Bartelt (2003) reported activation energies ranging from 66 to 426 kJ mol<sup>-1</sup>, depending on temperature and sample density. They noted a general increase in  $Q$  with both temperature and porosity. Using a similar protocol, Delmas (2013) performed

creep tests at two temperatures ( $-5^{\circ}\text{C}$  and  $-15^{\circ}\text{C}$ ) on two grain types (rounded grains, RG; faceted crystals, FC), and reported activation energies of  $341.5$  and  $602\text{ kJ mol}^{-1}$ . Schleef et al. (2014b) investigated temperature sensitivity during compaction experiments monitored by ~~X-ray~~X-ray microtomography and obtained an activation energy of  $54\text{ kJ mol}^{-1}$ . More recently, Li et al. (2024) determined activation energies from mechanical compression tests performed on firm at  $-5^{\circ}\text{C}$ ,  $-18^{\circ}\text{C}$ , and  $-30^{\circ}\text{C}$ . They reported activation energies of  $61.4$ ,  $87.3$ , and  $102.8\text{ kJ mol}^{-1}$  for densities of  $596\text{ kg m}^{-3}$ ,  $679\text{ kg m}^{-3}$ , and  $779\text{ kg m}^{-3}$ , respectively.

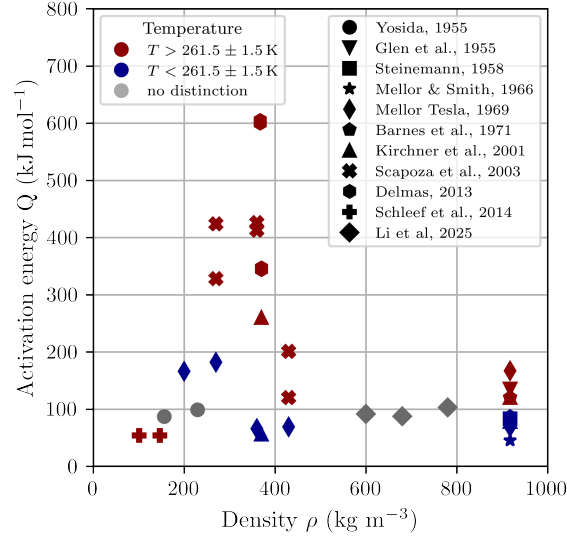

**Figure 1.** Reported activation energies of the viscoplastic behaviour of the snow-firm-ice continuum as a function of density and temperature regime.


Overall, two well-defined temperature regimes are consistently observed in polycrystalline ice. In contrast, activation energies in snow show substantial variability. This variability may primarily arise from the experimental protocols. Indeed, accurately characterising the temperature dependence of viscoplastic behaviour requires experiments in which temperature is the only varying parameter. In previous studies, different samples with similar characteristics were tested at different temperatures, with thermal regulation applied only at the cold-room scale. However, in practice, reproducing identical snow samples in terms of density and microstructure is extremely challenging. Védérine and Hagenmuller (2025) demonstrated that even a 5 % increase in density between two samples—which is common in practice (e.g. for firm Li et al., 2024)—can lead to a relative difference in strain rate of approximately 50 %. Such a change in strain rate corresponds to a temperature difference of about  $4^{\circ}\text{C}$ , assuming an activation energy of  $Q = 69.3\text{ kJ mol}^{-1}$   $Q = 68.8\text{ kJ mol}^{-1}$ . In addition, typical temperature fluctuations in cold rooms, caused by heat exchanger defrost cycles and heating from X-ray sources, reach up to  $\pm 0.6^{\circ}\text{C}$  and  $\pm 0.5^{\circ}\text{C}$ , respec-

tively (Schleef et al., 2014b). These fluctuations further contribute to substantial uncertainty in the experimental quantification of the temperature dependence of snow viscoplasticity.

75 To address these limitations, we propose a new experimental protocol designed to tightly control both temperature and microstructure in order to quantify the temperature sensitivity of snow viscoplasticity. Quantifying the influence of temperature on strain rate requires measurable deformation, which induces densification and viscoplastic hardening. We developed a thermo-mechanical cell that enables precise control of sample temperature and allows temperature to be varied during creep tests. Sample deformation is monitored using laser displacement measurements, which provide sufficient accuracy without  
80 requiring large strains, thereby limiting microstructural evolution. Microstructural changes are further monitored using X-ray tomography. In addition, geometric hardening during the experiments is accounted for in the identification procedure using a state-of-the-art snow creep model (Védrine and Hagenmuller, 2025). This approach allows us to isolate the temperature dependence of the viscoplastic response from microstructural effects. Applying this protocol to five samples subjected to five temperature steps, we derive a two-regime Arrhenius law relationship between strain rate and temperature. Finally, we compare  
85 the resulting parametrisation with settlement laws implemented in snowpack models and discuss the implications for snowpack modelling.

## 2 Materials and methods

### 2.1 Experimental setup of the sample environment

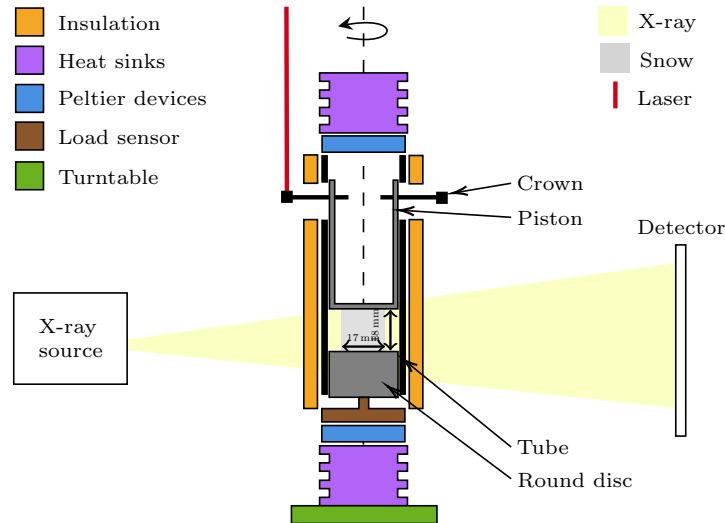

**Figure 2.** Scheme of the experimental setup.

The thermo-mechanical cell was designed for micro-CT measurements of snow settlement under controlled load and temperature conditions. To this end, we drew inspiration from the *Snowbreeder 5* cell developed at the WSL-SLF (Wiese and Schneebeili, 2017) and adapted the setup of Dick et al. (2026) for settlement analysis. In particular, we controlled the sample temperature independently of the cold-room temperature, and we monitored the applied load to ensure that it remained constant throughout the tests.

The thermo-mechanical cell (Fig. 2) consists of an aluminium cylindrical tube with a diameter of 20 mm and a height of 90 mm. The wall thickness of the aluminium cell (0.5 mm) was chosen to allow X-rays to penetrate the cell and image the sample. A piston transmits the load to the sample. The mass of the piston and crown alone is  $m = 28.79$  g. Because the piston is hollow, additional mass can be added to increase the applied load.

Two Peltier thermoelectric modules (TEC-14,7-3,9-34,0-70-30/0-R from Arctic TEC), referred to simply as Peltier units, are placed at the lower and upper ends of the cell, providing precise control of the sample temperature (Fig. 2). The Peltier modules are driven by a controller unit (TEC-1161-4A from MEERSTETTER). These Peltier modules ensure that temperature differences within the cell remain on the order of  $10^{-3}$  K and provide an absolute temperature accuracy better than  $\pm 0.5$  K. Heat sinks and fans dissipate the heat produced by the Peltier units. The cell can be operated at temperatures up to  $\pm 10$  K relative to the ambient temperature. A thick insulating ~~Styrofoam~~styrofoam ring is added around the cell to ensure isothermal conditions. The Peltier units maintain temperature control during the experiment and prevent sample heating during scans.

Temperature is measured at each Peltier module at 0.5 Hz.

Two additional measurements are integrated into the system:

- *Sample top displacement*: A laser sensor (OM30-P0100.HV.YUN from Baumer) mounted on the supporting frame measures the distance to a crown fixed to the piston applying the load to the snow sample. It is used to track the vertical displacement of the top of the snow sample. The crown design enables displacement tracking regardless of the cell orientation. The laser signal is transmitted via a 16-bit ADC acquisition card (MCCUSB234 from Digilent) to a computer located outside the cold room. The displacement data are recorded at a frequency of 0.2 Hz, with a measurement range of 15 mm and a resolution of  $1 \mu\text{m}$ . The vertical strain  $\varepsilon_{zz}$  is defined as:

$$\varepsilon_{zz} = \frac{h - h_i}{L} \quad (3)$$

where  $L$  is the sample height, and  $h$  and  $h_i$  are the current and initial laser distances, respectively.

- *Force measurement*: A miniature bottom load cell (LLB130 from FUTEK) is placed beneath the snow sample through a washer, allowing the force transmitted to the sample to be measured. It is used to ensure that a constant force is applied and to verify that the piston moves without frictional resistance. A driver (SM18-gage) amplifies the signal from the strain gauges, which is then sent to the same acquisition card as the laser displacement measurement. This sensor has a resolution of 0.1 g and, like the laser measurement, is recorded at a frequency of 0.2 Hz.

Because the cell rotates during tomographic acquisition, data are transmitted via a slip ring.

2.2 X-ray tomography

The evolution of the snow microstructure was monitored during the compression tests using an X-ray tomograph (DeskTom130, RX Solutions). Every 8 hours, a series of scans was acquired; each series consisted of one high-resolution scan (HR) and one low-resolution scan (LR). The HR scans captured an inner region (diameter of 10 mm and height of 10 mm) with a nominal voxel size of 11.23  $\mu\text{m}$ , and the LR scans covered the whole sample at a nominal voxel size of 27.44  $\mu\text{m}$ . The scan settings for the different modalities are summarized in Table 1. The greyscale attenuation images were segmented into pore space and a continuous ice matrix (Hagenmuller et al., 2013).

Table 1. Acquisition parameters for tomographic imaging.

|                 |                                                                      | LR    | HR    |
|-----------------|----------------------------------------------------------------------|-------|-------|
| X-ray source    | Voltage (kV)                                                         | 80    | 60    |
|                 | Current ( $\mu\text{A}$ )                                            | 200   | 132   |
| Detector        | Averaged frames                                                      | 3     | 2     |
|                 | Frame rate ( $\text{s}^{-1}$ )                                       | 5     | 1     |
|                 | Number of projections                                                | 1000  | 1440  |
| Scan trajectory | <del>Voxel-nominal</del> <u>Nominal voxel</u> size ( $\mu\text{m}$ ) | 27.44 | 11.23 |

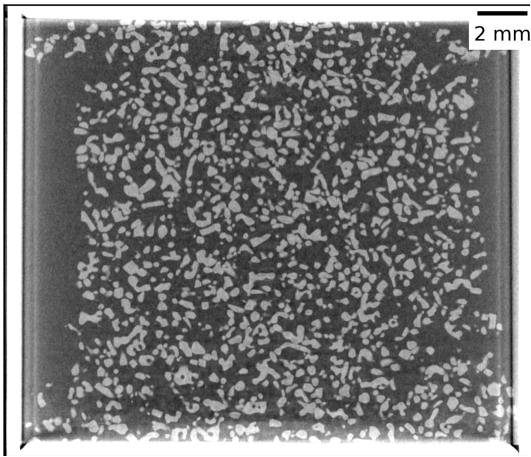


Figure 3. Vertical slice of the snow sample imaged in the thermo-mechanical cell using LR scans. The image is shown in grayscale.

To assess the consistency between the bulk deformation measured by laser and the deformation within the sample, axial strain was computed using Digital Volume Correlation (DVC) (Stamati et al., 2020) applied to low-resolution (LR) images. The analysis was conducted over a single region of interest (ROI) with dimensions of  $10.3 \times 10.3 \times 10.3 \text{ mm}^3$ .

## 2.3 Experimental protocol

Snow samples were prepared as follows. Natural snow was collected in the field and stored in styrofoam boxes in a cold room at a constant temperature of  $-20^{\circ}\text{C}$  for several months, where it evolved into Decomposing and Fragmented precipitation particles (DF) through isothermal metamorphism. The snow particles were then sieved into a sample holder using a 1.6 mm sieve. The sample holder was cylindrical, with a diameter of 17 mm and a height of 17 mm, and was used to mould the snow samples. The diameter of the sample holder, 17 mm, was smaller than the 20 mm diameter of the cell tube, thereby creating unconfined conditions during the creep test and avoiding uncontrolled sidewall friction (Fig. 3). The samples were left to sinter for at least two weeks at  $-18^{\circ}\text{C}$  before being placed into the cell tube.

We conducted creep tests with stepwise temperature variations to determine the temperature sensitivity of snow viscoplasticity. Temperature control was achieved using the Peltier modules. A stress of 1.25 kPa was applied to the snow sample, corresponding to the overburden stress exerted by a 0.45 m thick snow layer at the density used in the experiment. To limit lateral heat transfer, the cold room temperature was set to the average temperature of the experimental series. Each experiment lasted 5 days and consisted of 5 temperature steps, each lasting 1 day, with temperatures ranging from  $-6$  to  $-18^{\circ}\text{C}$  in  $3^{\circ}\text{C}$  increments. The first 8 hours of each experiment, corresponding to sample stabilisation (i.e., densification of the layer at the sample-piston interface and the establishment of steady-state conditions), were excluded from the analysis. This protocol was repeated on five snow samples with initial densities ranging from 278 to  $320\text{ kg m}^{-3}$ <sup>1</sup>.

## 2.4 Snow viscoplastic model

The temporal evolution of the thickness  $e$  of a layer subjected to an overburden stress  $\sigma$  is related to the vertical strain rate through  $\dot{\epsilon}_{zz} = \dot{e}/e$  (taken to be positive in compression). In its generic form (Védrine and Hagenmuller, 2025), the densification law can be expressed as a function of the solid fraction  $\Phi = \rho/\rho_s$ , where  $\rho$  is the snow density and  $\rho_s = 917.15\text{ kg m}^{-3}$  is the density of ice:

$$\dot{\epsilon}_{zz}(T, \sigma) = \dot{\epsilon}_0(T) f(\sigma, \Phi), \quad f(\sigma, \Phi) = S_\nu \left( \frac{\sigma}{\sigma_{0,s} \Phi^m} \right)^n, \quad (4)$$

where  $S_\nu$  is the boundary condition prefactor, equal to 1 here for free boundary conditions,  $n$  is the stress exponent,  $m$  is the solid-fraction exponent characterising the microstructure, and  $\dot{\epsilon}_0(T)$  is the temperature-dependent prefactor. The latter is set to  $1\text{ s}^{-1}$  at the reference temperature  $T_0 = 263.15\text{ K}$ , for which the reference stress of ice is  $\sigma_{0,s} = 272\text{ MPa}$  (Jacka and Maccagnan, 1984). The stress exponent was set to  $n = 2.2$  and the solid-fraction exponent to  $m = 4$ , based on experimental and modelling studies (Scapozza and Bartelt, 2003; Schleef et al., 2014a; Védrine and Hagenmuller, 2025).


The objective of the present study is to determine the temperature dependence of the prefactor  $\dot{\epsilon}_0(T)$ . To quantify the influence of temperature on strain rate, the sample must undergo measurable deformation; this inevitably induces densification and thus geometric hardening, i.e., an increase in the reference stress  $\sigma_0 = \sigma_{0,s} \Phi^m$ . As a result, even at constant temperature,

<sup>1</sup>Note that, due to a technical issue, [Samples](#) 1 and 3 do not include a temperature step at  $-18^{\circ}\text{C}$ .

the strain rate decreases during the test. To minimise geometric hardening, we apply a low overburden stress so that the microstructure remains only weakly deformed. Moreover, we use Eq. (4) to isolate the temperature prefactor  $\dot{\epsilon}_0(T)$  by dividing the measured vertical strain rate  $\dot{\epsilon}_{zz}$  by its mechanical component  $f(\sigma, \Phi)$ .

### 3 Results

#### 3.1 Exemplary creep test

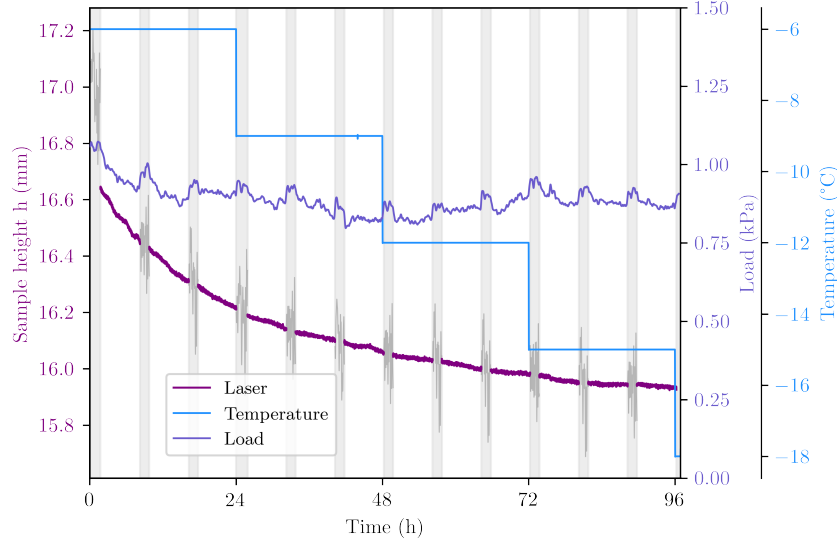


**Figure 4.** Temporal evolution of the sample height, the applied load, and the sample temperature for sample 1. Grey shaded areas indicate time intervals affected by X-ray tomographic scans.

We first show the results obtained on one sample (sample 1). The corresponding data for the other experimental series are provided in Appendix A1.

Figure 4 shows the temporal evolution of the sample height, applied load, and temperature. At each temperature step, an apparent change in the slope of the displacement curve is observed, reflecting a change in the strain rate. In addition, small displacement jumps occur at temperature transitions and are attributed to thermal expansion of the experimental cell. These jumps do not affect the subsequent analysis, as their magnitude is small and the analysis focuses on the derivative of the displacement (strain rate) obtained outside the scan periods. Because the applied load is small compared with the sensor measurement range (0–1 kg), the transmitted signal is weak and highly sensitive to the contact quality in the slip ring as well as to external perturbations. Nevertheless, we observe that the applied load remains nearly constant throughout the experiment, varying by less than 0.17 kPa, and is close to the nominal imposed load, which indicates that parasitic friction from the piston

or the washer is negligible. In the remainder of this study, the load applied to the sample is therefore assumed to be constant at 1.25 kPa (mass of the piston and crown divided by the sample cross-section).

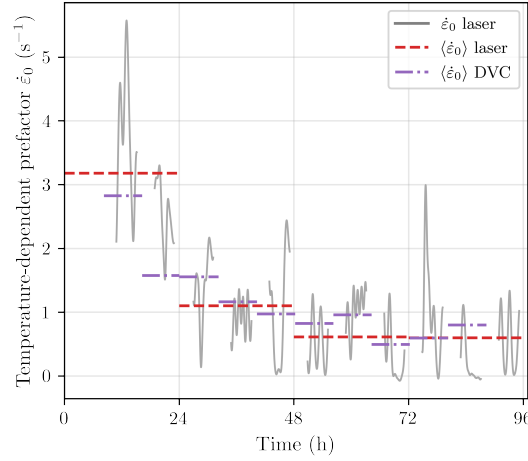


**Figure 5.** Temporal evolution of the strain rate prefactor  $\dot{\epsilon}_0$ , computed from laser displacement measurements and digital volume correlation (DVC).


To quantify the observed slope changes, the effects of densification and geometric hardening are first removed to isolate the temperature dependence of the deformation rate. Starting from the measured strain rate  $\dot{\epsilon}$ , the temperature-dependent prefactor  $\dot{\epsilon}_0$  is computed and shown in Fig. 5. Despite significant fluctuations associated with experimental measurement noise, a systematic decrease in  $\dot{\epsilon}_0$  is observed at each temperature step. Figures 5 and A4 show the temporal evolution of the strain rate prefactor  $\dot{\epsilon}_0$ , computed from both laser displacement measurements and DVC for all samples. The measurements are consistent with each other, indicating that the laser-based deformation accurately reflects the sample response despite the sample heterogeneities.

For each temperature plateau, the mean value of  $\dot{\epsilon}_0$  is calculated and plotted as a function of inverse temperature  $1/T$  (Fig. 6). On a logarithmic scale,  $\dot{\epsilon}_0$  exhibits a linear dependence on  $1/T$ , consistent with an Arrhenius-type relationship, for which the slope equals  $-Q/R$ . The [apparent](#) activation energy of sample 1 is thus estimated to be  $Q_{S1} = 134 \pm 30 \text{ kJ mol}^{-1}$ . Uncertainties here represent one standard deviation (68% confidence interval) derived from the covariance matrix, assuming Gaussian uncertainties in both temperature and strain rate.

We can compare the densification model (Eq. 4) with the measured vertical deformations using the previously calculated [apparent](#) activation energy (Fig. 7). If temperature variations are neglected and the temperature is assumed to remain constant at its initial value, the deformation decreases more slowly and deviates from the experimental measurements. This comparison shows that the slowdown in deformation rate is primarily due to the decrease in temperature, as geometric hardening alone cannot account for the observed behaviour.

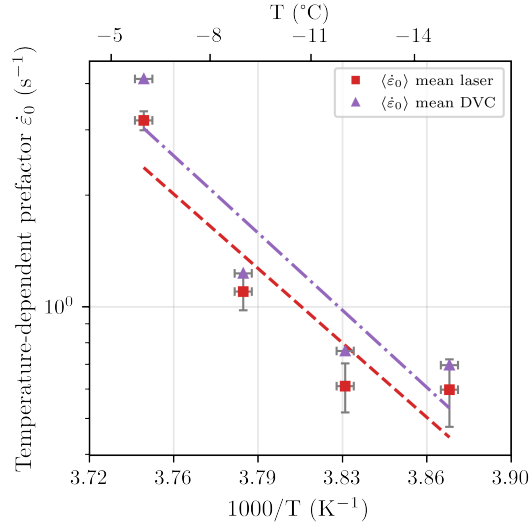


**Figure 6.** Mean values of the strain rate prefactor  $\dot{\epsilon}_0$  as a function of temperature. The strain rate was computed from laser displacement measurements and digital volume correlation (DVC). Uncertainties in strain rate correspond to the standard deviation of the laser-derived measurements around the mean value shown in Fig. 5. Temperature uncertainty was estimated at  $\pm 0.5^\circ\text{C}$ .

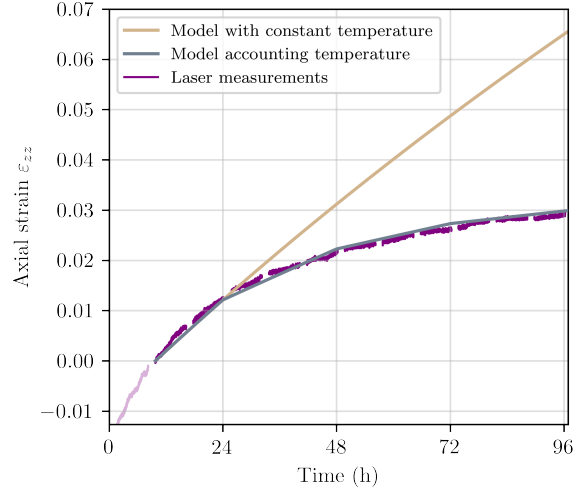

**Figure 7.** Strain versus time measured by the laser and predicted with the model Eq. 4 considering the measured temperature and a constant temperature equal to the initial temperature. The offset of the temperature prefactor is calibrated on the first temperature step. The first 8 hours (grey area) are excluded from the analysis.

In this section, we analyse the full set of experimental results. At a given temperature, the temperature prefactor  $\dot{\epsilon}_0$  varies by approximately 40% across the different experimental samples (Fig. A2). This dispersion is likely due to differences in second-order microstructural features that the mechanical model does not explicitly capture. In particular, samples 3 and 5 consistently exhibit higher values of  $\dot{\epsilon}_0$  across the entire temperature range, whereas samples 1 and 4 show systematically lower values. Since our focus is on the temperature dependence, each sample series was first corrected for these second-order microstructural effects by subtracting the mean offset. Figure 8 shows the corrected scaled strain-rate prefactor as a function of inverse temperature for each sample. The data collapse onto a single master curve, indicating that all samples share a similar temperature dependence. We therefore use the complete dataset to characterise the viscoplastic response, accounting for the associated uncertainties.

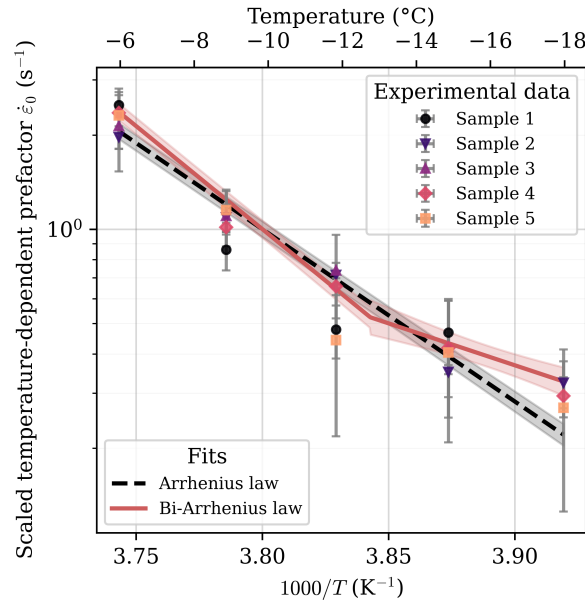


**Figure 8.** Scaled strain rate prefactor  $\dot{\epsilon}_0$  as a function of inverse temperature for all studied samples, corrected for second-order microstructural effects.

Fitting a single Arrhenius law to all data yields an apparent activation energy of  $Q = 105 \pm 6 \text{ kJ mol}^{-1}$ . However, a simple Arrhenius formulation fails to capture the change in slope observed around  $-12^\circ\text{C}$ , particularly for series 4 and 5. By fitting a two-regime Arrhenius law (Eq. 5) to the data, two apparent activation energies are identified:  $Q_h = 126 \pm 6 \text{ kJ mol}^{-1}$  and  $Q_l = 51 \pm 18 \text{ kJ mol}^{-1}$ , with a transition temperature of  $T_c = -13 \pm 1^\circ\text{C}$ . The apparent activation energy associated with the low-temperature regime is subject to substantial uncertainty, owing to the large experimental scatter at low temperatures, where deformation rates are low. The two-regime Arrhenius law is statistically preferred according to the Akaike Information Criterion ( $\delta AIC = -8$   $\Delta AIC = -8$ ), indicating that the data support a transition between two temperature-dependent regimes.

$$\dot{\varepsilon}_0(T) = \begin{cases} \exp\left[-\frac{Q_h}{R}\left(\frac{1}{T} - \frac{1}{T_0}\right)\right], & T > T_c, \\ \exp\left[-\frac{Q_l}{R}\left(\frac{1}{T} - \frac{1}{T_0}\right) + \frac{Q_l - Q_h}{R}\left(\frac{1}{T_c} - \frac{1}{T_0}\right)\right], & T \leq T_c. \end{cases} \quad (5)$$

### 3.3 Analysis of the evolution of microstructural properties and spatial heterogeneity

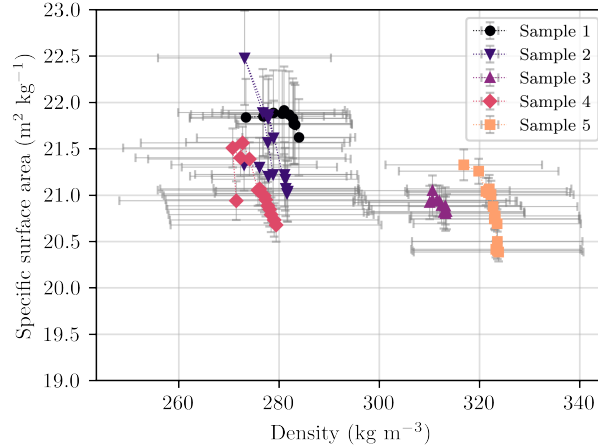

**Figure 9.** Evolution of specific surface area and density during the tests. Error bars represent the spatial heterogeneity within one sample (standard deviation between horizontal slices).

Tomographic scans were performed every 8 h during the tests to monitor the evolution of the microstructure. Figure 9 shows the evolution of the density and specific surface area (SSA) calculated over a  $5.6 \times 5.6 \times 5.6 \text{ mm}^3$  volume. An increase in density was observed, whereas the SSA showed only a slight decrease. The microstructural variations are minimal during the experiment, with relative changes in density below 4% (less than  $10 \text{ kg m}^{-3}$ ) and in SSA below 7% (less than  $1.4 \text{ m}^2 \text{ kg}^{-1}$ ). The observed variation of the SSA is within the margin of error of tomographic image analysis (e.g., Hagenmuller et al., 2016). It confirms that the microstructure remained essentially unchanged during the compression tests, indicating a minimal effect on the mechanical properties.


## 4 Discussion

### 4.1 Robust identification of the temperature sensitivity of snow viscoplasticity

In this study, we isolated the effect of temperature on the viscoplastic response by (i) using the same snow sample throughout each test, (ii) limiting microstructural variations across temperature steps, and (iii) accounting for geometric hardening using the model proposed by Védérine and Hagenmuller (2025). This procedure enables robust identification of the temperature sensitivity

of snow viscoplasticity and disentangles it from microstructural effects. We discuss here how the choice of geometric hardening model and sample heterogeneity may affect the results.

Figure 10 illustrates the sensitivity of the identified apparent activation energy to the parameters of the constitutive law. If the apparent activation energy were estimated without accounting for geometric hardening ( $n = 0$  and  $m = 0$ ), a value of  $Q = 116 \pm 7 \text{ kJ mol}^{-1}$  would be obtained, corresponding to a deviation of approximately 10%. This deviation remains relatively small because microstructural changes are intentionally limited. Nevertheless, it highlights the importance of decoupling the effects of geometric hardening and temperature. Furthermore, within the range of  $n$  and  $m$  typically reported for snow (Scapozza and Bartelt, 2003; Schleef et al., 2014a; Védrine et al., 2025), the sensitivity of  $Q$  to these parameters is low, resulting in a maximum deviation of 3%.

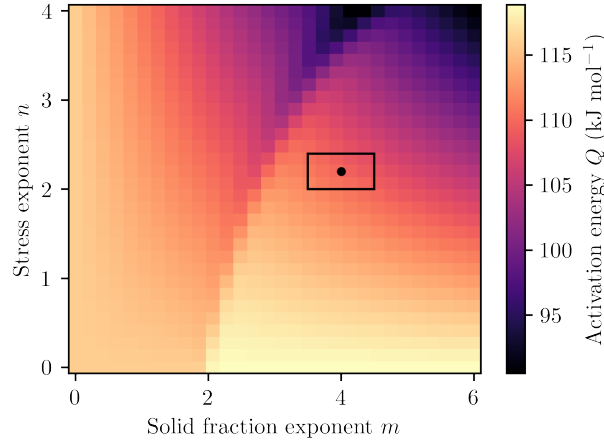

**Figure 10.** Activation-Apparent activation energy estimated from the experimental measurements as a function of the model parameters  $m$  and  $n$ . The rectangle indicates the range of physically meaningful parameters ( $m = 4 \pm 1$  and  $n = 2.2 \pm 0.2$ ).

In our model, each sample was assumed homogeneous and characterised by its mean density. However, the tomographic scans reveal spatial heterogeneities within the samples (Fig. 9), which can lead to stress concentrations and higher strain rates (Fig. 8). Differences in microstructural heterogeneity between samples, as well as second-order microstructural parameters (Fig. 9), affect the mean strain-rate but not its temperature dependence. These effects can therefore be readily accounted for, allowing the influence of temperature to be isolated (Fig. 8). These results clearly demonstrate the necessity of using the same snow sample to identify the temperature sensitivity of snow viscoplasticity. If different samples are used at each temperature step, microstructural effects can no longer be disentangled from temperature dependence (e.g., Scapozza and Bartelt, 2003; Delmas, 2013; Li et al., 2024).

## 4.2 Comparison of the temperature dependence of snow viscoplasticity with previous studies

Our results ( $Q_h = 126 \pm 6 \text{ kJ mol}^{-1}$  above  $T_c = -13 \pm 1^\circ\text{C}$  and  $Q_l = 51 \pm 18 \text{ kJ mol}^{-1}$  below) fall within the wide range of  
245 activation energies reported in the literature (Fig. 1) and confirm previous reports of two temperature regimes in snow (Kirchner  
et al., 2001; Scapozza and Bartelt, 2003). For example, Kirchner et al. (2001) observed an ~~activation-energy~~ activation-energy  
transition near  $-6^\circ\text{C}$ , with  $Q = 56 \text{ kJ mol}^{-1}$  below this threshold and  $Q = 260 \text{ kJ mol}^{-1}$  above. Scapozza and Bartelt (2003)  
reported an increase in apparent activation energy from approximately  $69 \text{ kJ mol}^{-1}$  between  $-18^\circ\text{C}$  and  $-11^\circ\text{C}$  to about  
 $120 \text{ kJ mol}^{-1}$  between  $-12^\circ\text{C}$  and  $-5^\circ\text{C}$  for snow with a density of  $430 \text{ kg m}^{-3}$ . However, our apparent activation energy  
250 estimates are substantially higher than those reported by Schleef et al. (2014b), who found an apparent activation energy of  
 $Q = 54 \text{ kJ mol}^{-1}$  between  $-13^\circ\text{C}$  and  $-3^\circ\text{C}$ . The very high apparent activation energy values reported by Scapozza and Bartelt  
(2003) and Delmas (2013) are likely due to microstructural variability, because only two temperatures were used to determine  
the apparent activation energy, which makes the estimated activation energy highly sensitive to differences in microstructure  
between samples.

## 255 4.3 A signature of microscale deformation mechanisms?

At first glance, the viscoplastic response of snow exhibits a temperature sensitivity similar to that reported for polycrystalline  
ice. In particular, the bilinear temperature dependence inferred from our data yields apparent activation energies consistent  
with commonly reported values for ice creep. The high-temperature regime is characterised by an apparent activation energy  
of  $Q_h = 126 \pm 6 \text{ kJ mol}^{-1}$ , in good agreement with values reported for polycrystalline ice, typically around  $130 \text{ kJ mol}^{-1}$   
260 (e.g., Glen, 1955; Steinemann, 1954; Mellor and Testa, 1969b; Barnes et al., 1971). At lower temperatures, a second regime is  
observed, with  $Q_l = 51 \pm 18 \text{ kJ mol}^{-1}$ , close to the commonly used value of  ~~$69.1 \text{ kJ mol}^{-1}$~~   $68.8 \text{ kJ mol}^{-1}$  for polycrystalline  
ice below  $-10^\circ\text{C}$  (Mellor and Testa, 1969b).

However, this apparent similarity should be interpreted with caution. Védérine et al. (2024) demonstrated that deformation  
in snow is primarily governed by basal slip in the ice matrix. This result suggests that the temperature sensitivity of snow  
viscoplasticity may primarily be inherited from that of basal slip. Yet, the temperature sensitivity of basal slip at the single-  
265 crystal scale remains poorly constrained. The apparent activation energy associated with basal slip has been reported to lie in the  
range  $60\text{--}90 \text{ kJ mol}^{-1}$  (Okada et al., 1999; Meyssonier et al., 2009) at low temperatures ( $\leq -10^\circ\text{C}$ ). Jones and Brunet (1978)  
investigated the temperature sensitivity of ice single crystals over the range  $-20^\circ\text{C}$  to  $-0.2^\circ\text{C}$  and reported an activation  
energy of  $Q = 70 \pm 2 \text{ kJ mol}^{-1}$ , independent of temperature. However, they observed that the stress exponent of basal slip,  $n_b$ ,  
270 varied linearly with temperature, decreasing from  $n_b = 2.07$  at  $-20^\circ\text{C}$  to  $n_b = 1.95$  at  $-0.2^\circ\text{C}$ . Such temperature dependence  
of the stress exponent is commonly reported in single crystals (e.g., Spitzig and Keh, 1970; Wollgramm et al., 2016).

In our model,  $n$  was fixed at 2.2. However, when this relative temperature dependence of the exponent is taken into ac-  
count ( ~~$n(T) = 2.15 - 7.26 \times 10^{-3} T$ , assuming the same temperature dependence as for the basal slip system~~), we obtain ~~,~~  
using the temperature dependence of  $n$  reported for basal slip and normalizing its value at  $-10^\circ\text{C}$  to recover the stress  
275 exponent of 2.2 used for snow, we obtained  $n(T) = 2.14 - 6 \times 10^{-3} T$ . This yields a single effective activation energy of

~~$Q = 73.5 \pm 6 \text{ kJ mol}^{-1}$~~   $Q = 78 \pm 6 \text{ kJ mol}^{-1}$  (Fig. A3) over the full temperature range. This value is consistent with the activation energy for basal slip determined by Jones and Brunet (1978). This result suggests that part of the apparent bilinear temperature dependence observed at the macroscopic scale may not reflect a true transition in activation energy, but rather the effect of a temperature-dependent stress exponent. These results highlight the need for dedicated experimental and modelling studies to better constrain the temperature dependence of the stress exponent and its contribution to the apparent macroscopic temperature sensitivity of snow viscoplasticity.


In this study, we did not investigate the behaviour of snow above  $-6^\circ\text{C}$ . Additional experiments in this temperature range could provide further insight into the active deformation mechanisms. In polycrystalline ice, a strongly nonlinear increase in creep rate as the melting point is approached has often been reported, with grain-boundary processes suggested as a possible explanation (e.g., Jacka and Maccagnan, 1984; Morgan, 1991). In contrast, Jones and Brunet (1978) showed that a system deforming predominantly by basal slip, as may be the case for snow (Védrine et al., 2024), does not necessarily exhibit such an acceleration of creep close to the melting point. Whether the temperature dependence observed here persists at higher temperatures or whether additional mechanisms lead to a nonlinear increase in creep rate therefore remains an open question.

#### 4.4 Impact on snowpack model

We compare our model with the parametrisation of Brun et al. (1992) (BR92), implemented in the detailed snowpack model *Crocus*, and with the parametrisation of Kojima (1975) (K75) for fresh snow, implemented in the snowpack model *Snowpack* (Lehning et al., 2002). In the BR92 parametrisation, the temperature dependence is expressed as  $e^{a_\eta(T_m - T)}$ , with  $a_\eta = 0.1 \text{ K}^{-1}$ , where  $T_m$  is the melting temperature and  $T$  is the snow temperature in  $^\circ\text{C}$ . This expression corresponds to the first-order expansion (close to  $0^\circ\text{C}$ ) of the Arrhenius law with ~~a-an apparent~~ activation energy of  $62 \text{ kJ mol}^{-1}$ , which is close to the value obtained for the low temperature regime but significantly lower than that obtained for the high temperature regime. In the K75 parametrisation, the effects of density and temperature are coupled through a power law in the expression of the compactive viscosity,  $\eta_{K75} = 7 \times 10^{-9} \rho^{(4.75 - T/40)}$ , where  $\rho$  is the snow density and  $T$  is the temperature in  $^\circ\text{C}$ .

Figure 11 shows the strain rate predicted by the detailed snowpack models and our parametrisation for different densities: 100, 200, and  $400 \text{ kg m}^{-3}$ . The BR92 model exhibits the weakest temperature sensitivity. At low densities, the K75 model is close to BR92, whereas at a density of  $400 \text{ kg m}^{-3}$  it shows a variation in strain rate between  $-30^\circ\text{C}$  and  $0^\circ\text{C}$  that is similar to our parametrisation. Finally, only our parametrisation exhibits two distinct temperature regimes.

Let us consider an isothermal snowpack 1 m thick with an initial density of  $\rho = 100 \text{ kg m}^{-3}$ . Figure 12 shows the evolution of snow height predicted by the different models at different temperatures. At low density and across all temperatures, our model predicts significantly higher strain rates than those obtained with the BR92 and K75 parametrisations, which yield nearly identical results in this regime. This behaviour is consistent with the commonly reported limitations of the BR92 formulation for fresh snow (Quéno et al., 2016). A clear sensitivity of snow compaction to temperature also emerges. After one hour, compared to a snowpack at  $-2^\circ\text{C}$ , the snow height at  $-20^\circ\text{C}$  decreases by ~~16%~~  $18\%$ ,  $21\%$ , and  $23\%$  for the BR92, K75, and our parametrisation, respectively. After one day, the influence of temperature and the differences in temperature sensitivity among the models become less pronounced. Overall, temperature mainly affects the characteristic timescale of

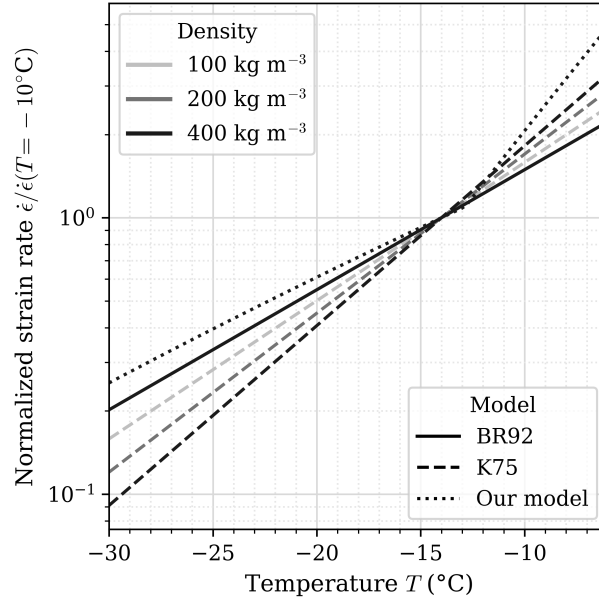


**Figure 11.** Normalized strain rate at  $-10^\circ\text{C}$  predicted by the model of Brun et al. (1992) (BR92), Kojima (1975) (K75), and our parametrisation incorporating the two-regime Arrhenius law (Eq. 5) as a function of temperature for different snow densities.

compaction and, to a lesser extent, the long-term snowpack height. For example, after seven days, an isothermal snowpack at  $-20^\circ\text{C}$  exhibits a snow height that is ~~25%~~42%~~20%~~34%, and ~~36%~~27% higher than that predicted at  ~~$-2^\circ$~~  $-6^\circ$  for the BR92, K75, and our parametrisation, respectively. These results underline that accurately capturing the temperature sensitivity of snow viscoplasticity is essential for predicting snowpack evolution.

## 5 Conclusion and perspectives

We developed a new thermo-mechanical cell that enables precise temperature control during in-tomograph snow-creep experiments and allows the sample temperature to be varied during creep tests. Using this device, we performed five series of experiments on samples with initial densities ranging from 278 to 320  $\text{kg m}^{-3}$ , each subjected to five temperature steps between  $-6^\circ\text{C}$  and  $-18^\circ\text{C}$ . By tracking the response of a single sample across successive temperature steps, we isolated the temperature dependence of snow viscoplasticity from microstructural variability by accounting for geometric hardening. ~~The~~Assuming a  
constant stress exponent with temperature, the measured response is well described by a two-regime Arrhenius law, with a ~~transition-characteristic~~ temperature of  $T_c = -13 \pm 1^\circ\text{C}$ , a high-temperature activation energy of  $Q_h = 126 \pm 6 \text{ kJ mol}^{-1}$ , and a low-temperature apparent activation energy of  $Q_l = 51 \pm 18 \text{ kJ mol}^{-1}$ . Although the densification measured during the tests intentionally remained small ( $<4\%$ ), neglecting geometric hardening would lead to an apparent activation energy of  $Q = 116 \text{ kJ mol}^{-1}$ , corresponding to an error of about 10%.

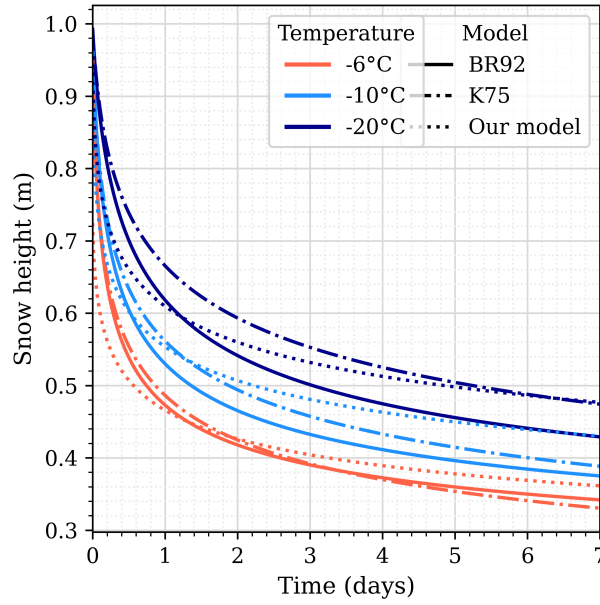

**Figure 12.** Evolution of snow height predicted using the parametrisations of Brun et al. (1992) (BR92), Kojima (1975) (K75), and our parametrisation incorporating the two-regime Arrhenius law (Eq. 5). Simulations are performed for a 1 m thick isothermal snowpack with an initial density of  $\rho = 100 \text{ kg m}^{-3}$ .

325 These results provide a robust basis for extending snow densification laws over a wide temperature range and show that accurately capturing temperature sensitivity is essential for predicting snowpack evolution. Assuming a constant stress exponent, the identified behaviour closely resembles that reported for polycrystalline ice. However, when the temperature dependence of the stress exponent is taken into account, following the trend reported for basal slip by Jones and Brunet (1978), the data can also be described by a single effective activation energy of  $Q = 73.5 \pm 6 \text{ kJ mol}^{-1}$   $Q = 78 \pm 6 \text{ kJ mol}^{-1}$ , consistent with  
 330 basal-slip creep. This suggests that part of the apparent bilinear temperature dependence observed at the macroscopic scale may reflect a temperature-dependent stress exponent rather than a true transition in activation energy. Dedicated experiments and modelling analyses are therefore still needed to better constrain the temperature dependence of the stress exponent and to clarify the respective roles of microscale deformation mechanisms in the macroscopic viscoplastic response of snow.

*Code and data availability.* All measurements are available at <https://doi.org/10.5281/zenodo.18824418> (Védrine et al., 2026), the tomographic data are available on request.  
 335

*Video supplement.* Videos of the compression experiments are available at <https://doi.org/10.5281/zenodo.18824418> (Védrine et al., 2026).

## **Appendix A: Results for other creep tests**

### **A1 Displacement and load**

Figure A1 shows the temporal evolution of the sample displacement and applied load for the Samples 2 to 5.


### 340 **A2 Raw strain rate prefactor for all series**

### **A3 Temporal evolution of the strain rate prefactor**


*Author contributions.* B.L., L.V. and P.H. developed the thermo-mechanical cell "CellCold". M.Brun, M.Bozon, L.V. and B.L. conducted the experiments and the data processing. L.V. and P.H. interpreted the results and wrote the paper with the input from all co-authors. P.H. and L.V. designed the study.

345 *Competing interests.* The authors declare that they have no conflict of interest.


*Acknowledgements.* CEN is part of LabEx OSUG@2020 (ANR-15-IDEX-02). The tomography apparatus (TomoCold) was funded by INSU-LEFE, Labex OSUG (Investissements d'avenir–ANR10 LABX56) and CNRM. The laser sensor was funded by Région Auvergne-Rhône-Alpes under the CPER MECASNOW program. The authors would like to thank the whole Col de Porte team for their warm welcome. We thank K. Fourteau and O. Dick for fruitful discussions.

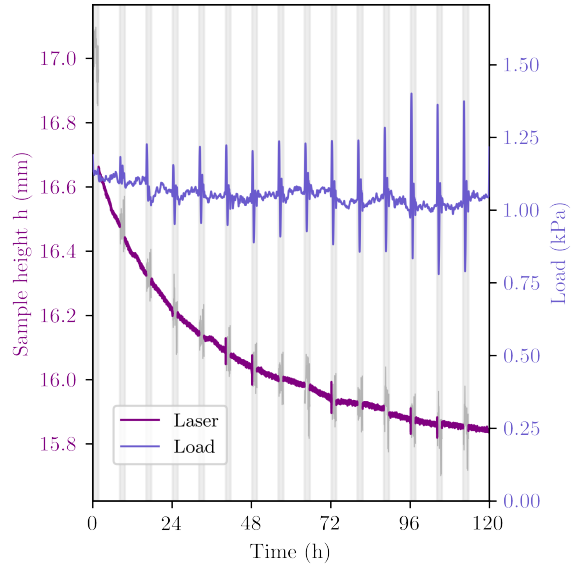


(a) Sample 2

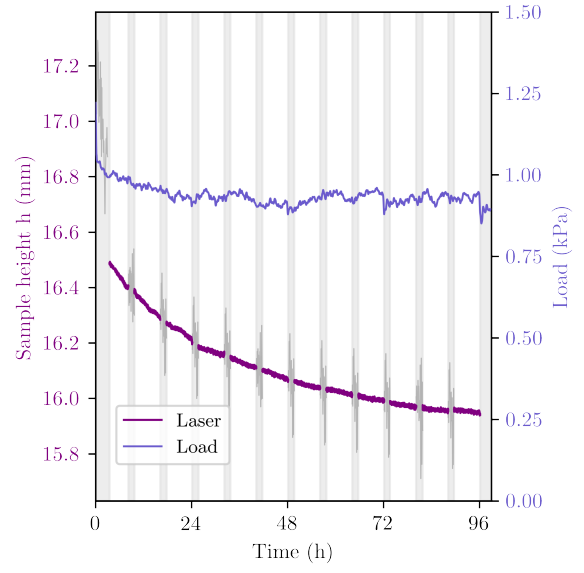

(b) Sample 3

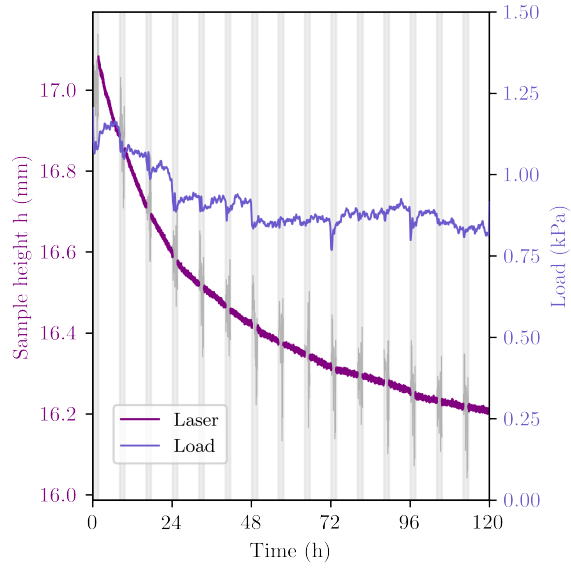


(c) Sample 4

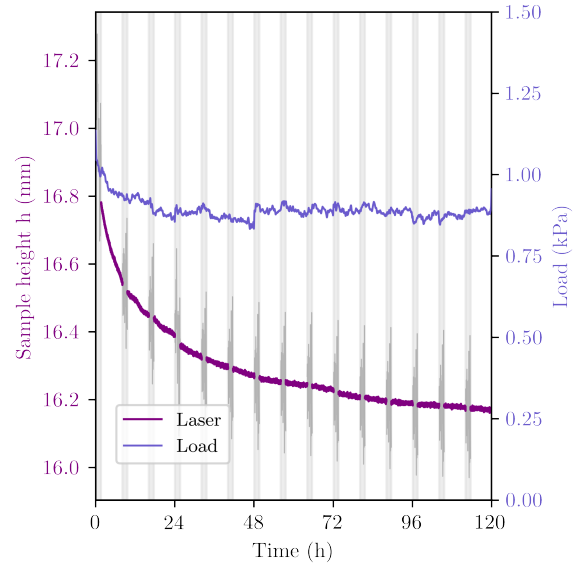


(d) Sample 5


**Figure A1.** Temporal evolution of the sample height, the applied load, and the sample temperature for ~~for~~ the sample not shown in Fig. 4. Grey shaded areas indicate time intervals affected by X-ray tomographic scans.

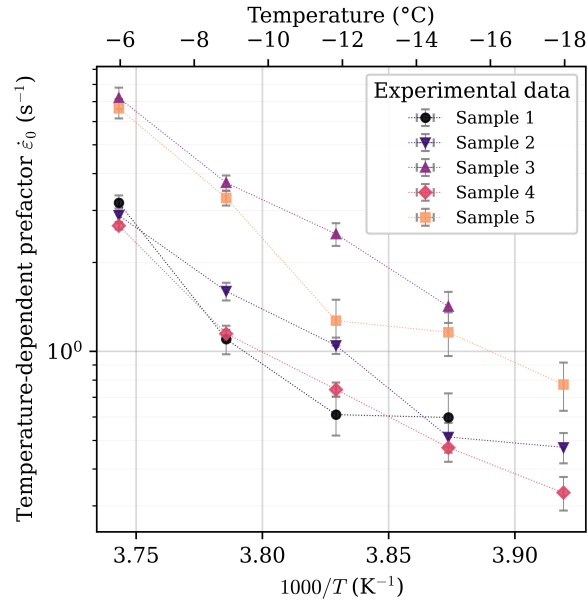

**Figure A2.** Strain rate prefactor  $\dot{\epsilon}_0$  as a function of inverse temperature for all studied samples.

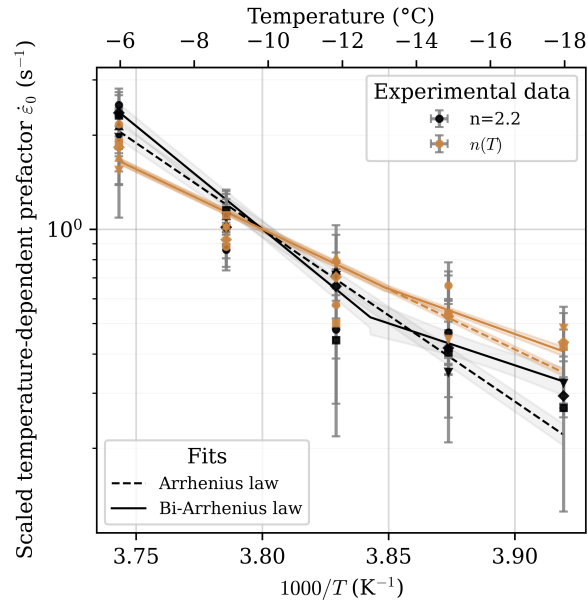

**Figure A3.** Scaled strain rate prefactor  $\dot{\epsilon}_0$  as a function of inverse temperature for all studied samples considering a constant stress exponent and the stress exponent temperature sensitivity proposed by Jones and Brunet (1978).

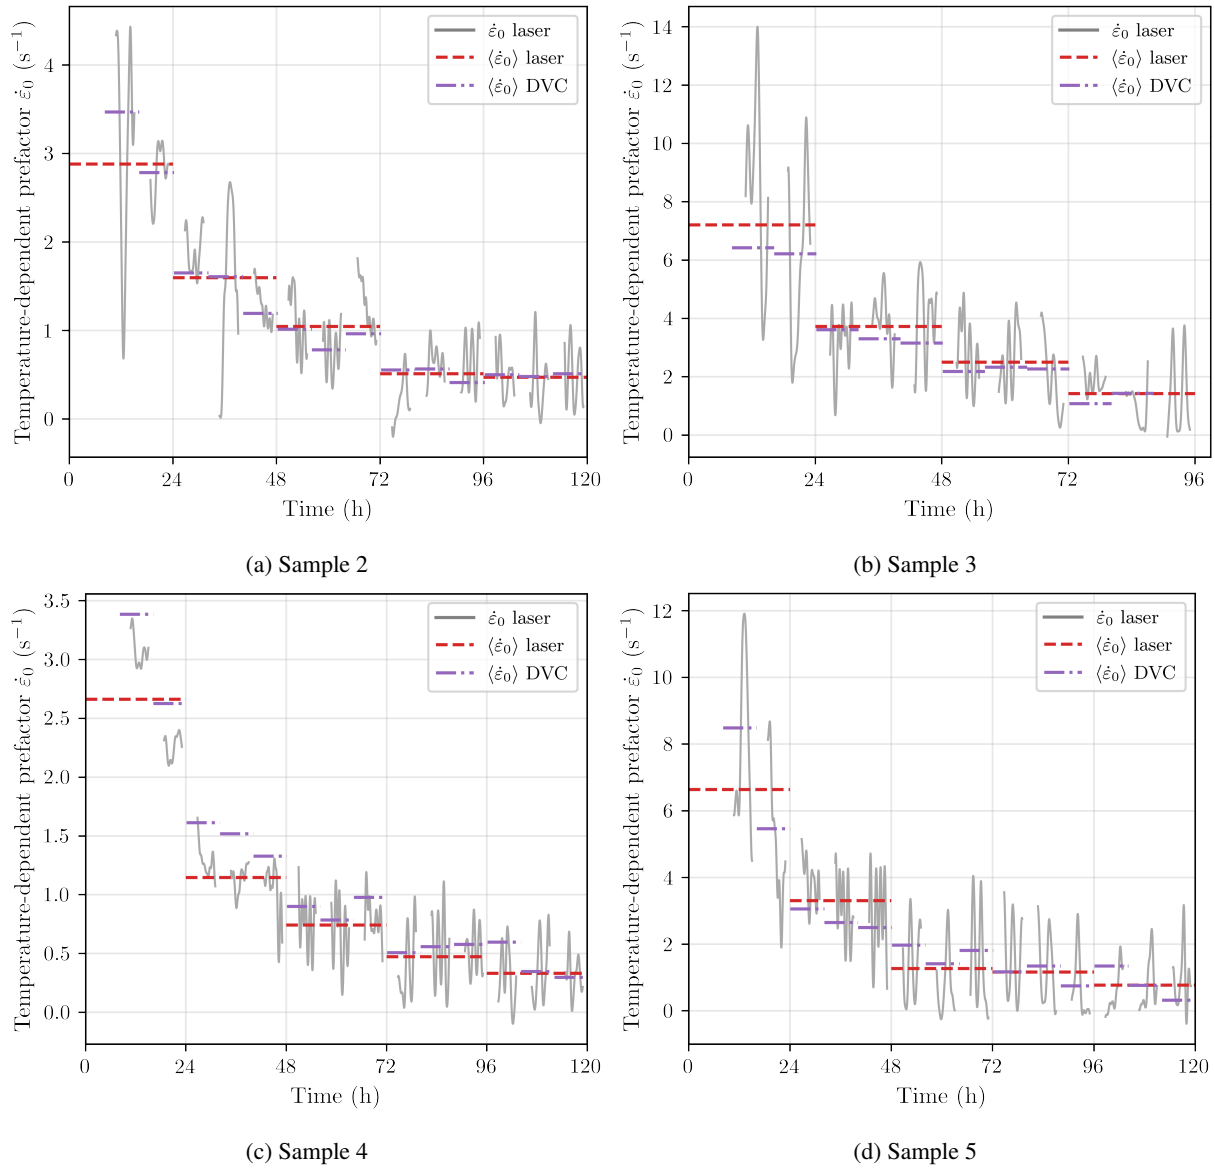

**Figure A4.** Temporal evolution of the strain rate prefactor  $\dot{\epsilon}_0$ , computed from laser displacement measurements and DVC.

## 350 References

- Bader, H.: Der schnee und seine metamorphose, vol. 3, Kommissionsverlag Kummerly & Frey, Druck von Aschmann & Scheller a.-g., Zurich, 1939.
- Barnes, P., Tabor, D., and Walker, J. C. F.: The Friction and Creep of Polycrystalline Ice, Proceedings of the Royal Society of London. Series A, Mathematical and Physical Sciences, 324, 127–155, <https://www.jstor.org/stable/77933>, publisher: Royal Society, 1971.

- 355 Barnett, T. P., Pierce, D. W., Hidalgo, H. G., Bonfils, C., Santer, B. D., Das, T., Bala, G., Wood, A. W., Nozawa, T., Mirin, A. A., Cayan, D. R., and Dettinger, M. D.: Human-Induced Changes in the Hydrology of the Western United States, *Science*, 319, 1080–1083, <https://doi.org/10.1126/science.1152538>, publisher: American Association for the Advancement of Science, 2008.
- Barnola, J. M., Raynaud, D., Korotkevich, Y. S., and Lorius, C.: Vostok ice core provides 160,000-year record of atmospheric CO<sub>2</sub>, *Nature*, 329, 408–414, <https://doi.org/10.1038/329408a0>, publisher: Nature Publishing Group, 1987.
- 360 Brun, E., David, P., Sudul, M., and Brunot, G.: A numerical model to simulate snow-cover stratigraphy for operational avalanche forecasting, *Journal of Glaciology*, 38, 13–22, <https://doi.org/10.3189/S0022143000009552>, 1992.
- Bucher, E.: Beitrag zu den theoretischen Grundlagen des Lawinenverbau, Ph.D. thesis, ETH Zürich, <https://doi.org/10.3929/ethz-a-000103484>, 1948.
- Budd, W. F. and Jacka, T. H.: A review of ice rheology for ice sheet modelling, *Cold Regions Science and Technology*, 16, 107–144, [https://doi.org/10.1016/0165-232X\(89\)90014-1](https://doi.org/10.1016/0165-232X(89)90014-1), 1989.
- 365 DeBeer, C. M. and Pomeroy, J. W.: Influence of snowpack and melt energy heterogeneity on snow cover depletion and snowmelt runoff simulation in a cold mountain environment, *Journal of Hydrology*, 553, 199–213, <https://doi.org/10.1016/j.jhydrol.2017.07.051>, 2017.
- Delmas, L.: Influence of snow type and temperature on snow viscosity, *Journal of Glaciology*, 59, 87–92, <https://doi.org/10.3189/2013JoG11J231>, 2013.
- 370 Dick, O., Calonne, N., Laurent, B., and Hagenmuller, P.: Monitoring dry snow metamorphism using 4D tomography across 20 experimental conditions, *Earth System Science Data*, 18, 2875–2889, <https://doi.org/10.5194/essd-18-2875-2026>, publisher: Copernicus GmbH, 2026.
- Glen, J. W.: The Creep of Polycrystalline Ice, *Proceedings of the Royal Society of London Series A*, 228, 519–538, <https://doi.org/10.1098/rspa.1955.0066>, aDS Bibcode: 1955RSPSA.228..519G, 1955.
- Hagenmuller, P., Chambon, G., Lesaffre, B., Flin, F., and Naaïm, M.: Energy-based binary segmentation of snow microtomographic images, *Journal of Glaciology*, 59, 859–873, <https://doi.org/10.3189/2013JoG13J035>, 2013.
- 375 Hagenmuller, P., Matzl, M., Chambon, G., and Schneebeli, M.: Sensitivity of snow density and specific surface area measured by microtomography to different image processing algorithms, *The Cryosphere*, 10, 1039–1054, <https://doi.org/10.5194/tc-10-1039-2016>, publisher: Copernicus GmbH, 2016.
- Horlings, B. I., Courville, Z., Murdza, A., and Keegan, K. M.: Applicability of two-phase modeling with compression experiments for snow compaction dynamics, *Cold Regions Science and Technology*, 229, 104 336, <https://doi.org/10.1016/j.coldregions.2024.104336>, 2025.
- 380 Jacka, T. H. and Maccagnan, M.: Ice crystallographic and strain rate changes with strain in compression and extension, *Cold Regions Science and Technology*, 8, 269–286, [https://doi.org/10.1016/0165-232X\(84\)90058-2](https://doi.org/10.1016/0165-232X(84)90058-2), 1984.
- Jones, S. J. and Brunet, J.-G.: Deformation of Ice Single Crystals Close to the Melting Point, *Journal of Glaciology*, 21, 445–455, <https://doi.org/10.3189/S0022143000033608>, 1978.
- 385 Kirchner, H. K., Michot, G., Narita, H., and Suzuki, T.: Snow as a foam of ice: Plasticity, fracture and the brittle-to-ductile transition, *Philosophical Magazine A*, 81, 2161–2181, <https://doi.org/10.1080/01418610108217141>, publisher: Taylor & Francis \_eprint: <https://doi.org/10.1080/01418610108217141>, 2001.
- Kojima, K.: A field experiment on the rate of densification of natural snow layers under low stresses, in: *Snow Mechanics Symposium*, 1975.
- Lehning, M., Bartelt, P., Brown, B., Fierz, C., and Satyawali, P.: A physical SNOWPACK model for the Swiss avalanche warning: Part II. Snow microstructure, *Cold Regions Science and Technology*, 35, 147–167, [https://doi.org/10.1016/S0165-232X\(02\)00073-3](https://doi.org/10.1016/S0165-232X(02)00073-3), 2002.
- 390

- Lejeune, Y., Dumont, M., Panel, J.-M., Lafaysse, M., Lapalus, P., Le Gac, E., Lesaffre, B., and Morin, S.: 57 years (1960–2017) of snow and meteorological observations from a mid-altitude mountain site (Col de Porte, France, 1325 m of altitude), *Earth System Science Data*, 11, 71–88, <https://doi.org/10.5194/essd-11-71-2019>, publisher: Copernicus GmbH, 2019.
- Li, Y., Keegan, K., and Baker, I.: Observations of creep of polar firn at different temperatures, *EGUsphere*, pp. 1–42, <https://doi.org/10.5194/egusphere-2024-2337>, publisher: Copernicus GmbH, 2024.
- Mellor, M. and Smith, J. H.: Strength studies of snow, 168, US Army Materiel Command, Cold Regions Research & Engineering Laboratory, [https://books.google.fr/books?hl=fr&lr=&id=ITsMi8AP41gC&oi=fnd&pg=PR4&dq=strength+studies+of+snow+mellor&ots=t\\_dg-csgQw&sig=OXLUv79KJUoYW5Wce76AXTDSKNc](https://books.google.fr/books?hl=fr&lr=&id=ITsMi8AP41gC&oi=fnd&pg=PR4&dq=strength+studies+of+snow+mellor&ots=t_dg-csgQw&sig=OXLUv79KJUoYW5Wce76AXTDSKNc), 1966.
- Mellor, M. and Testa, R.: Creep of Ice under Low Stress, *Journal of Glaciology*, 8, 147–152, <https://doi.org/10.3189/S0022143000020815>, 1969a.
- Mellor, M. and Testa, R.: Effect of Temperature on the Creep of Ice, *Journal of Glaciology*, 8, 131–145, <https://doi.org/10.3189/S0022143000020803>, 1969b.
- Meyssonnier, J., Philip, A., Capolo, L., and Mansuy, P.: Experimental studies of the viscoplasticity of ice and snow, in: *Mechanics of Natural Solids*, edited by Kolymbas, D. and Viggiani, G., pp. 203–221, Springer, Berlin, Heidelberg, [https://doi.org/10.1007/978-3-642-03578-4\\_9](https://doi.org/10.1007/978-3-642-03578-4_9), 2009.
- Morgan, V. I.: High-temperature ice creep tests, *Cold Regions Science and Technology*, 19, 295–300, [https://doi.org/10.1016/0165-232X\(91\)90044-H](https://doi.org/10.1016/0165-232X(91)90044-H), 1991.
- Morin, S., Horton, S., Techel, F., Bavay, M., Coléou, C., Fierz, C., Gobiet, A., Hagenmuller, P., Lafaysse, M., Ližar, M., Mitterer, C., Monti, F., Müller, K., Olefs, M., Snook, J. S., van Herwijnen, A., and Vionnet, V.: Application of physical snowpack models in support of operational avalanche hazard forecasting: A status report on current implementations and prospects for the future, *Cold Regions Science and Technology*, 170, 102 910, <https://doi.org/10.1016/j.coldregions.2019.102910>, 2020.
- Morris, E. M. and Wingham, D. J.: Densification of polar snow: Measurements, modeling, and implications for altimetry, *Journal of Geophysical Research: Earth Surface*, 119, 349–365, <https://doi.org/10.1002/2013JF002898>, 2014.
- Okada, Y., Hondoh, T., and Mae, S.: Basal glide of dislocations in ice observed by synchrotron radiation topography, *Philosophical Magazine A*, 79, 2853–2868, <https://doi.org/10.1080/01418619908212028>, publisher: Taylor & Francis \_eprint: <https://doi.org/10.1080/01418619908212028>, 1999.
- Quéno, L., Vionnet, V., Dombrowski-Etchevers, I., Lafaysse, M., Dumont, M., and Karbou, F.: Snowpack modelling in the Pyrenees driven by kilometeric-resolution meteorological forecasts, *The Cryosphere*, 10, 1571–1589, <https://doi.org/10.5194/tc-10-1571-2016>, publisher: Copernicus GmbH, 2016.
- Ramseier, R. O.: Growth and mechanical properties of river and lake ice, PhD Thesis, éditeur non identifié, 1975.
- Scapozza, C. and Bartelt, P. A.: The influence of temperature on the small-strain viscous deformation mechanics of snow: a comparison with polycrystalline ice, *Annals of Glaciology*, 37, 90–96, <https://doi.org/10.3189/172756403781815410>, 2003.
- Schleef, S., Löwe, H., and Schneebeli, M.: Hot-pressure sintering of low-density snow analyzed by X-ray microtomography and in situ microcompression, *Acta Materialia*, 71, 185–194, <https://doi.org/10.1016/j.actamat.2014.03.004>, 2014a.
- Schleef, S., Löwe, H., and Schneebeli, M.: Influence of stress, temperature and crystal morphology on isothermal densification and specific surface area decrease of new snow, *The Cryosphere*, 8, 1825–1838, <https://doi.org/10.5194/tc-8-1825-2014>, 2014b.

- Simson, A., Löwe, H., and Kowalski, J.: Elements of future snowpack modeling – Part 2: A modular and extendable Eulerian–Lagrangian numerical scheme for coupled transport, phase changes and settling processes, *The Cryosphere*, 15, 5423–5445, <https://doi.org/10.5194/tc-15-5423-2021>, publisher: Copernicus GmbH, 2021.
- 430 Spitzig, W. A. and Keh, A. S.: Orientation dependence of the strain-rate sensitivity and thermally activated flow in iron single crystals, *Acta Metallurgica*, 18, 1021–1033, [https://doi.org/10.1016/0001-6160\(70\)90058-1](https://doi.org/10.1016/0001-6160(70)90058-1), 1970.
- Stamati, O., Andò, E., Roubin, E., Cailletaud, R., Wiebicke, M., Pinzon, G., Couture, C., Hurley, R., Caulk, R., Caillerie, D., Matsushima, T., Bésuelle, P., Bertoni, F., Arnaud, T., Laborin, A., Rorato, R., Sun, Y., Tengattini, A., Okubadejo, O., Colliat, J.-B., Saadatfar, M., Garcia, F., Papazoglou, C., Vego, I., Brisard, S., Dijkstra, J., and Birmipilis, G.: spam: Software for Practical Analysis of Materials, *Journal of*
- 435 *Open Source Software*, 5, 2286, <https://doi.org/10.21105/joss.02286>, 2020.
- Steinemann, S.: Results of Preliminary Experiments on the Plasticity of Ice Crystals, *Journal of Glaciology*, 2, 404–416, <https://doi.org/10.3189/002214354793702533>, 1954.
- Vionnet, V., Brun, E., Morin, S., Boone, A., Faroux, S., Le Moigne, P., Martin, E., and Willemet, J.-M.: The detailed snowpack scheme Crocus and its implementation in SURFEX v7.2, *Geoscientific Model Development*, 5, 773–791, [https://doi.org/10.5194/gmd-5-773-](https://doi.org/10.5194/gmd-5-773-2012)
- 440 2012, publisher: Copernicus GmbH, 2012.
- Védrine, L. and Hagenmuller, P.: Revisiting snow settlement with microstructural knowledge, *EGUsphere*, pp. 1–32, <https://doi.org/10.5194/egusphere-2025-4193>, publisher: Copernicus GmbH, 2025.
- Védrine, L., Hagenmuller, P., Gélébart, L., Montagnat, M., and Bernard, A.: Role of Ice Mechanics on Snow Viscoplasticity, *Geophysical Research Letters*, 51, e2023GL107 676, <https://doi.org/10.1029/2023GL107676>, 2024.
- 445 Védrine, L., Hagenmuller, P., Gélébart, L., Montagnat, M., and Löwe, H.: Sensitivity of the viscoplasticity of polycrystals to porosity and pore-to-crystal size ratio, *Acta Materialia*, 301, 121 507, <https://doi.org/https://doi.org/10.1016/j.actamat.2025.121507>, 2025.
- Védrine, L., Brun, M., Bozon, M., Laurent, B., and Hagenmuller, P.: Dataset for: Sensitivity of snow viscoplasticity to temperature: evidence from controlled creep experiments, <https://doi.org/10.5281/zenodo.18824419>, 2026.
- Wiese, M. and Schneebeli, M.: Snowbreeder 5: a Micro-CT device for measuring the snow-microstructure evolution under the simultaneous
- 450 influence of a temperature gradient and compaction, *Journal of Glaciology*, 63, 355–360, <https://doi.org/10.1017/jog.2016.143>, 2017.
- Wollgramm, P., Bürger, D., Parsa, A. B., Neuking, K., and Eggeler, G.: The effect of stress, temperature and loading direction on the creep behaviour of Ni-base single crystal superalloy miniature tensile specimens, *Materials at High Temperatures*, 33, 346–360, <https://doi.org/10.1080/09603409.2016.1186414>, publisher: Taylor & Francis \_eprint: <https://doi.org/10.1080/09603409.2016.1186414>, 2016.
- 455 Yosida, Z.: Physical studies on deposited snow thermal properties., *Contributions from the Institute of Low Temperature Science, Ser.A.*, 7, 19–74, <https://cir.nii.ac.jp/crid/1570009749325699456>, 1955.